


5.3 Chain-Growth Polymerization

Principal Steps of Chain-Growth Polymerizations


- monomers add rapidly to the active center of a growing chain until that center is deactivated

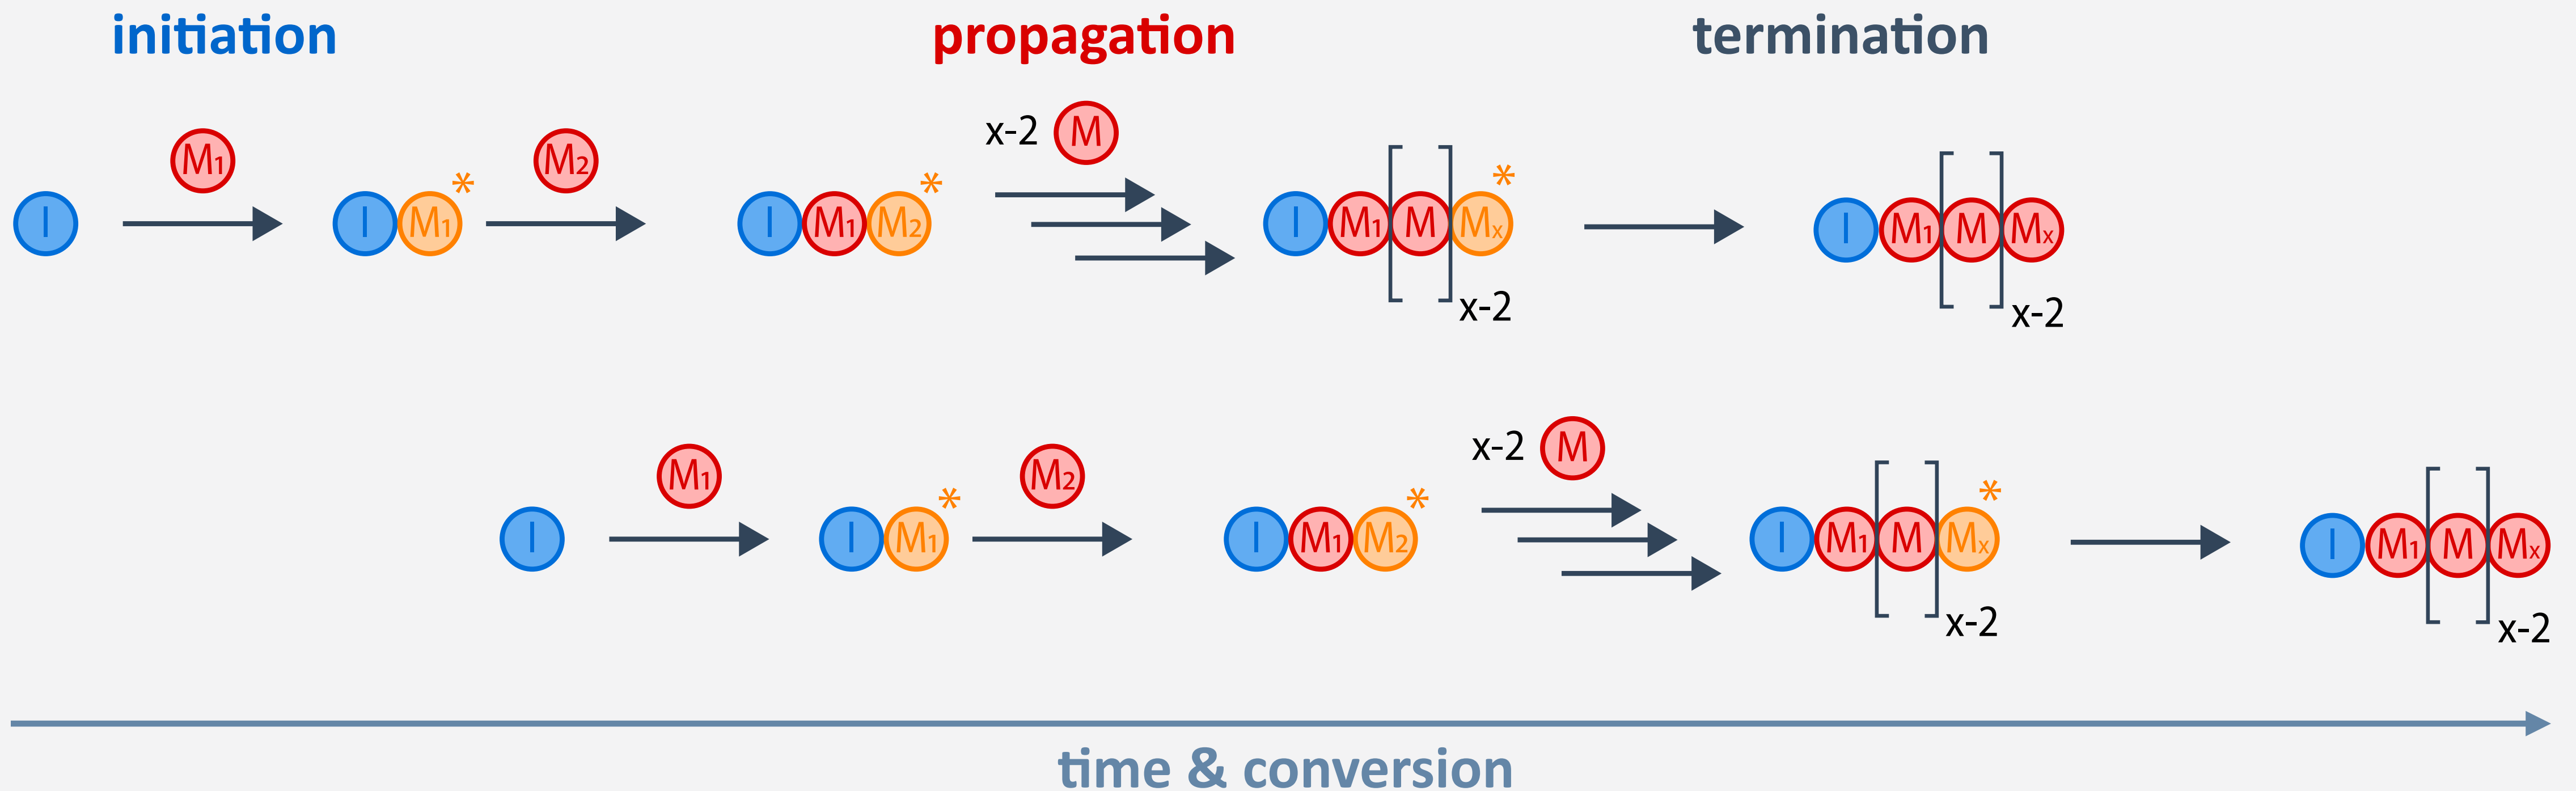

- polymerizations require an **initiator** that attacks a first monomer and creates an **active center**
- during propagation, **monomers** add consecutively to the **active center** of a growing polymer chain
- initiation continuously occurs during entire polymerization time
- termination is a stochastic event, greatly determining the molecular weight distribution

Molar Mass Distribution in Chain Growth Polymerizations

- Flory-Schulz-type distribution is expected (at least, in the low conversion regime)

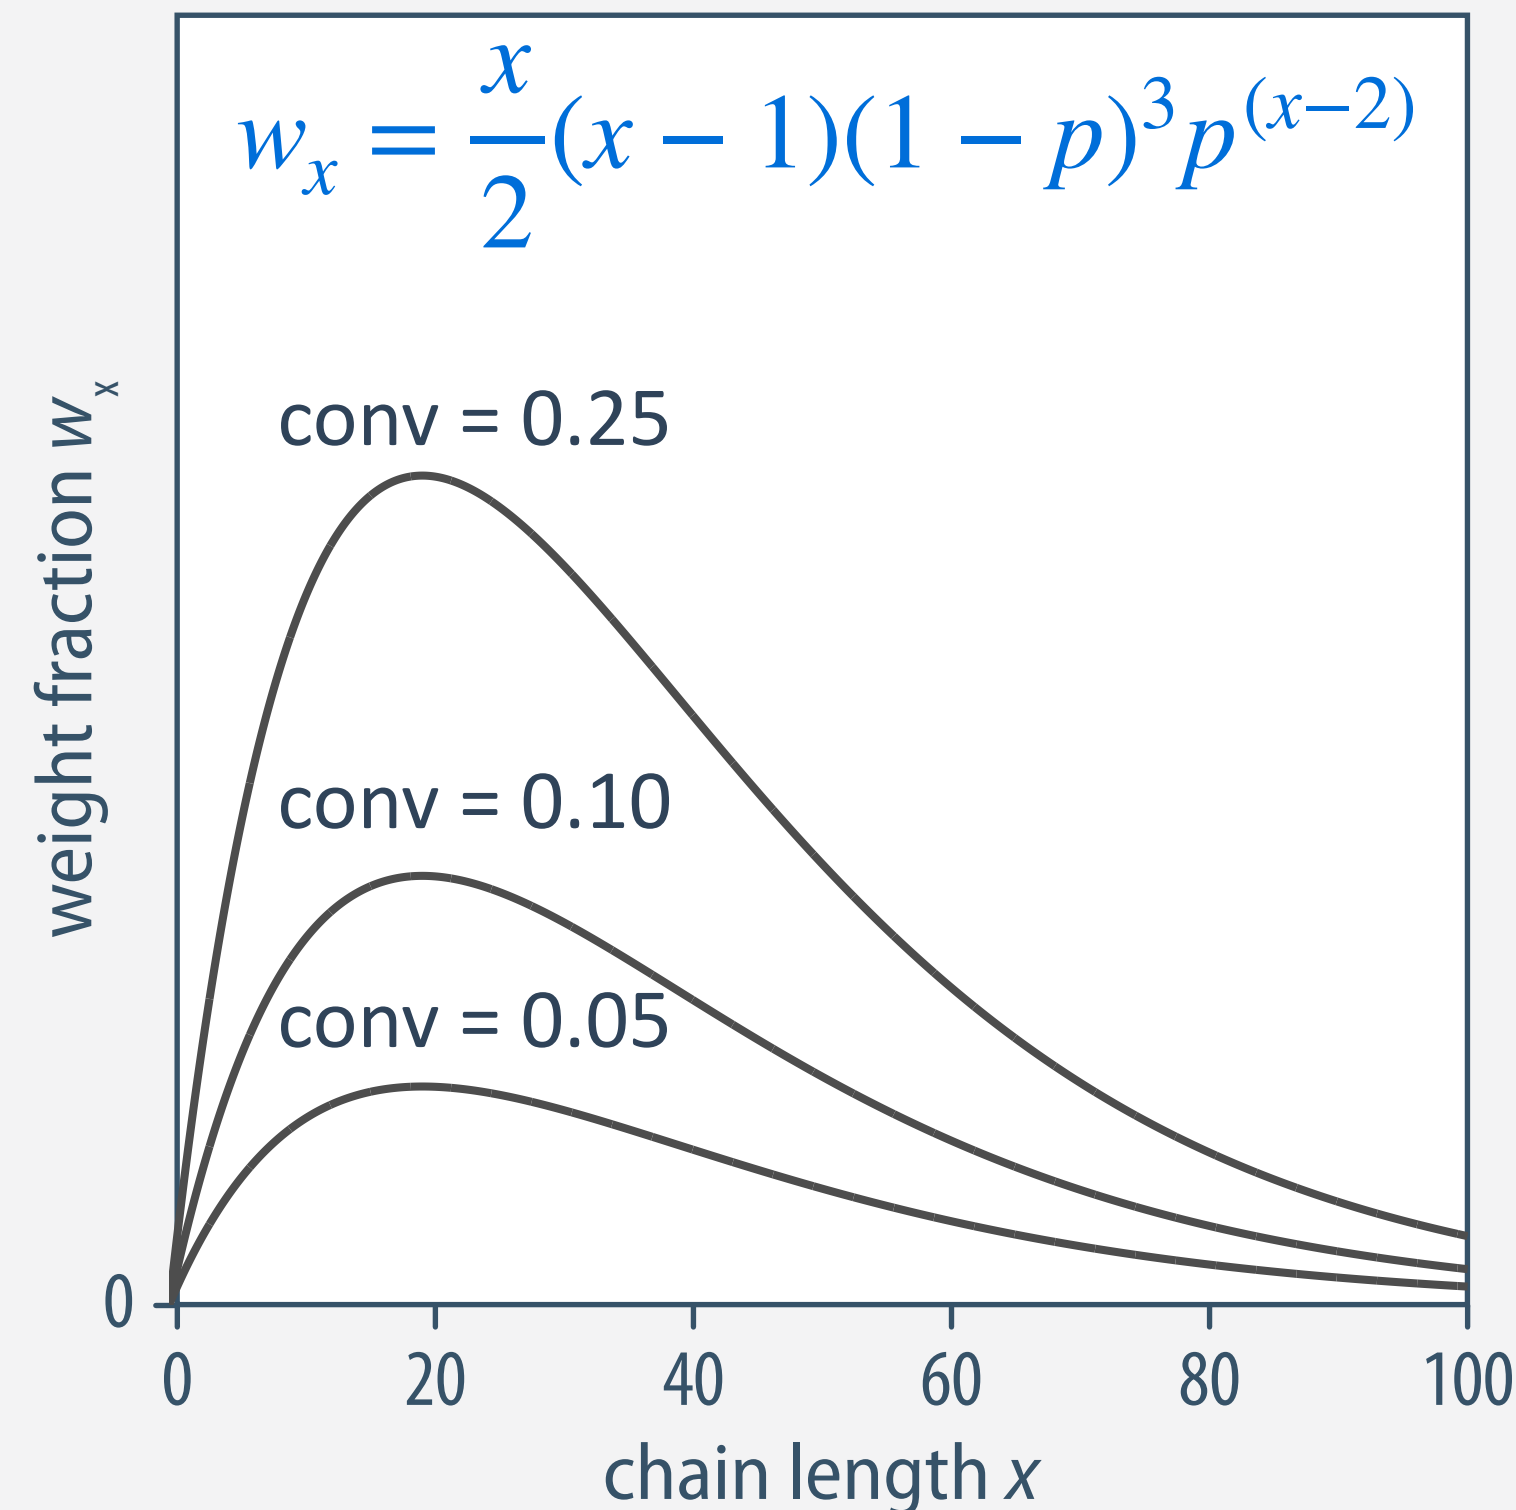

- high molar mass polymer is formed from the beginning in a free radical polymerization
- with increasing time and conversion, the number of each species increases continuously


Free Radical Polymerizations

Initiation and Propagation in Free Radical Polymerizations

- initiator decomposition (slow)




- initiation (fast)

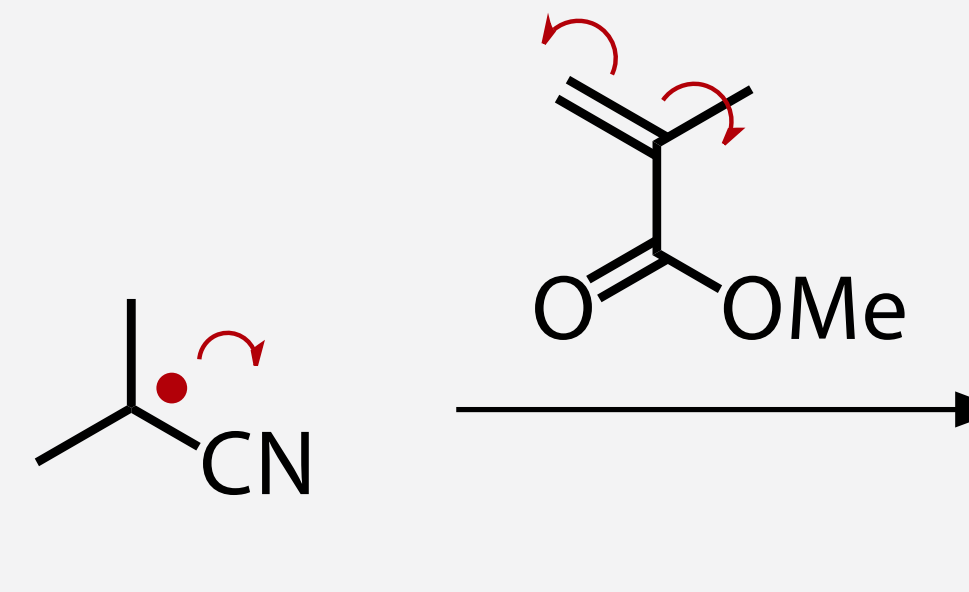

not all generated radicals
initiate chains
concentrations not identical
efficiency factor f


- propagation (chain growth)

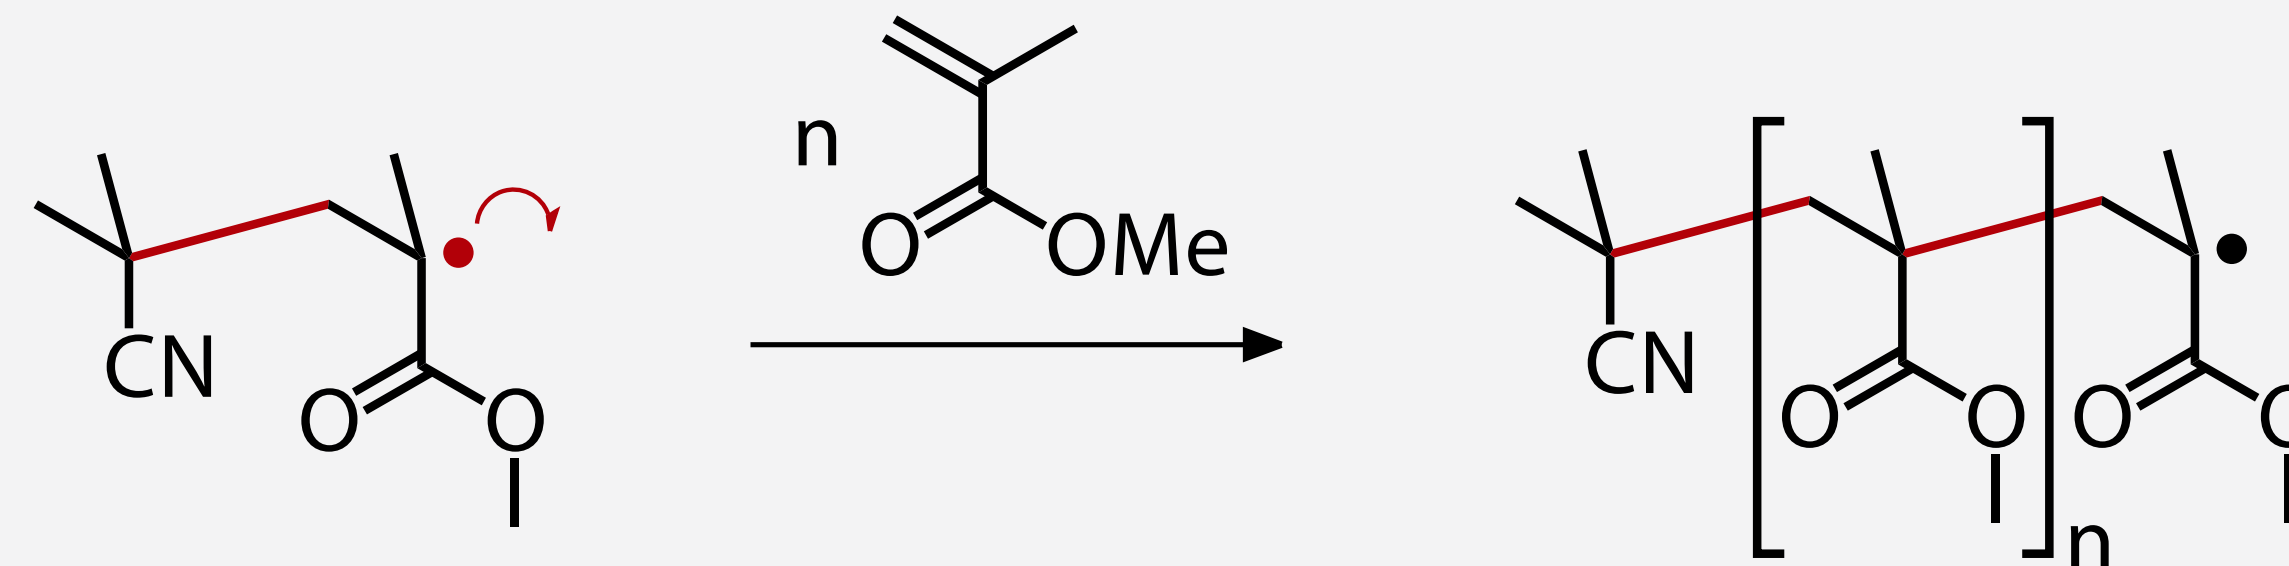


- reaction with a monomer instead of immediate recombination with **efficiency factor $f \approx 0.3\text{--}0.8$**
- initiator decomposition** is a statistical process, occurring slowly throughout polymerization process
- radical life time $\tau = 0.1\text{--}10$ s, about **100–10'000 propagation steps** before chain terminates

Termination Reactions in Radical Polymerizations

- termination by **radical combination**

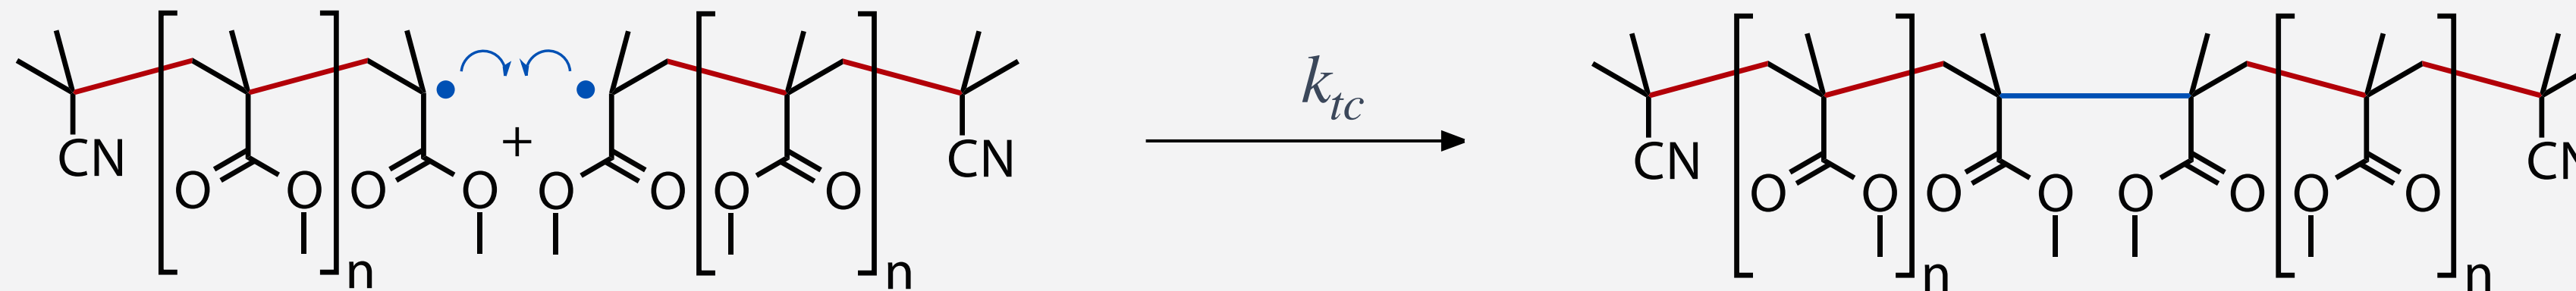


- termination by **disproportionation**

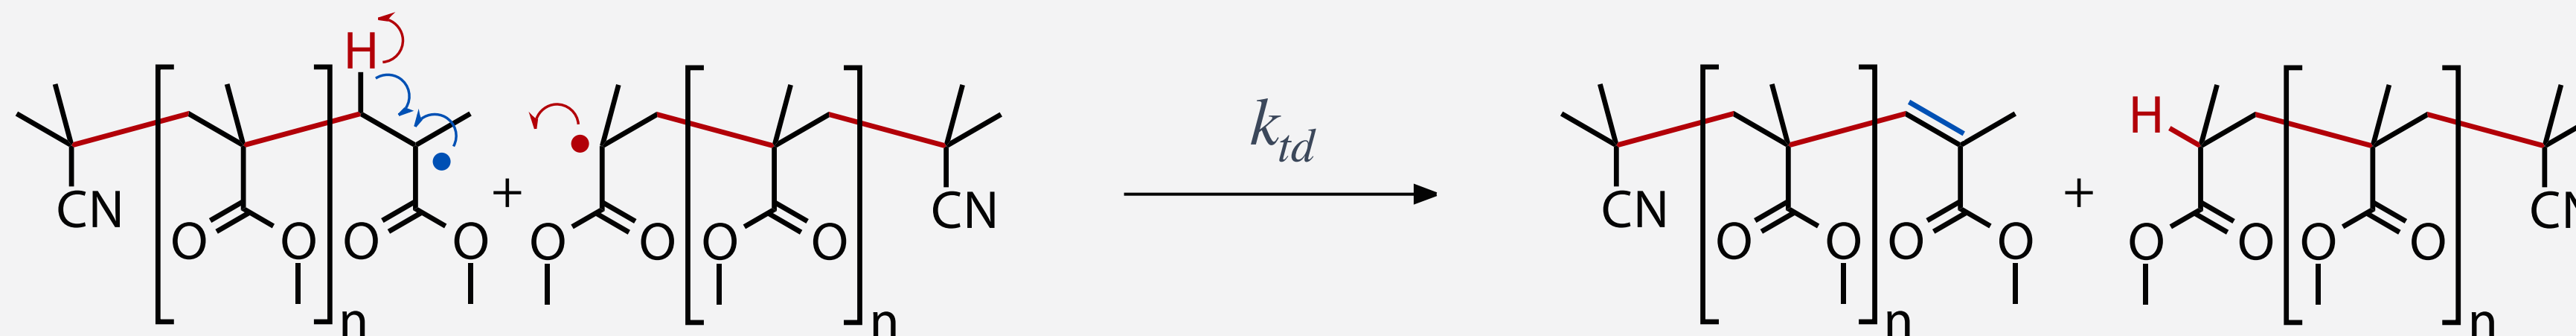

- termination by combination and disproportionation often occur both and are stochastic processes


Important Vinyl Monomers in Radical Polymerization




ethene
ethylene (PE)




chloroethene
vinyl chloride (PVC)

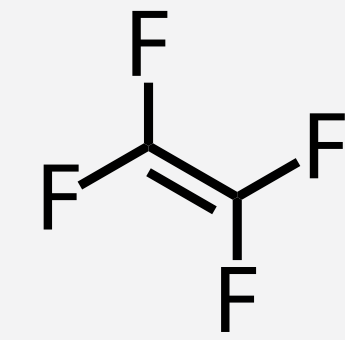


tetrafluoroethene
(PTFE, Teflon)




butadiene
(PB)




2-methylbutadiene
isoprene (PI)

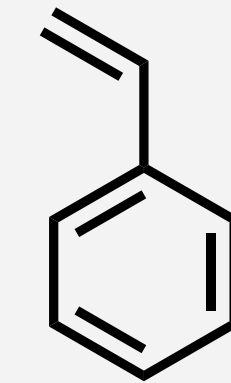


phenylethene
styrene (PS)

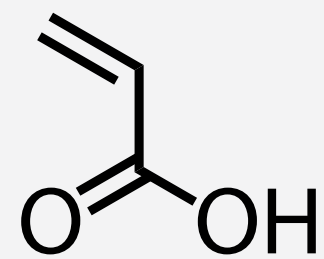

propenoic acid
acrylic acid (PAA)

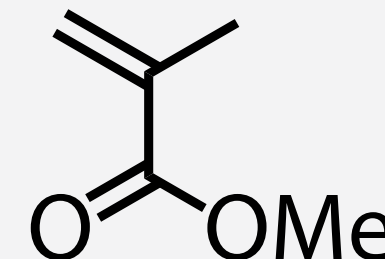

methyl 2-methylpropenoate
methyl **meth**acrylate (PMMA)

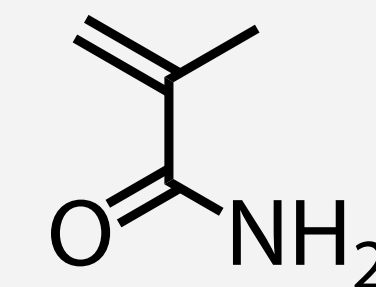


2-methylpropenoic amide
methacrylamide (for PMAAm)


- vinyl monomers mostly with +M or –M substituents used for technologically relevant polymers

Examples of Radical Initiators and their Decomposition


- azobis(isobutyronitrile) (AIBN)

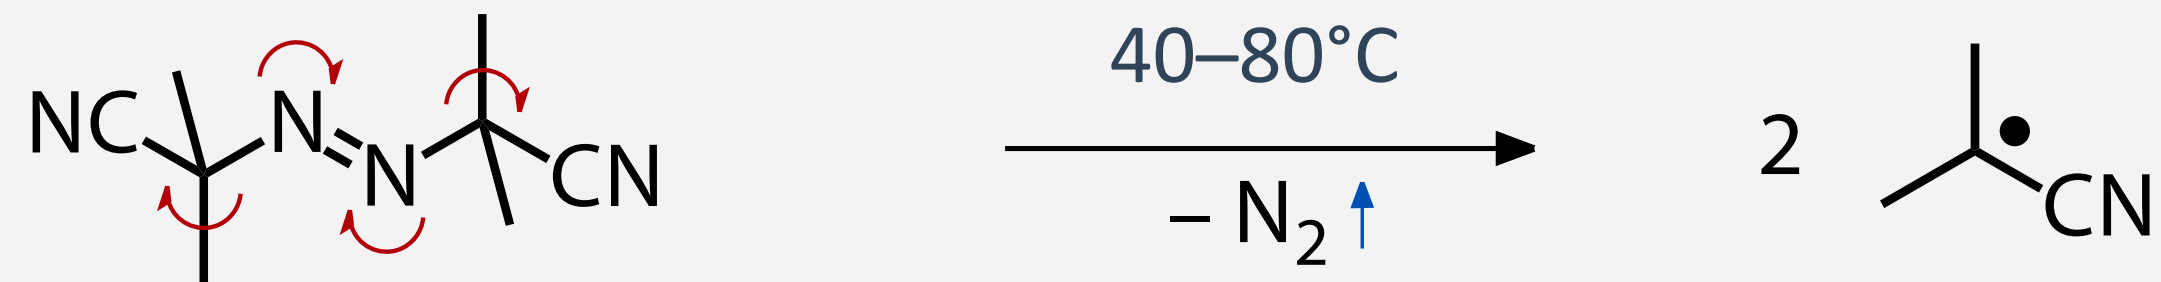


- di(tert.-butyl peroxide) (DTPO)

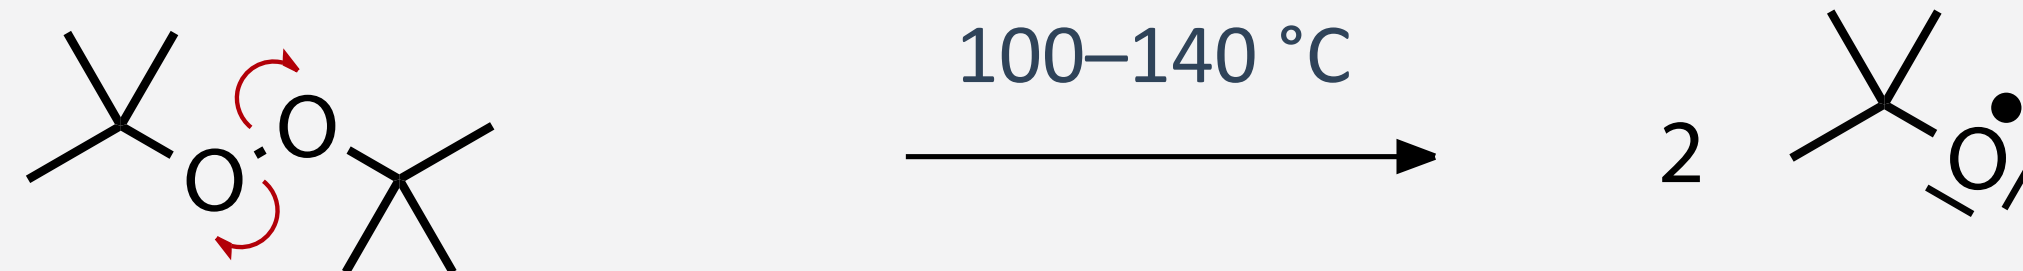

- dicumyl peroxide (DCPO)

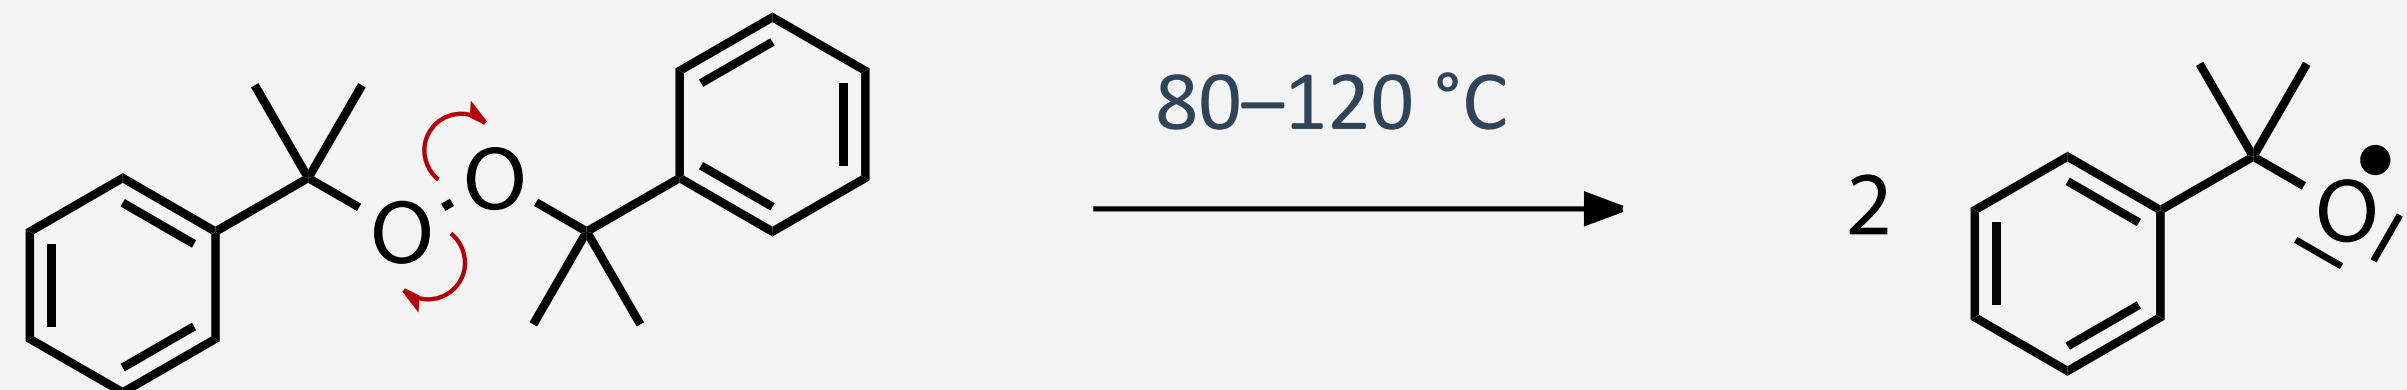

- dibenzoyl peroxide (DBPO)

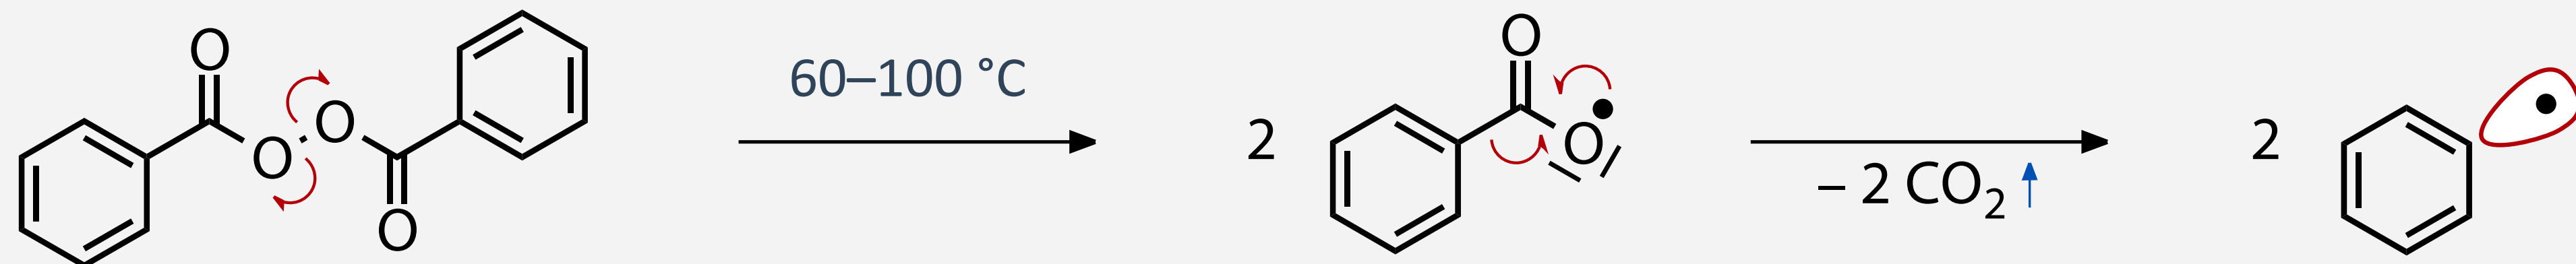

- suitable decomposition rates ($k_d = 10^{-7}$ – 10^{-6} M s^{-1}) for different temperature regimes
- goal is to balance initiation and termination reaction rates to reach “steady state” conditions

Kinetics of Chain Growth Polymerization

rate of initiation

$$R_i = \frac{d[R^\bullet]}{dt} = 2fk_d[I]$$

rate of propagation

$$R_p = -\frac{d[M]}{dt} = \sum k_p[M_i^\bullet][M]$$

rate of termination

$$R_t = -\frac{d[M^\bullet]}{dt} = 2k_t[M^\bullet]^2$$

- **steady-state-conditions:**

$$R_i = R_t$$

$$R_p = k_p \sqrt{\frac{fk_d}{k_t}} \sqrt{[M][I]}$$

$$\text{with } k_t = k_{tc} + k_{td}$$



- **kinetic chain length:**

$$\bar{\nu} = \frac{R_p}{R_i} = \frac{R_p}{R_t} = \frac{k_p[M]}{2(fk_i k_t[I])^{1/2}} \propto \frac{[M]}{\sqrt{[I]}}$$

- steady state conditions required for stable polymerization, results in reaction order 0.5 for initiator
- increasing initiator concentration **increases polymerization rate** but results in **decreased molar mass**

High Conversion Effects


- gel effect: diffusion-controlled termination (auto-acceleration of propagation)
- glass effect: monomers get trapped, if the matrix becomes increasingly glassy

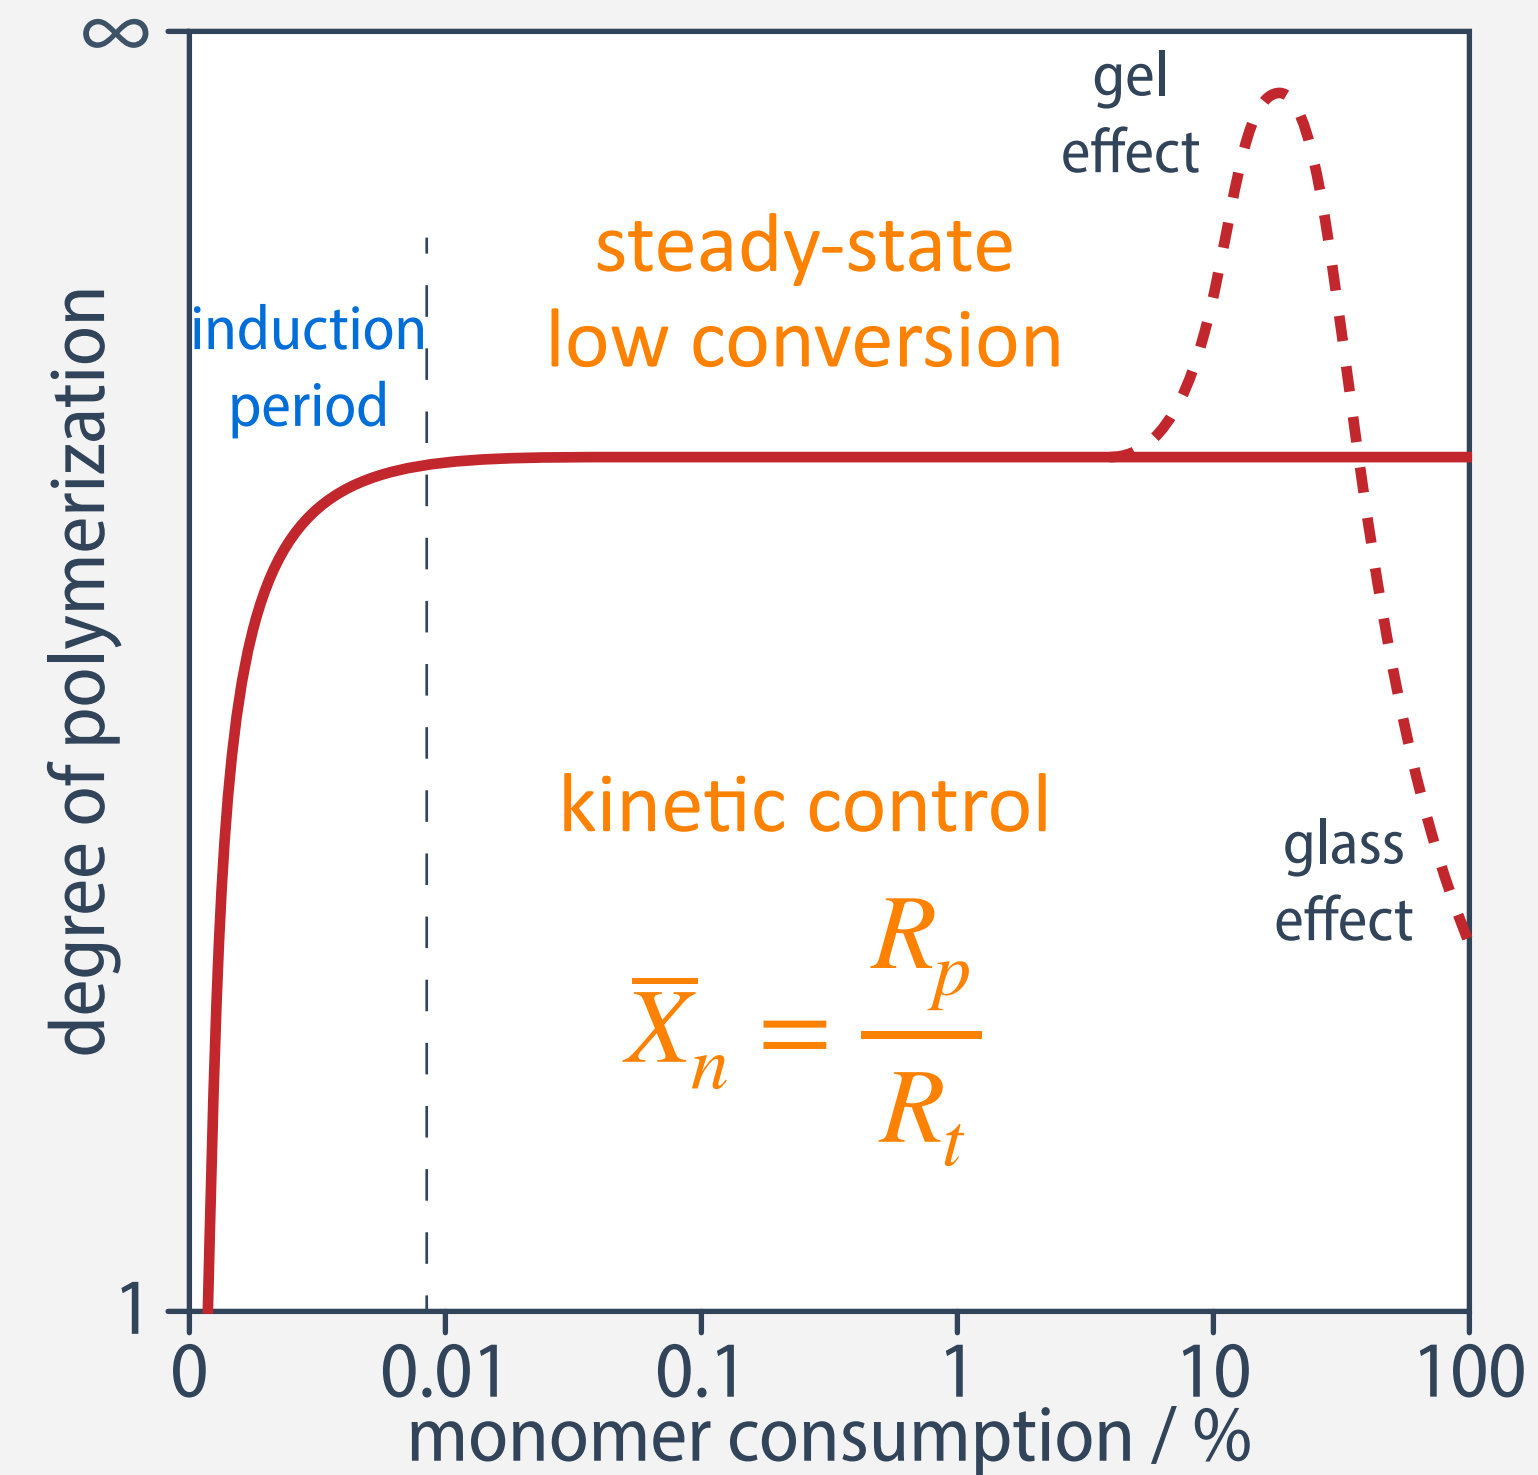
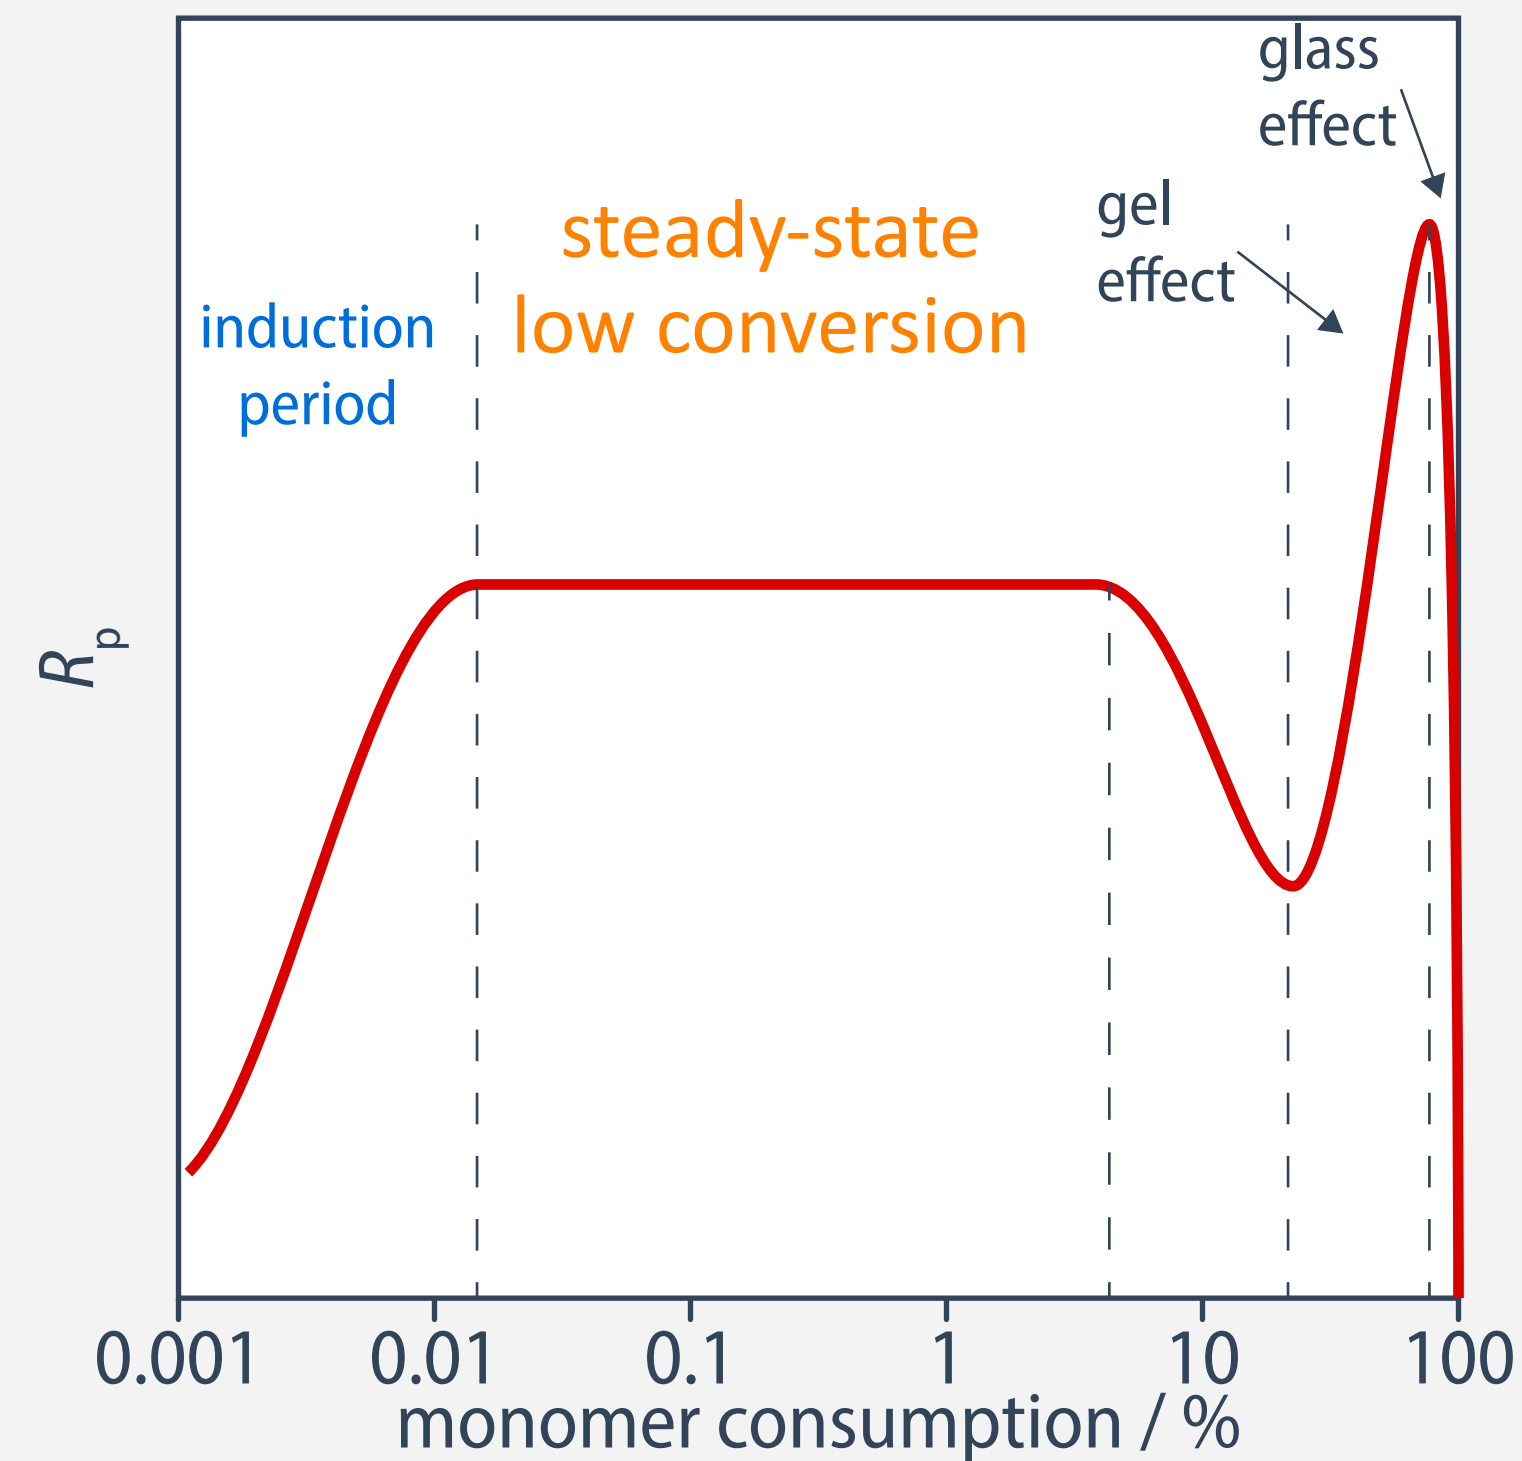


- steady-state conditions are not maintained at medium to high conversions, causing a loss of control over polymerization rate and molar mass distribution

Dispersity in the Low Conversion Regime

- in reality, termination may occur via both pathways
- transfer reactions and side-reactions are not taken into consideration

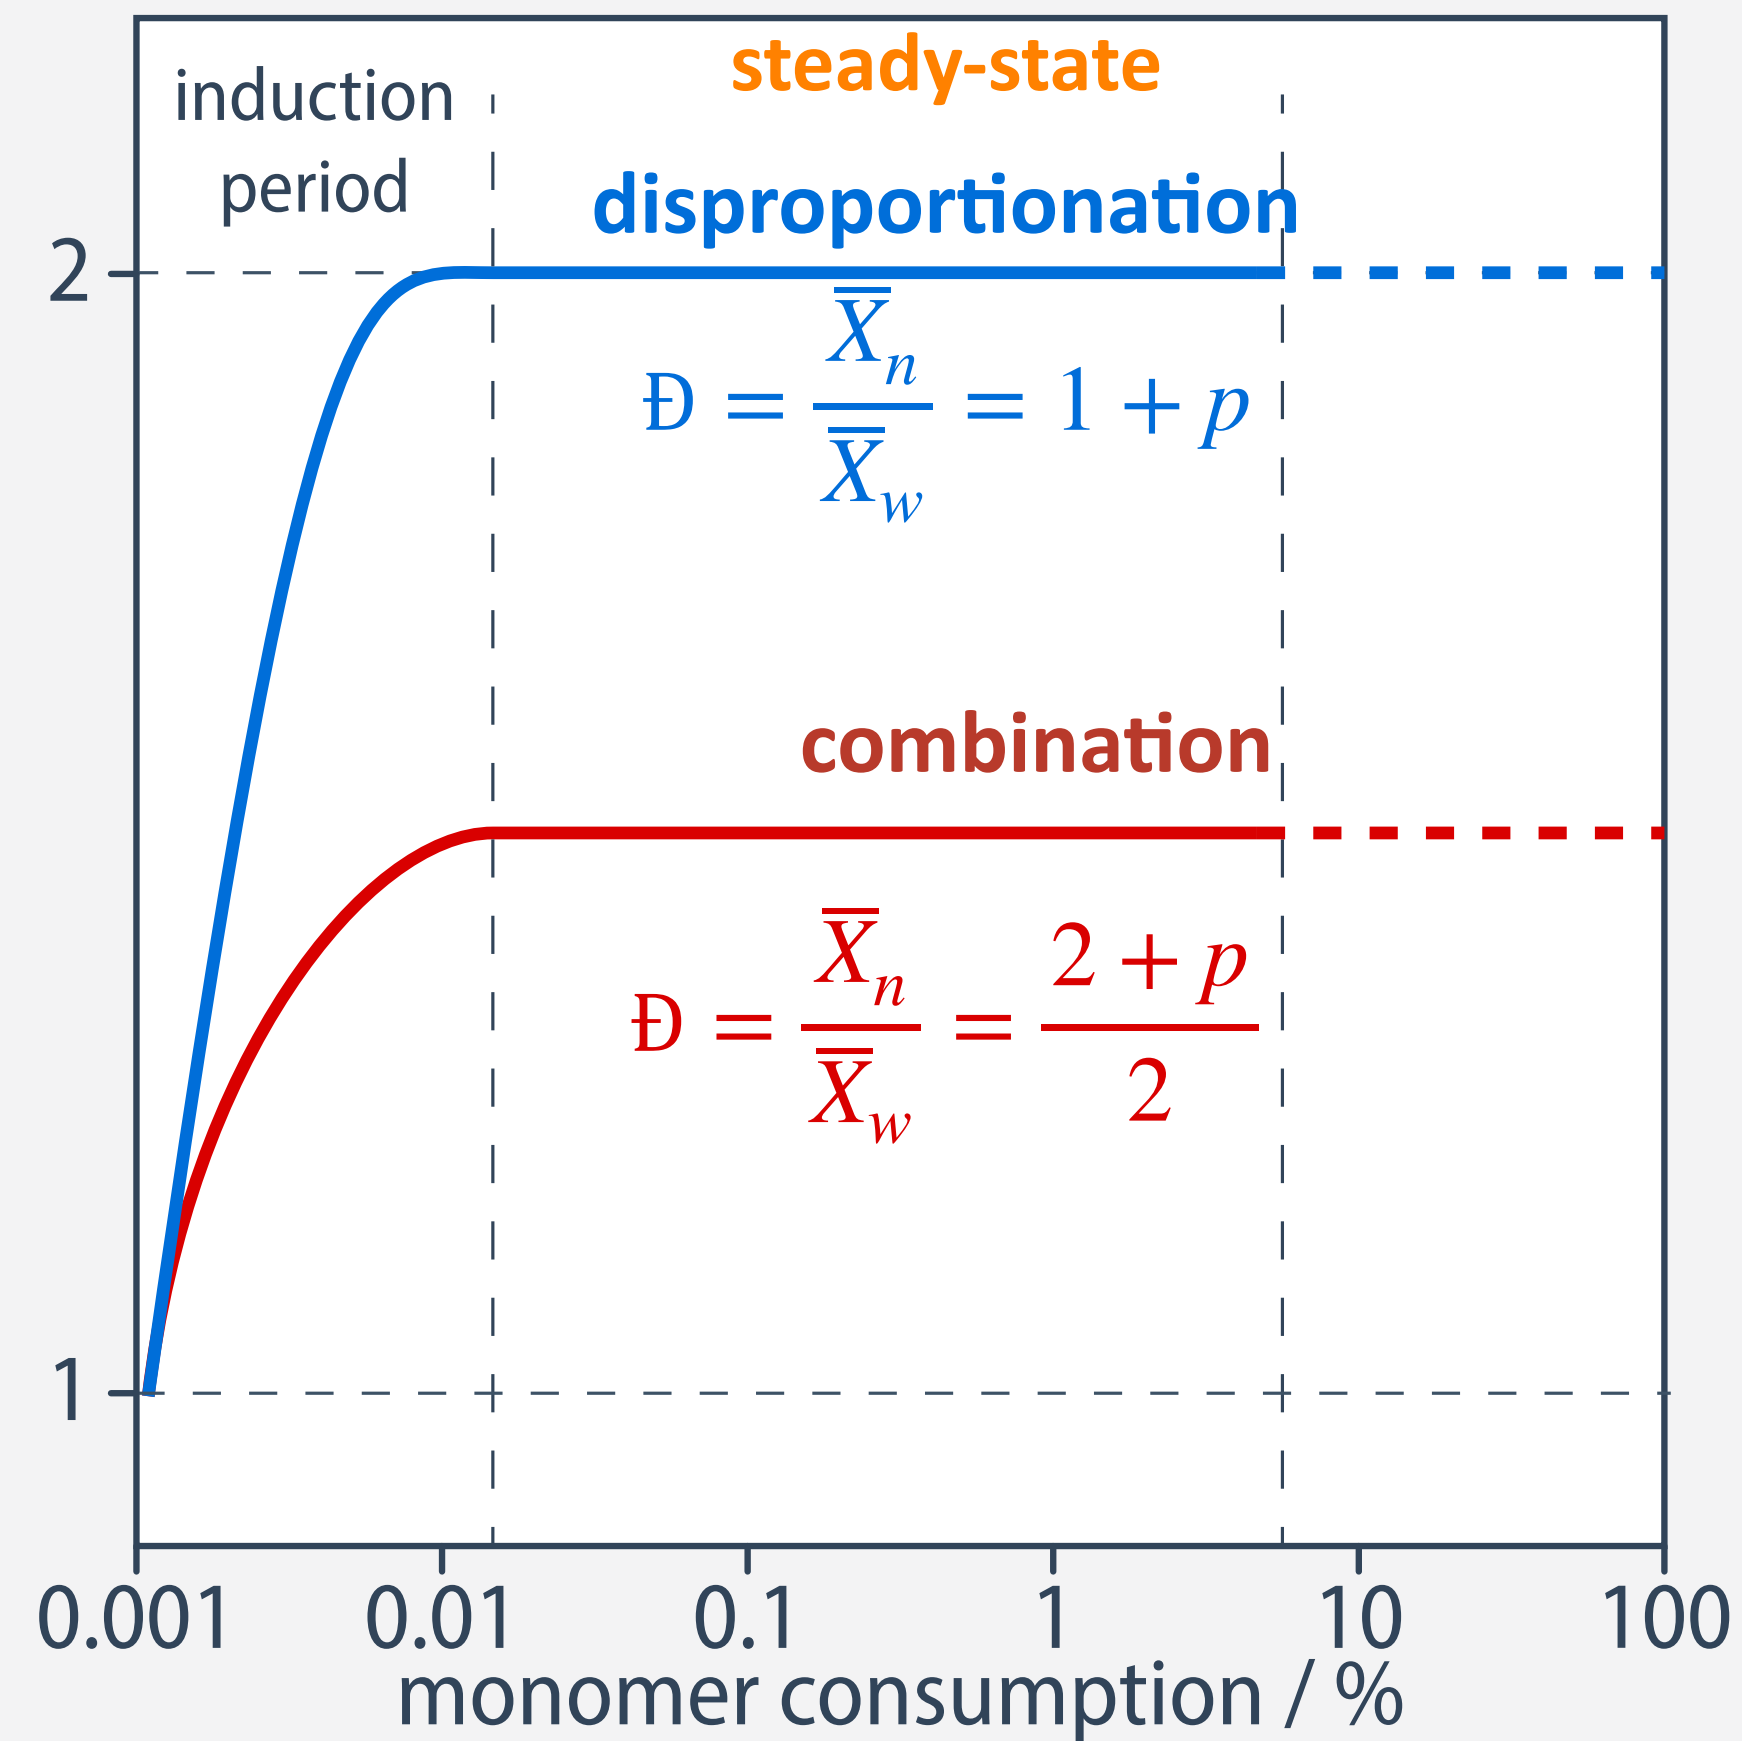

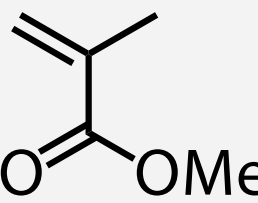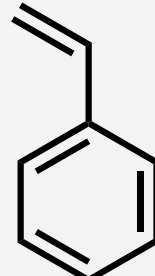
	disproportionation	combination
	0%	100%
	79%	21%
	23%	77%

- molecular weight distribution and dispersity depend on termination mechanism

Free Cationic Polymerization

Cationic Polymerization of Vinyl Monomers





- polymerization started by reaction of a vinyl monomer with a strong (cationic) electrophile

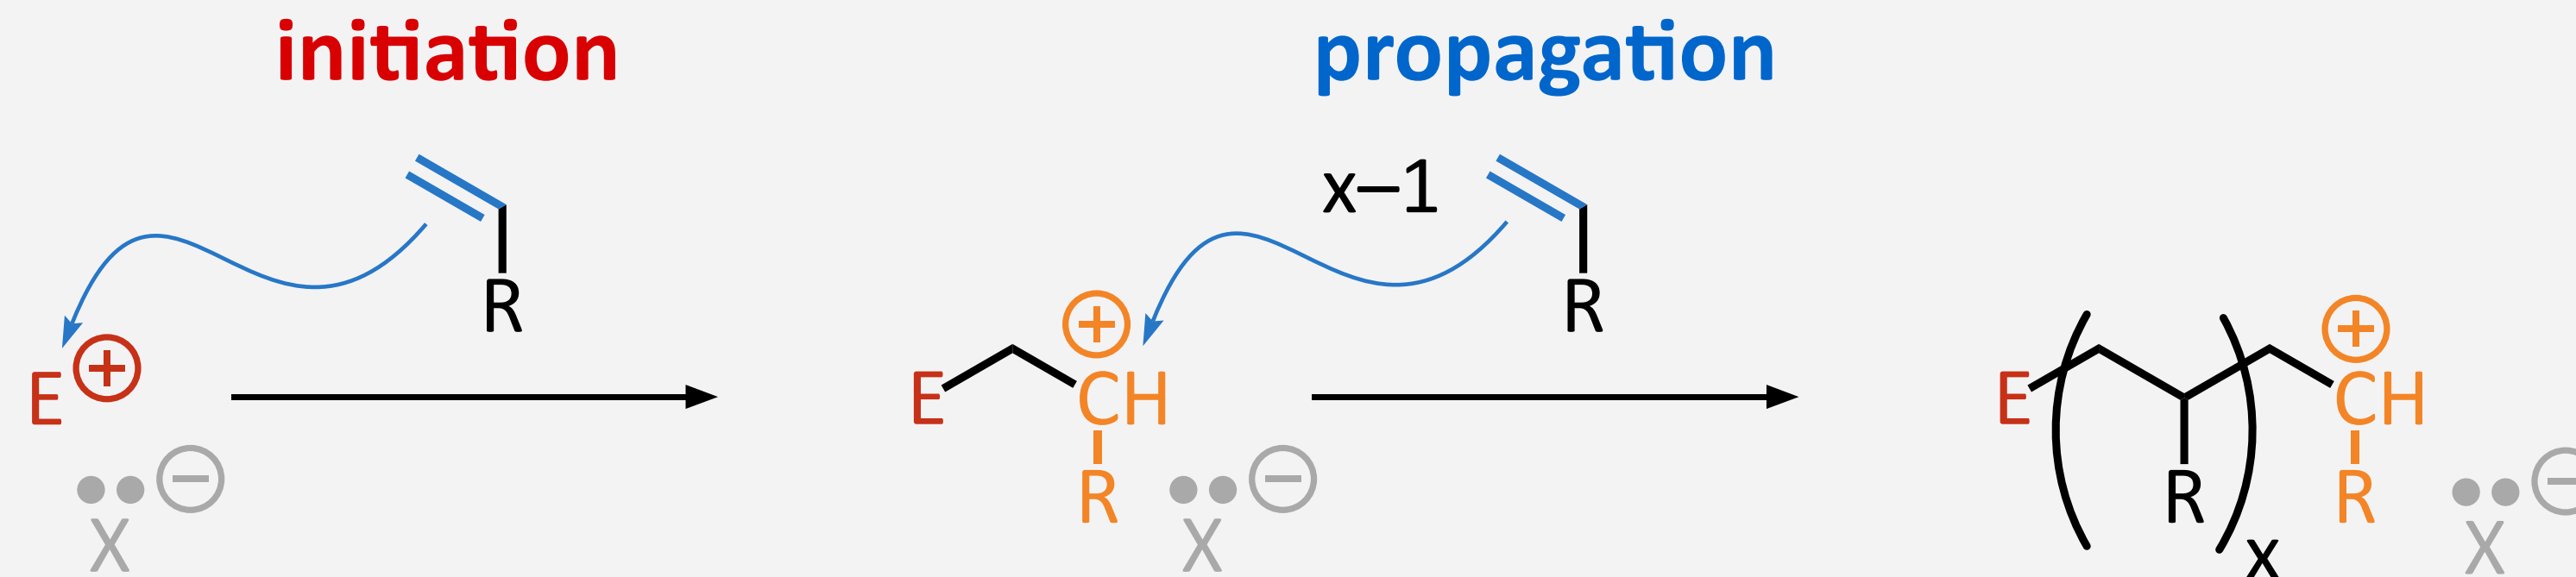


- initiation is like the first step in electrophilic addition to a double bond (of the monomer)
 - reactive chain end is a (highly electron-deficient, electrophilic, reactive) carbocationic intermediate
 - monomer must have electron-donating residue R to be reactive, but *also* to stabilize chain end
 - initiator must be sufficiently strong Lewis or Brønsted acid, hence counterion must be well stabilized
 - counterion must be well stabilized / non-nucleophilic *also* to avoid completing the addition reaction
 - carbocationic chain end and counterion are close ion pairs in organic solvents (even when not shown)
-
- cationic polymerization like first step of electrophilic addition, while avoiding the second step**

Examples of Initiators for Cationic Polymerization of Vinyl Monomers


- Brønsted acids with large, resonance-stabilized, non-coordinating, non-nucleophilic counterions

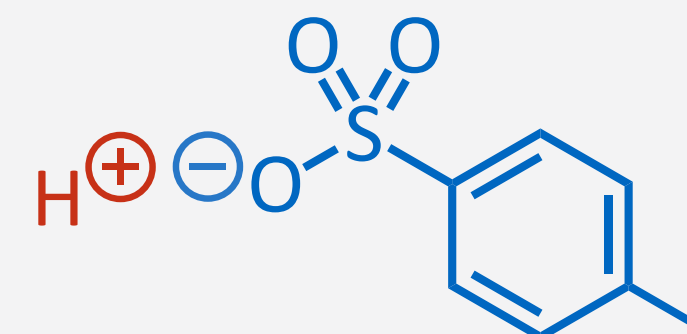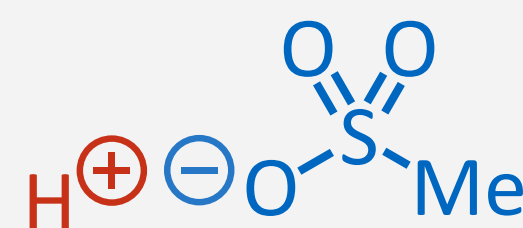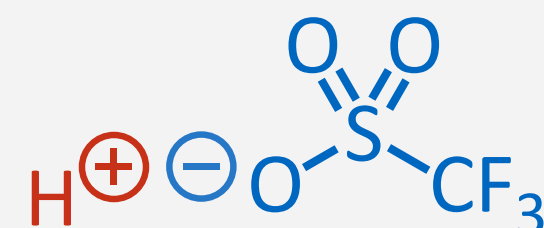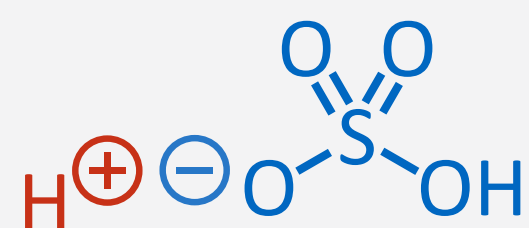

- hydrogen halogenides are inefficient as initiators
- halogenide counterions are still too nucleophilic, complete addition to the double bond
- Lewis acids such as halides of metals in high oxidation states (BF_3 , BCl_3 , AlCl_3 , TiCl_4 , SnCl_4 , SbCl_5 , ZnCl_2)
 - two coinitiators that deliver a proton as the actual initiator

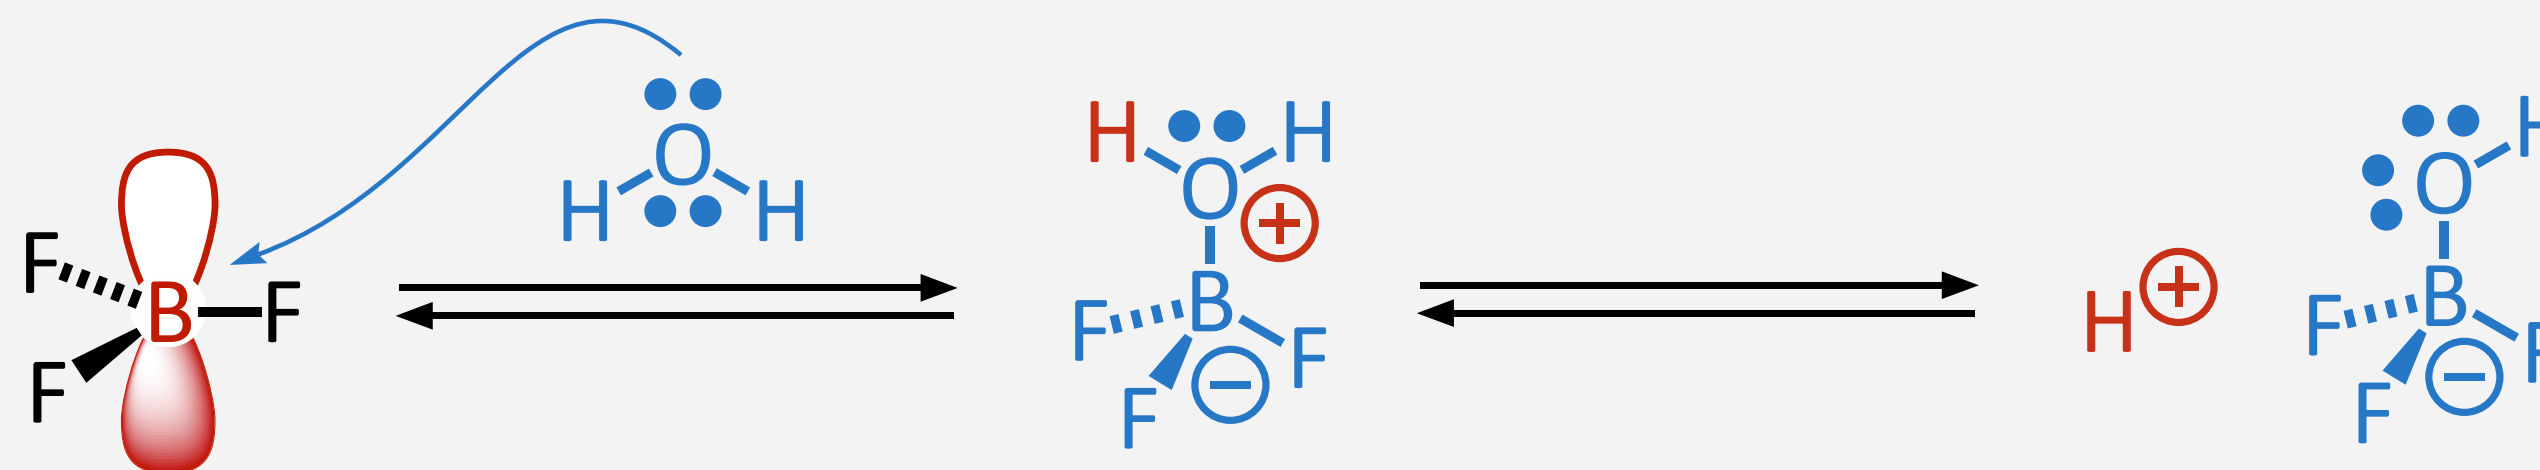


- two coinitiators, one with a good leaving group that generates a carbocation

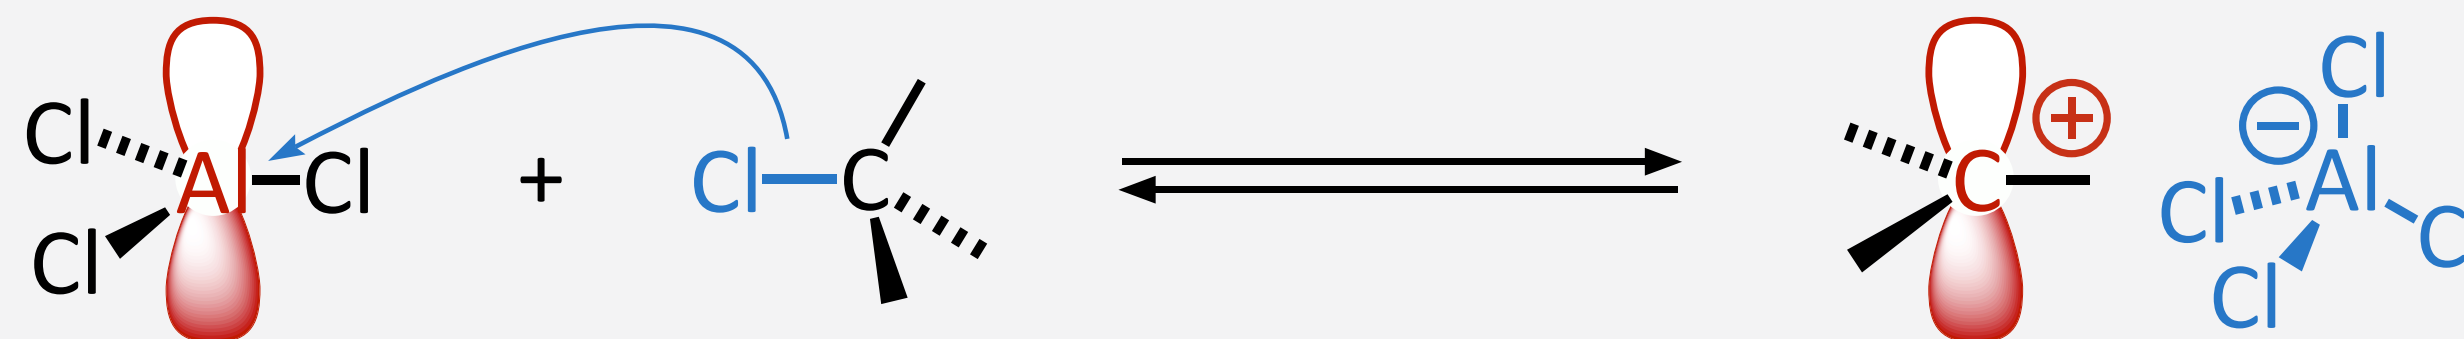


Examples of Monomers for Cationic Polymerization of Vinyl Monomers


- +M substituents or 1,1-dialkyl substitution (stabilized and polarized by hyperconjugation)

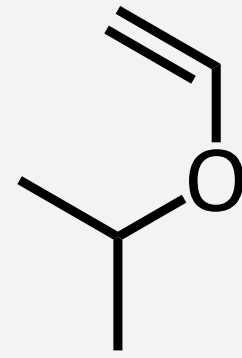


vinyl ethers

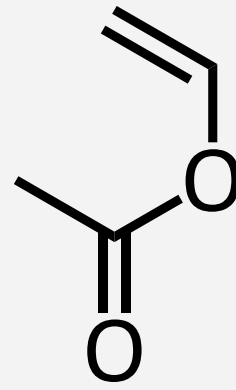


vinyl esters

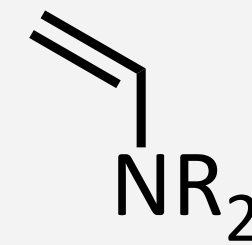


vinyl amines

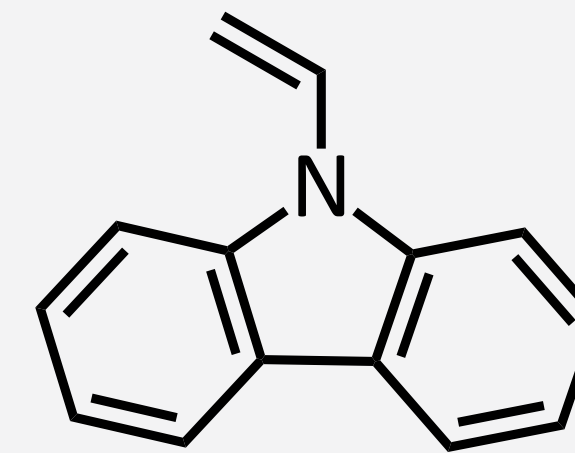

vinyl carbazol

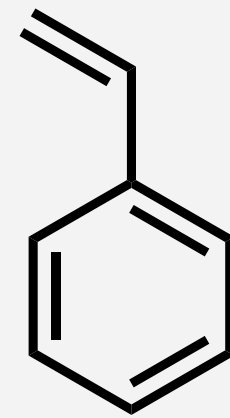


styrene(s)

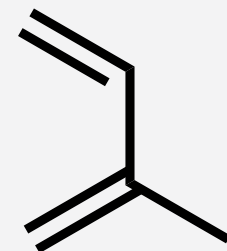

isoprene
2-methylbutadiene



butadiene

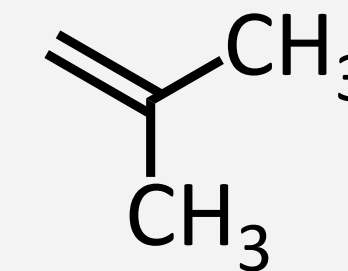


isobutylene
1,1-dimethylethene

- electron-donating group to increase reactivity towards electrophile and bias for terminal reaction
- also necessary to stabilize the carbocationic center on the reactive chain end

Chain Transfer Reactions







- chain transfer by β -hydrogen transfer to monomer is prevalent mechanism

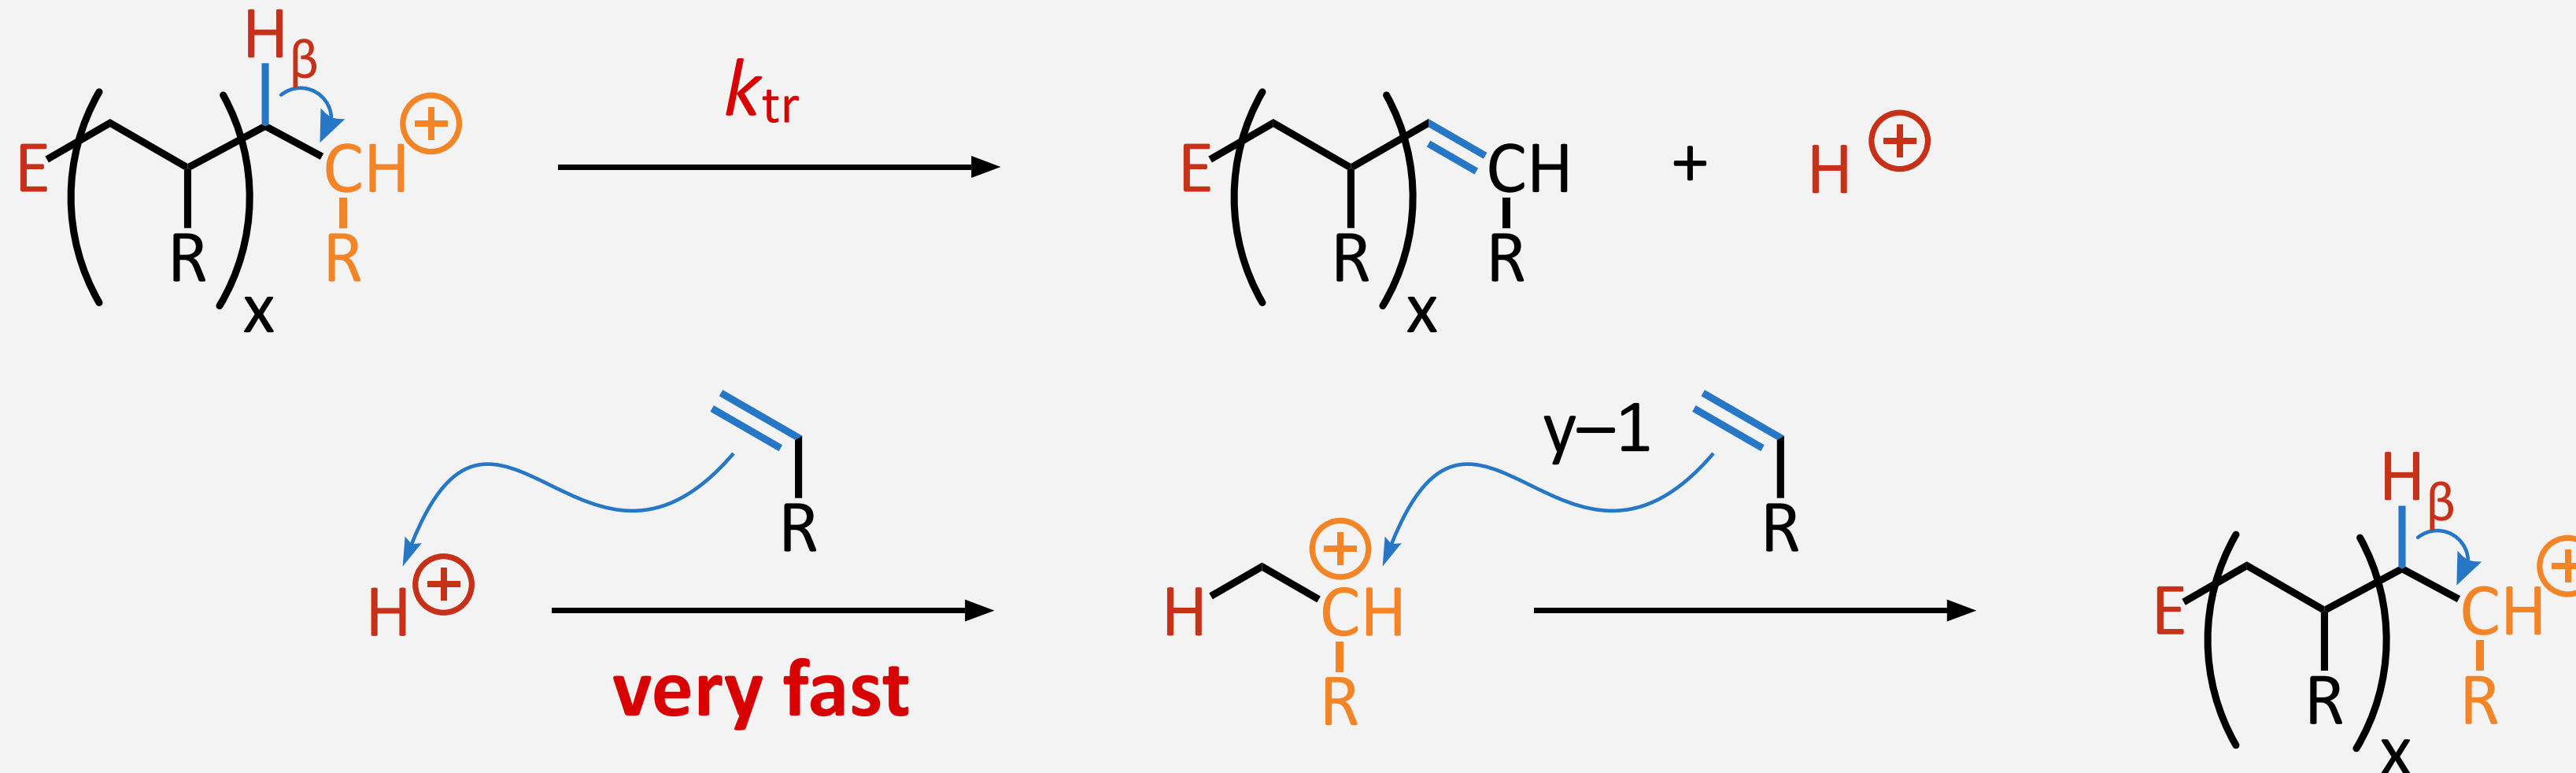

- individual polymer chain is deactivated but kinetic chain reaction continues
 - both propagation and chain transfer are first order in monomer and in active chain end
 - molar mass determined by kinetics, inverse of chain transfer constant $C_{tr} = k_{tr} / k_p$
 - polymerization typically performed at (very) low temperatures to increase molar mass
 - β -hydrogen transfer results in double bond chain ends; polymerizable hence risk of branching
- chain transfer to monomer is principal process that limits molar mass and results in Schulz-Flory distribution, especially at reaction temperatures above r. t.**

Termination Reactions


- chain termination is possible by combination with counterion (in some cases)

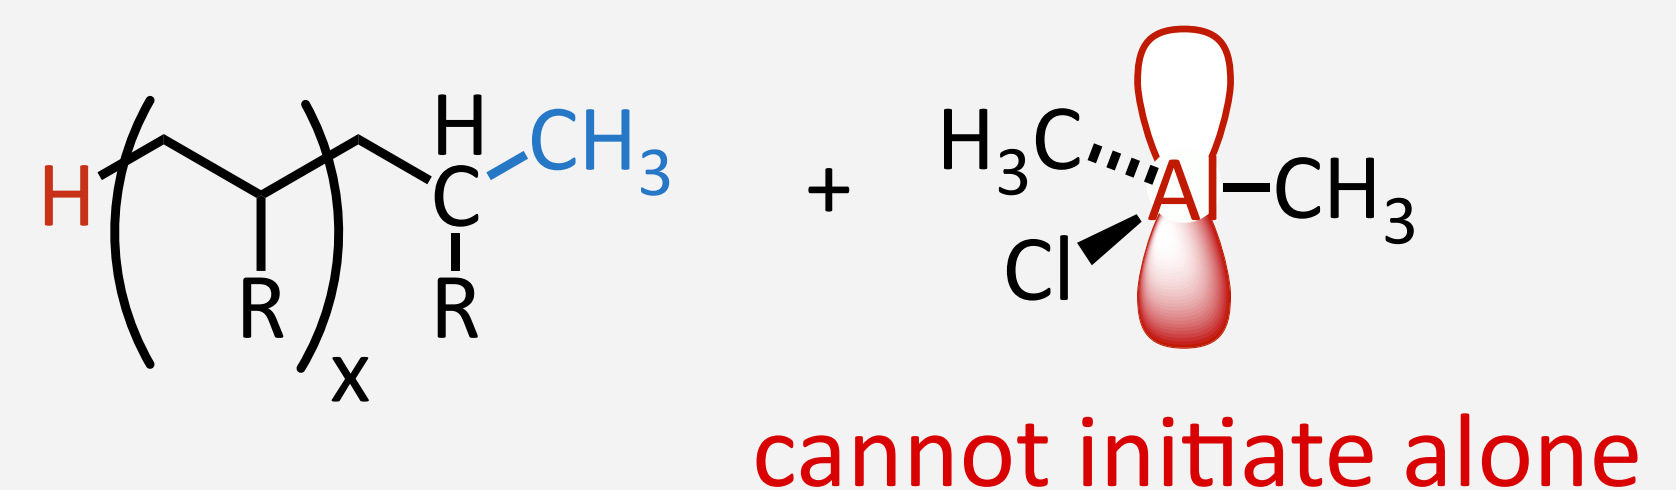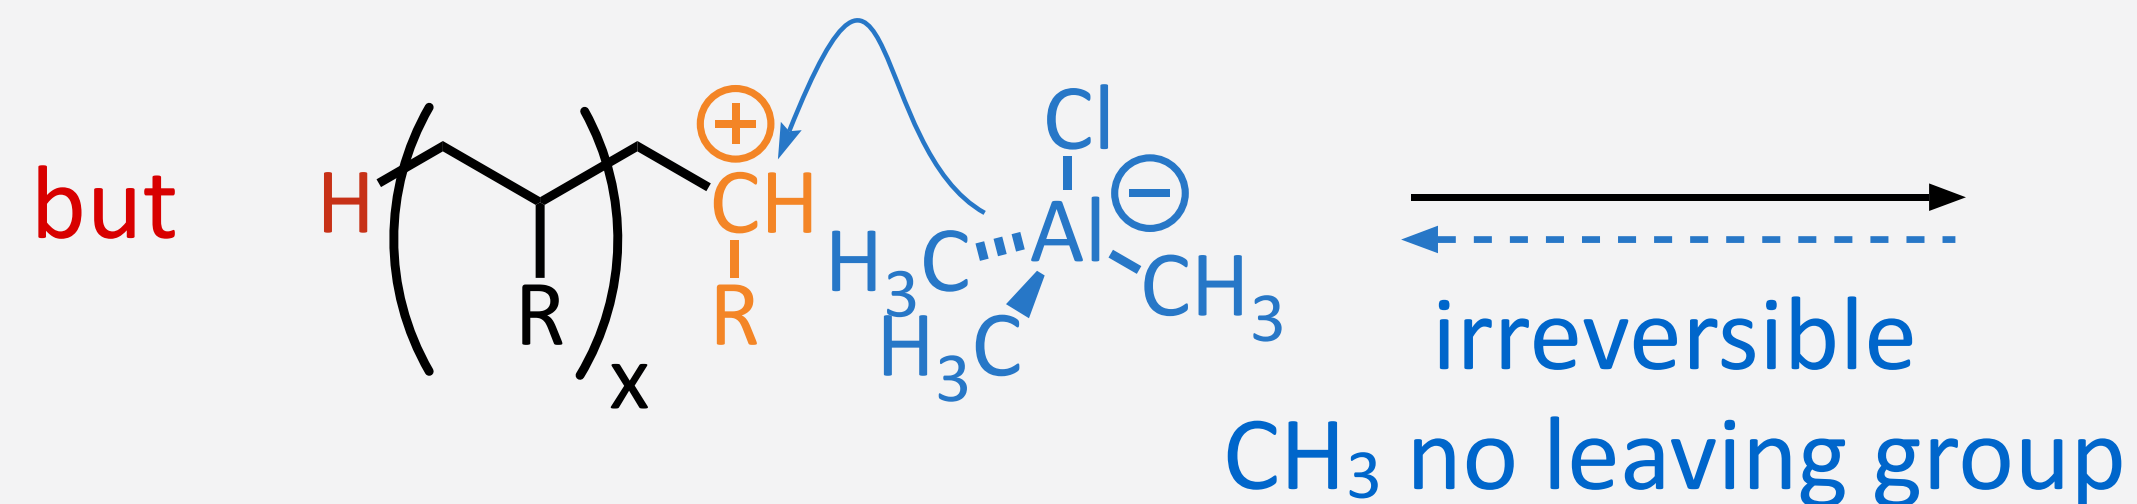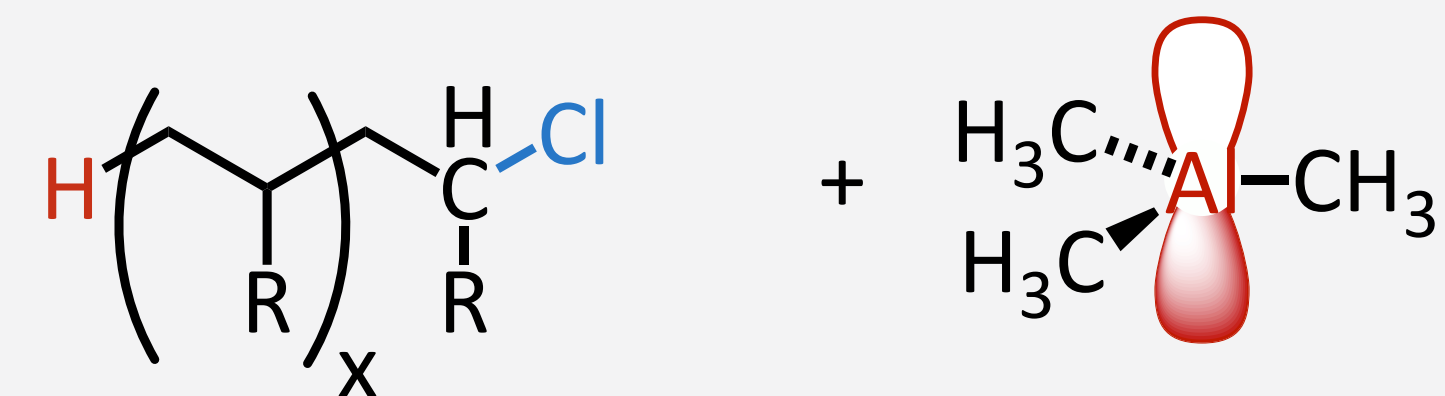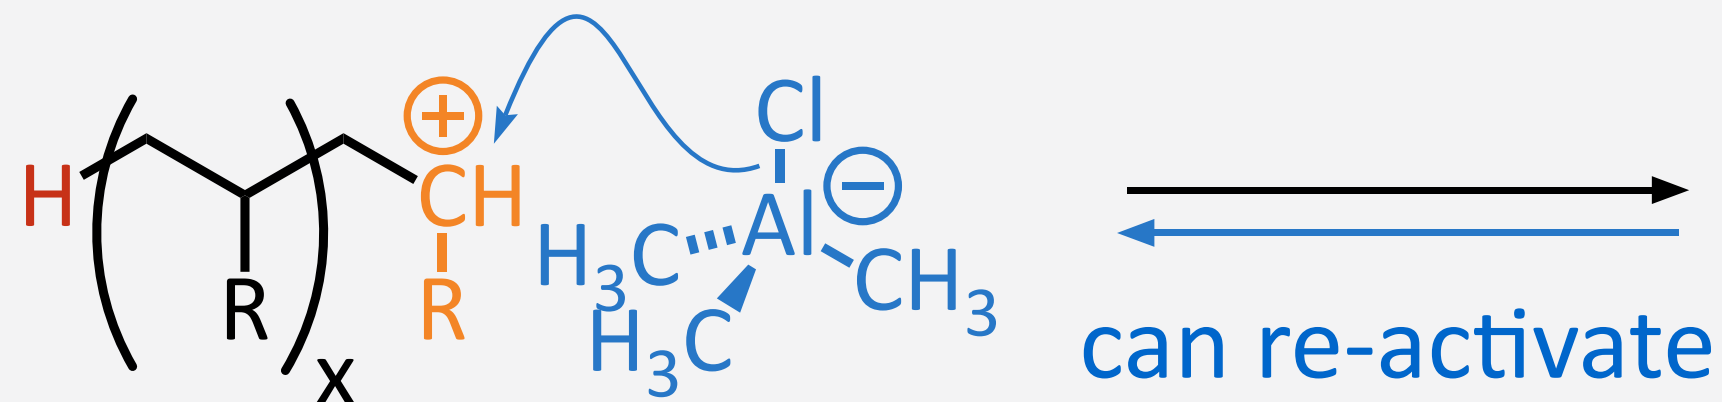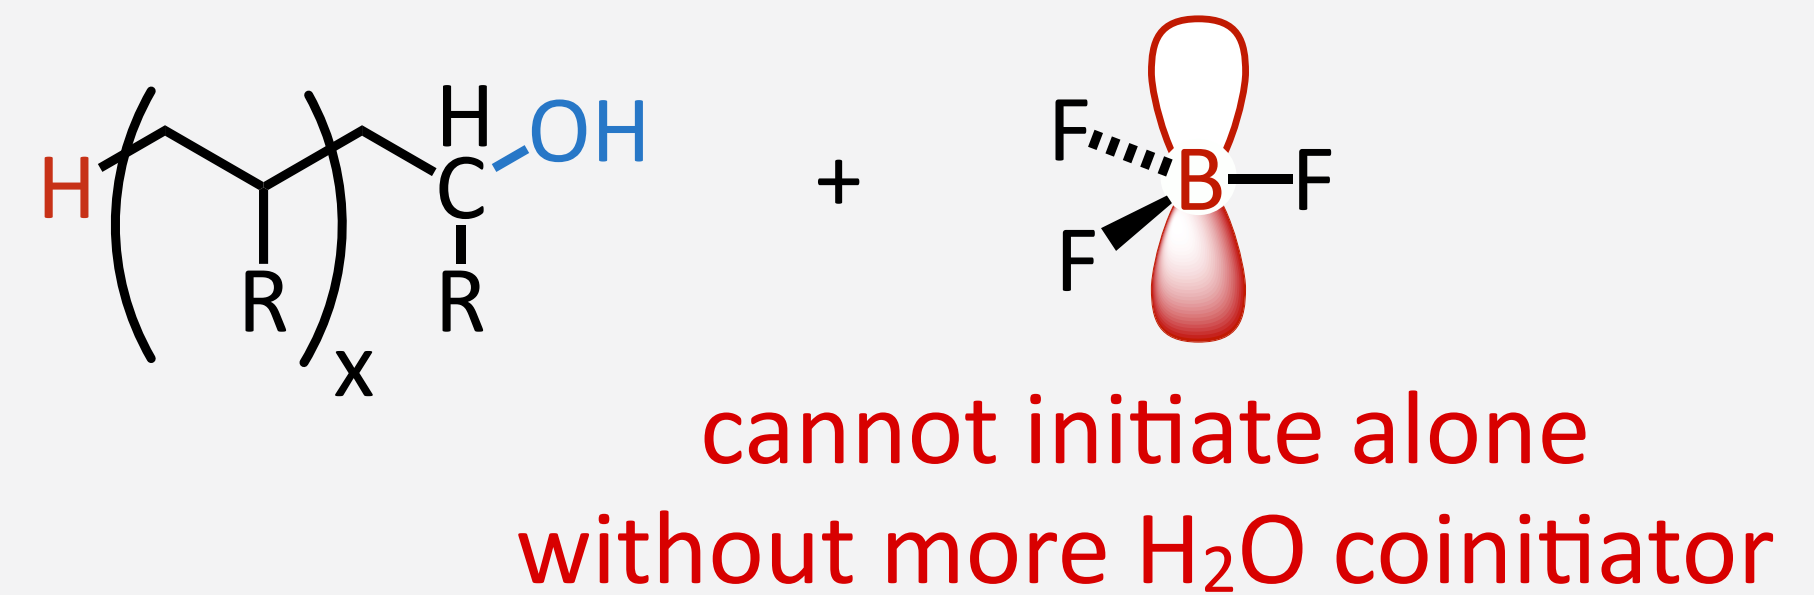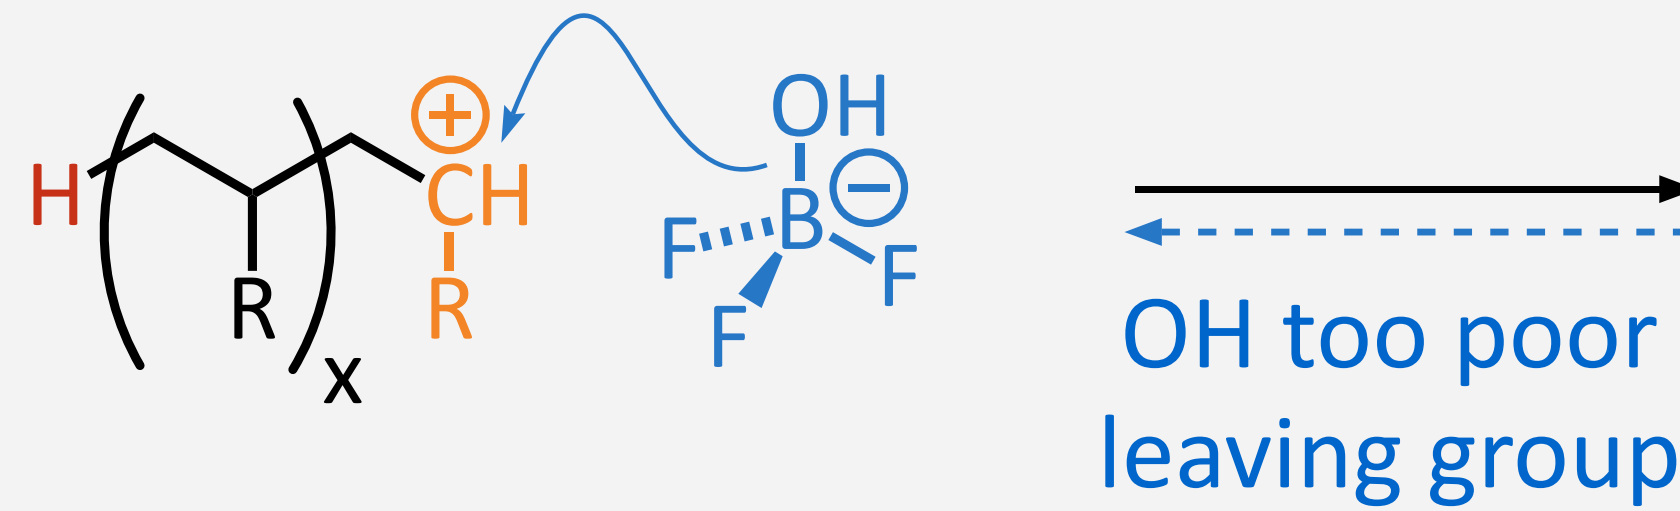


- different from radical polymerization, terminations are not prevalent in cationic polymerizations

Quenching

- carbocationic chain end remains reactive intermediate, is “quenched” (deactivated) by nucleophiles

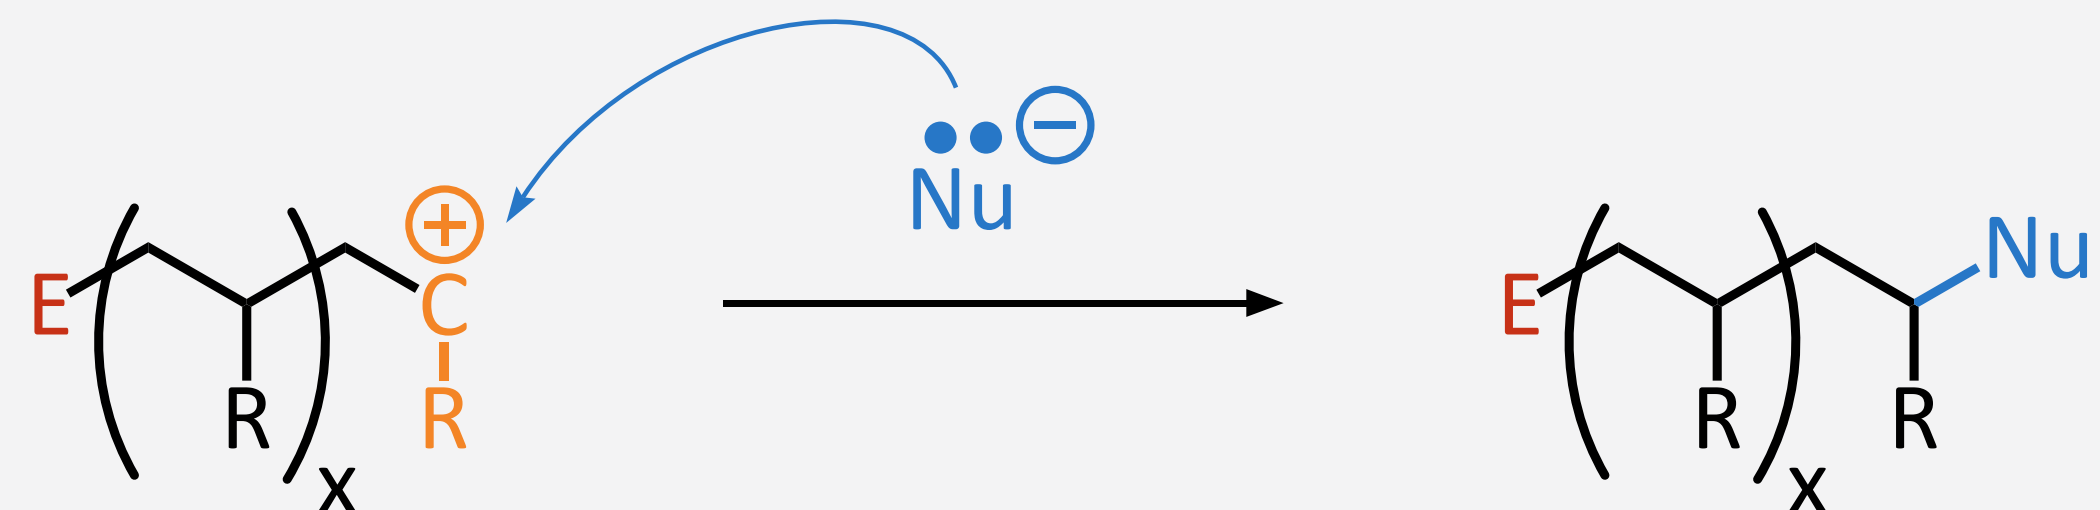

- strong nucleophiles (anionic, with weakly acidic counterions) result in irreversible termination
- weak nucleophiles that release strongly acidic counterion for accelerated chain transfer
- useful to tailor molar mass control

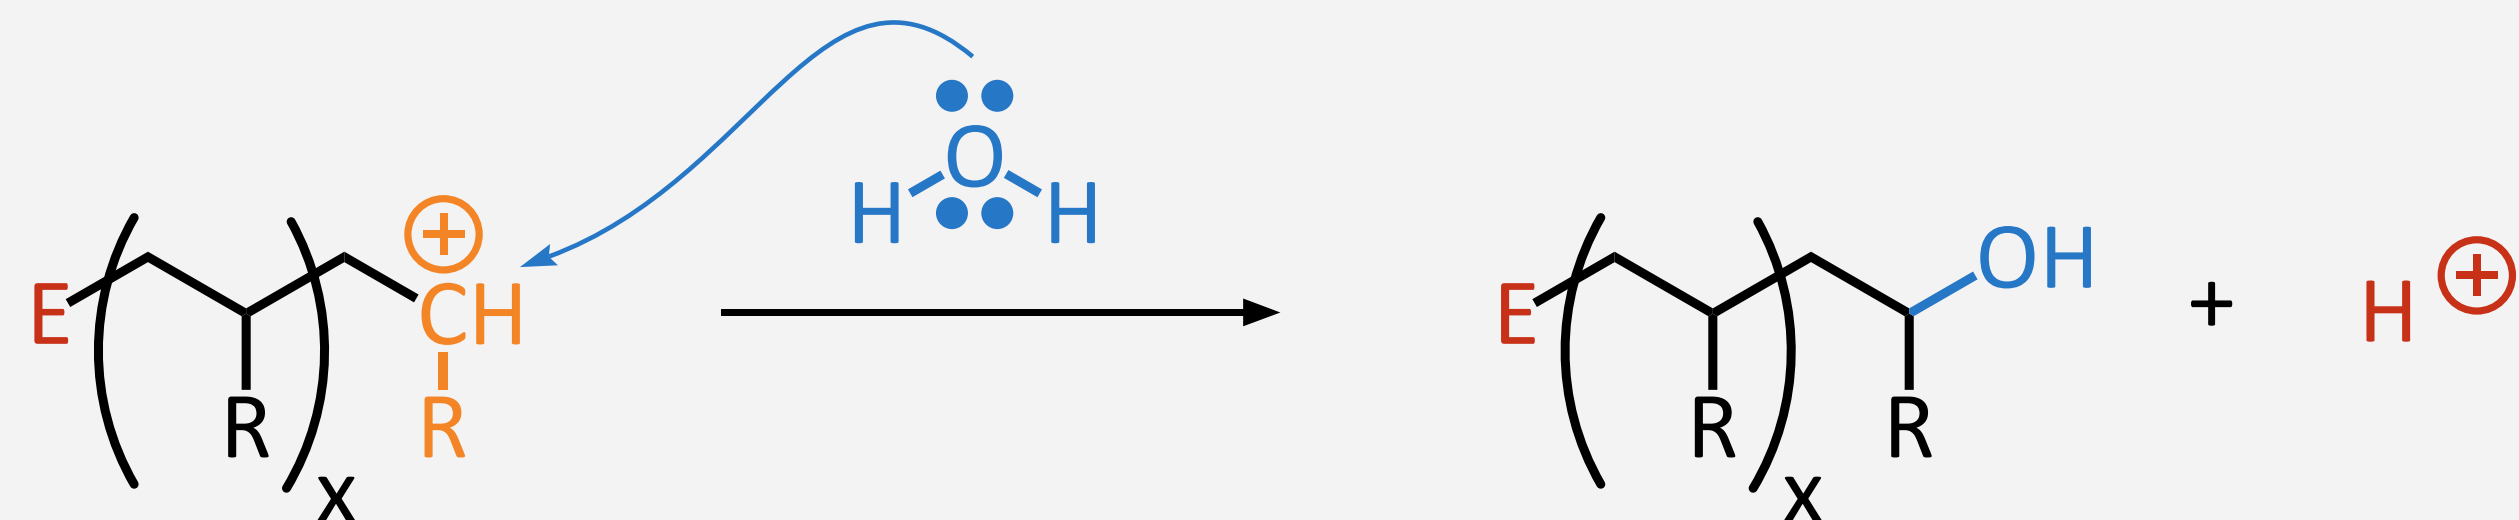


- quenching generally useless for introducing end groups deliberately because of chain transfer
- cationic polymerizations require careful scavenging of inadvertent nucleophiles (including water)

Coordination Polymerization

Generic Mechanism of Transition-Metal-Catalyzed Coordination Polymerization


- coordination (insertion) polymerization of alkenes by transition metals with empty coordination site

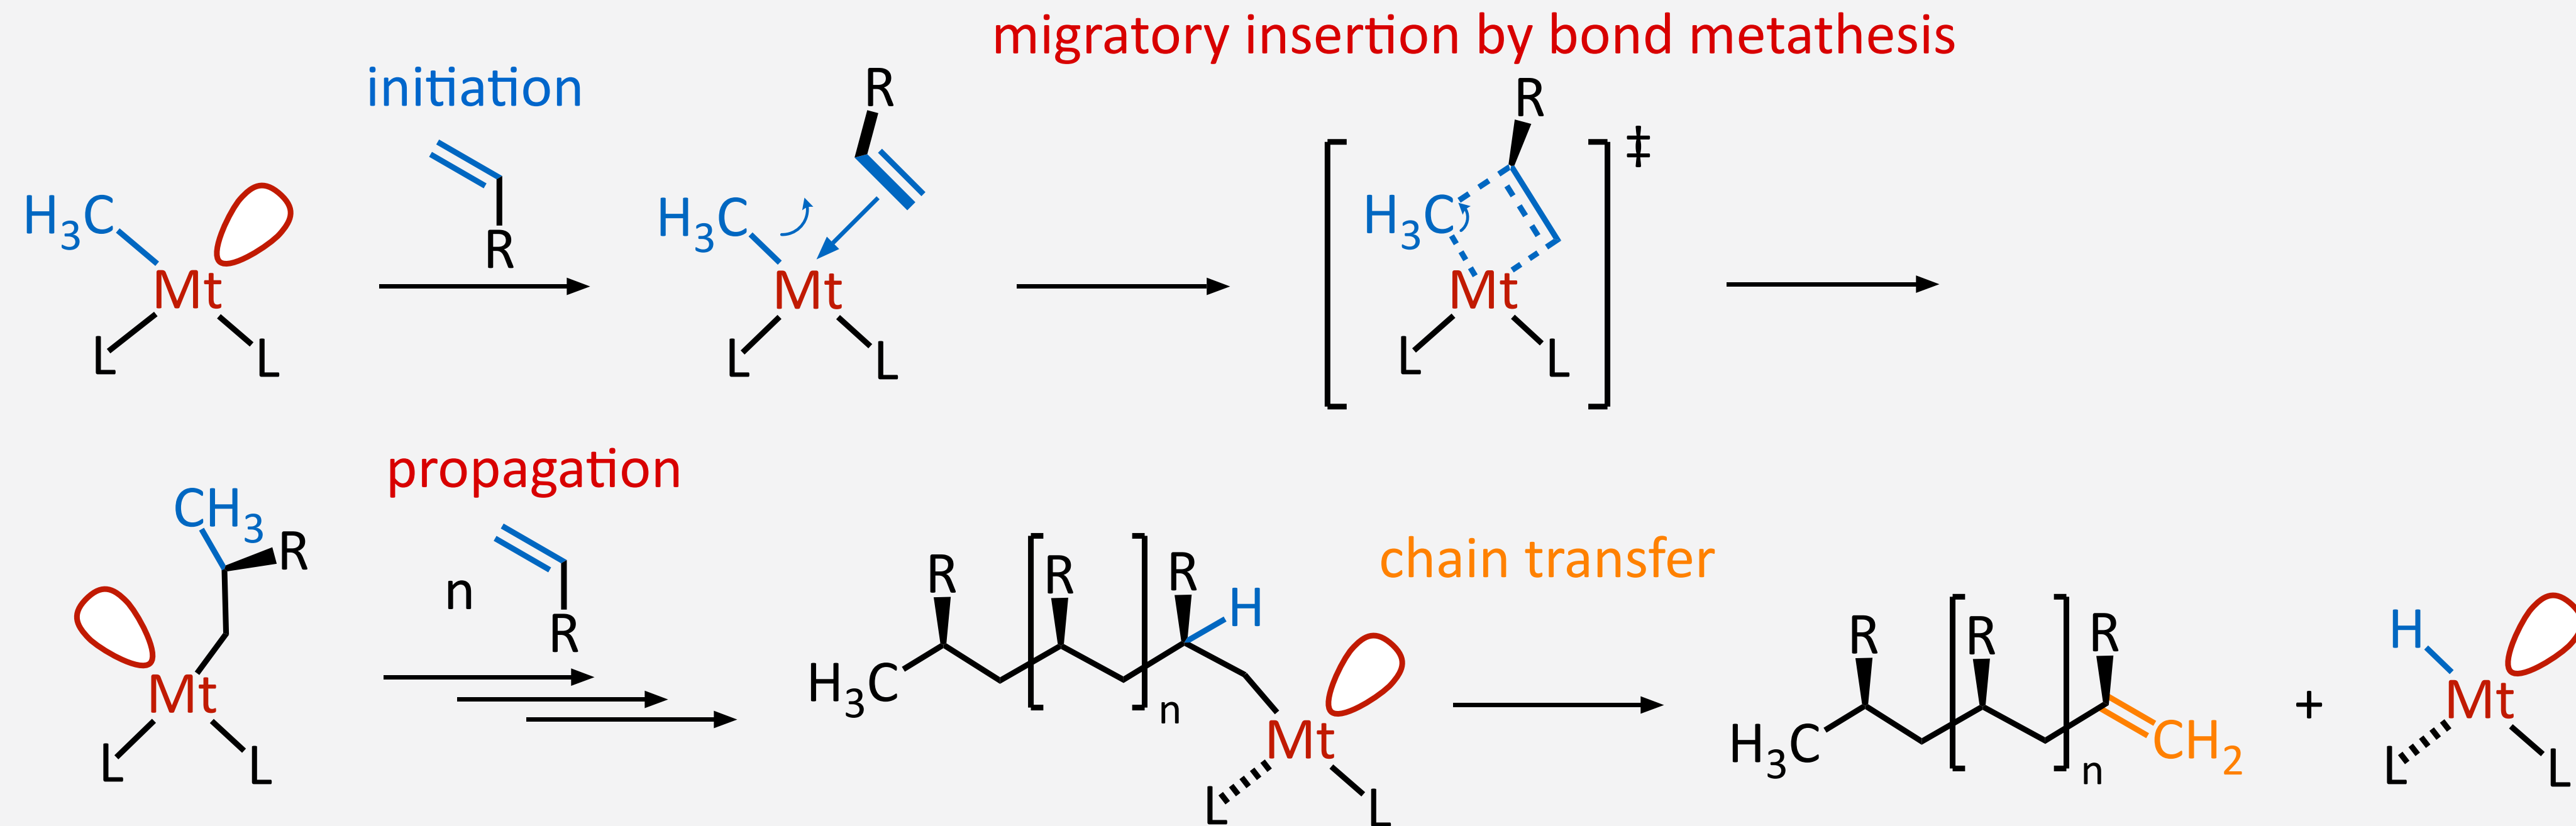


- initiation by first alkene monomer adding as ligand to the vacant coordination site (empty d orbital)
- propagation by migratory insertion of the monomer into Mt–C bond, polymer chain migrates
 - via four-electron, four-membered cyclic transition state
 - finalized by bond metathesis, generating new Mt–C & C–C bonds, reforming empty coordination site
- chain transfer by β -hydrogen elimination from last unit, generates double bond chain end

- typical catalysts are a wide variety of transition metal solids and molecular organometallic compounds

heterogeneous catalysts

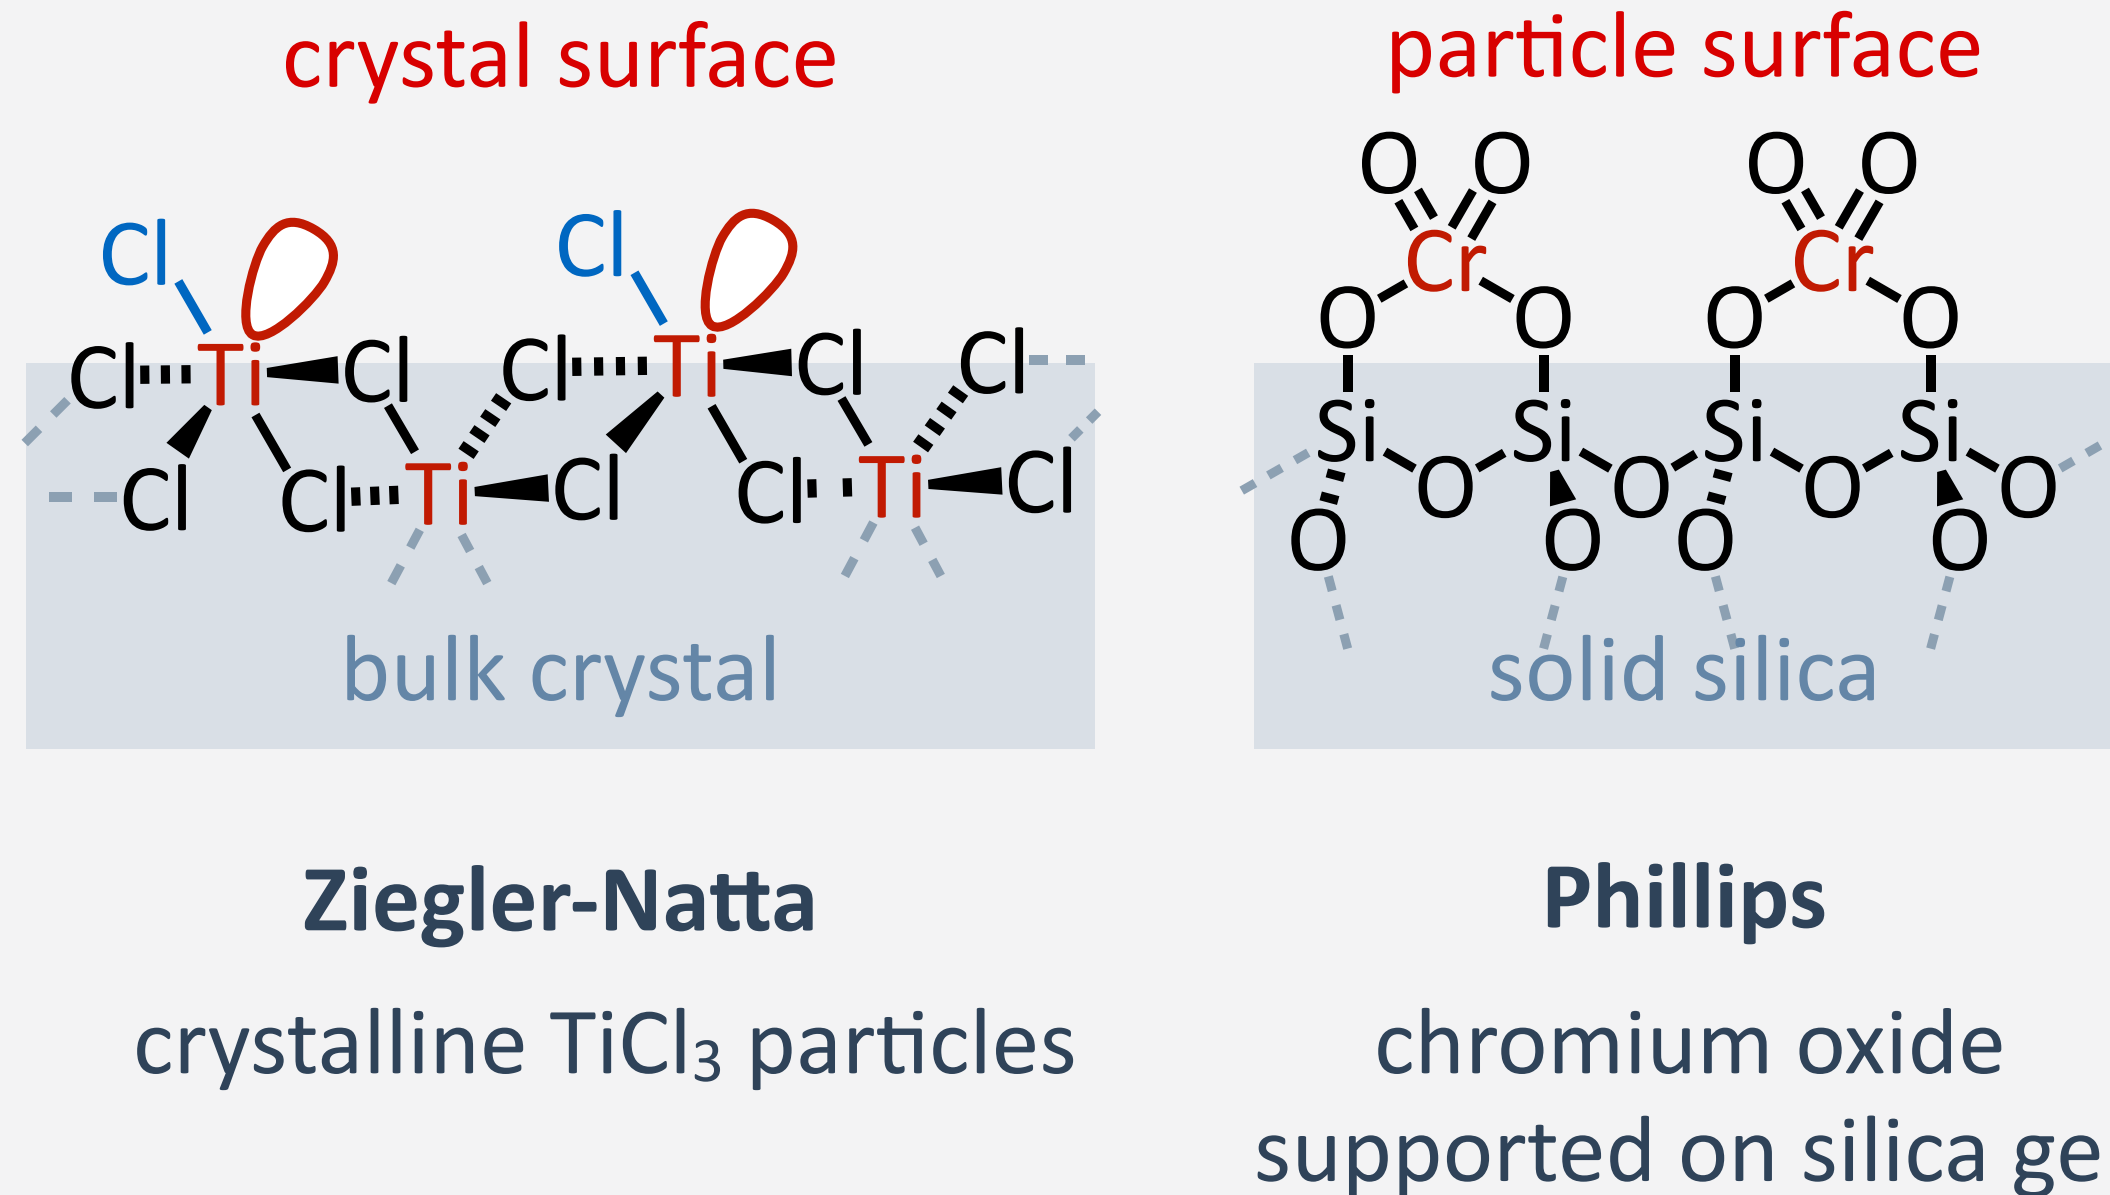


homogeneous catalysts

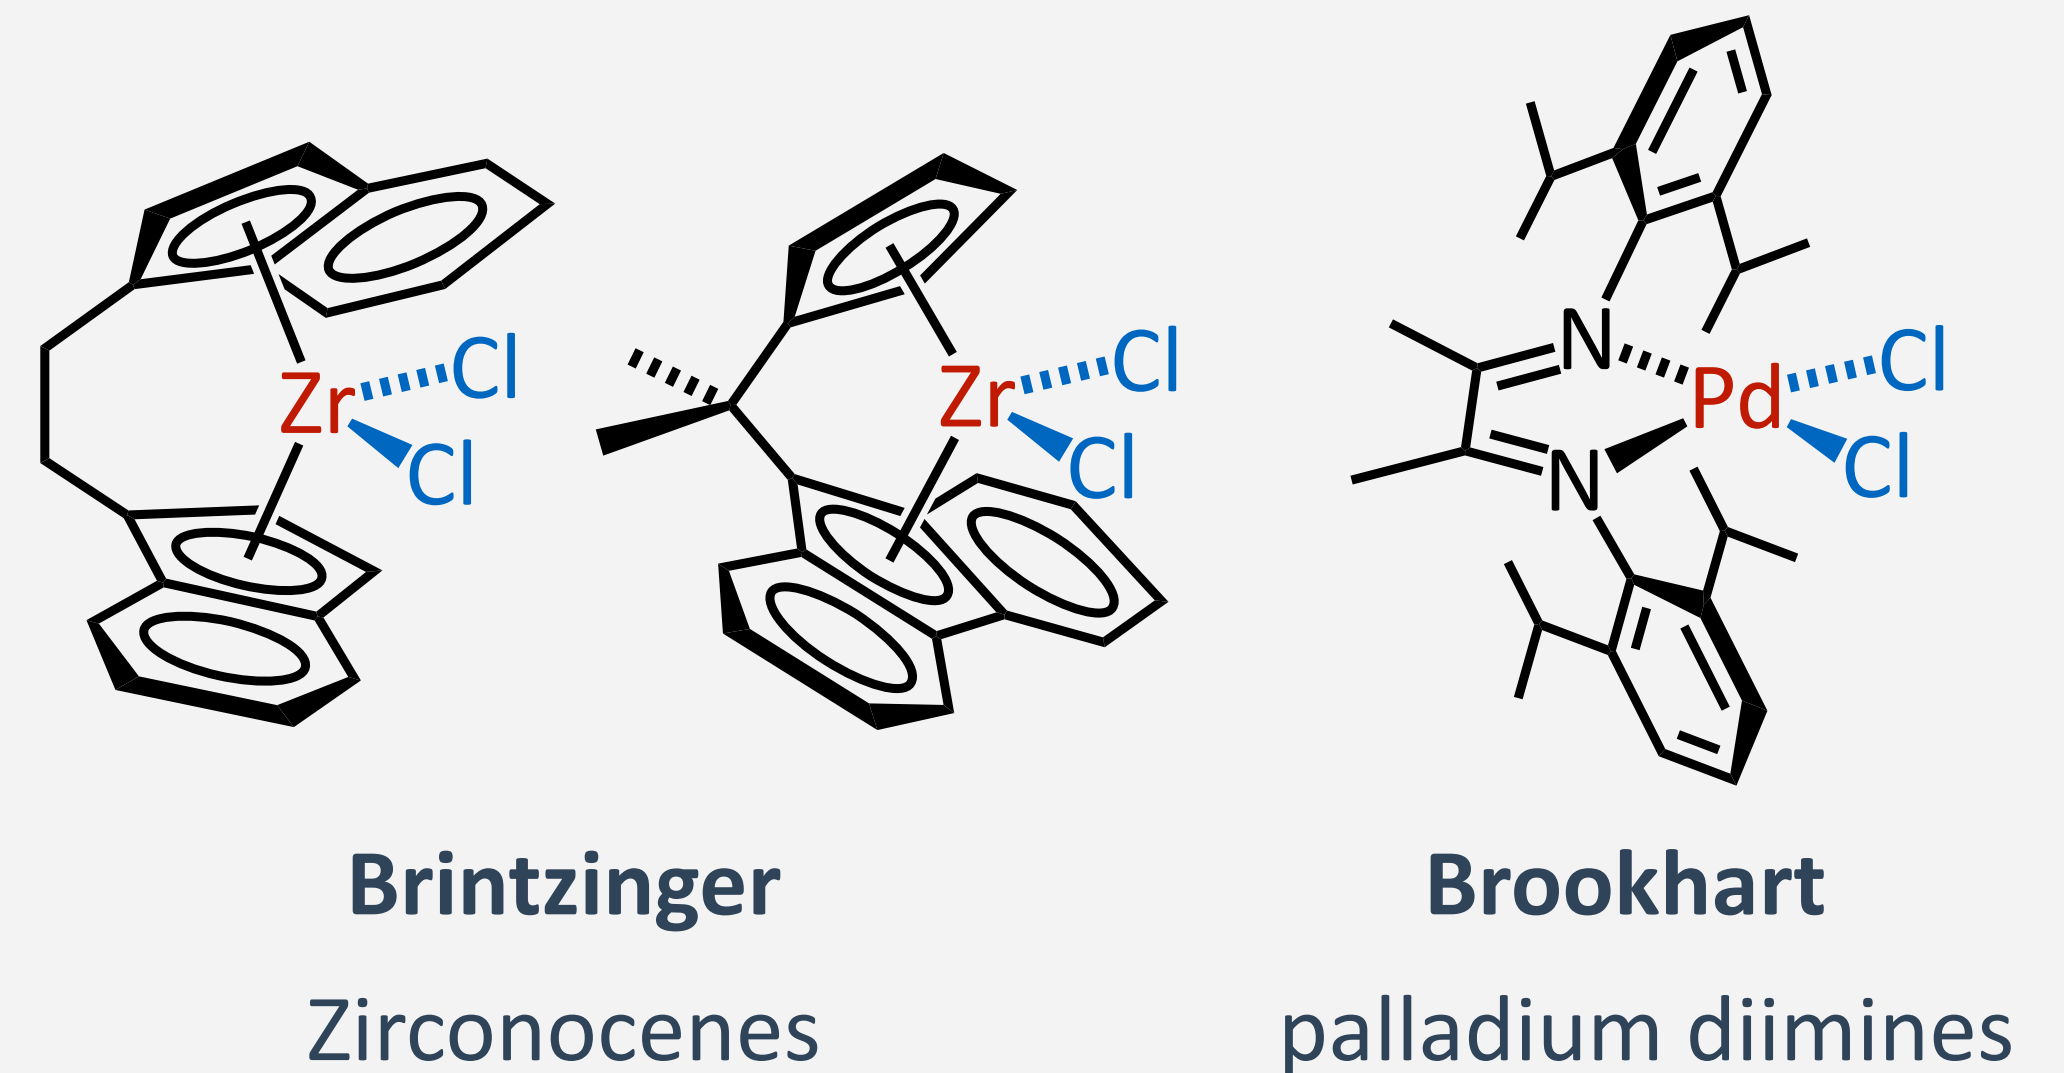

- heterogeneous catalysts are solid particles dispersed in reaction medium, only surface is active
- homogeneous catalysts are defined organometallic compounds, in homogeneous solution


Catalyst Activation

- catalyst activation requires generating an **alkylated metal center with a free coordination site**

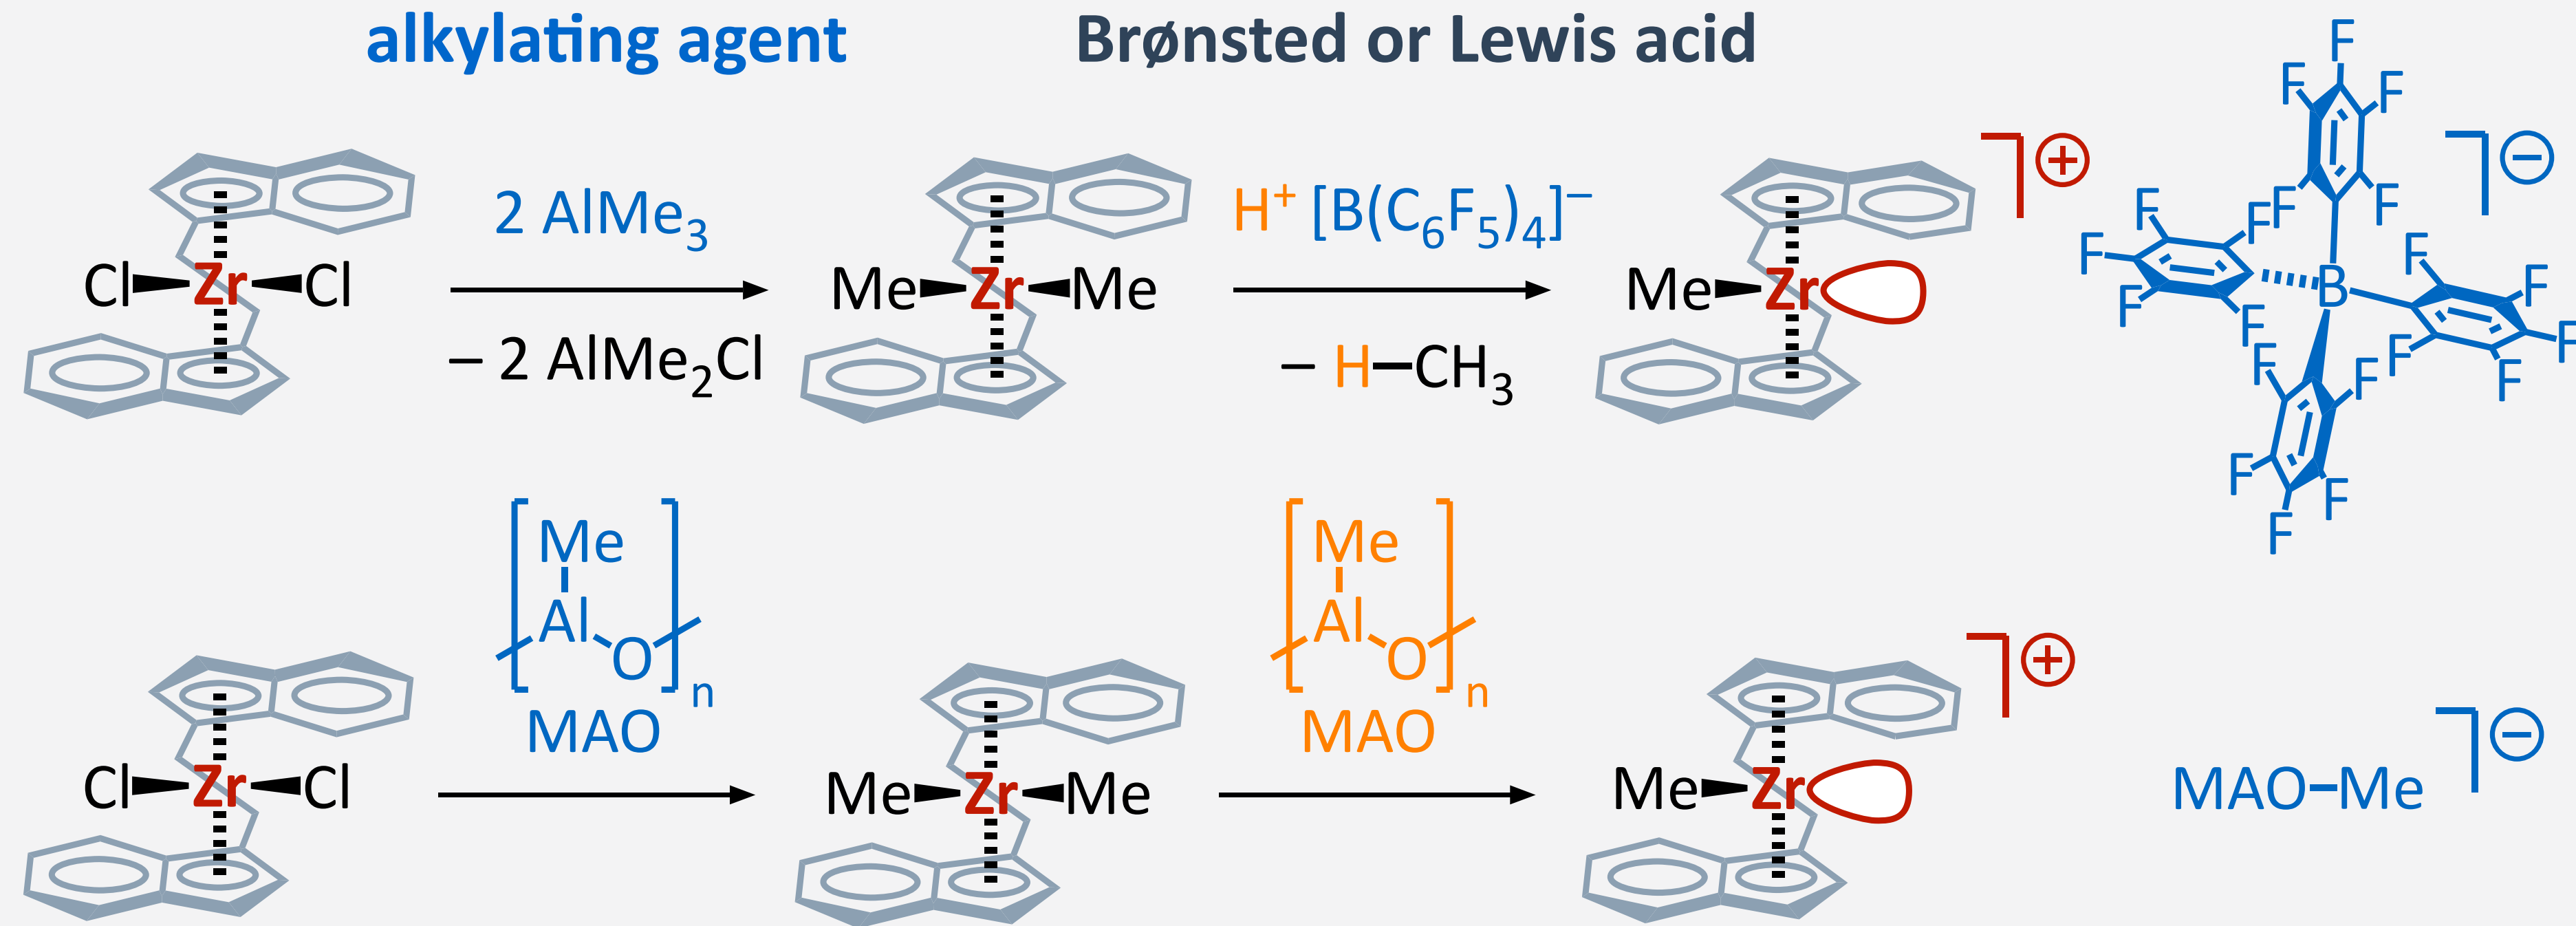


- alkylation** of stable precursors typically achieved with AlMe_3 or methylaluminoxide (MAO)
- alkylated metal center with a free coordination site is highly electron-deficient species**
- very strong Lewis/Brønsted acid** with **weakly coordinating anion** required for its formation
- MAO (clusters of about 20 Al atoms, unknown structure) does both, common in industrial processes

Example of a Ziegler-Natta Polymerization via Cossee-Arleman Mechanism

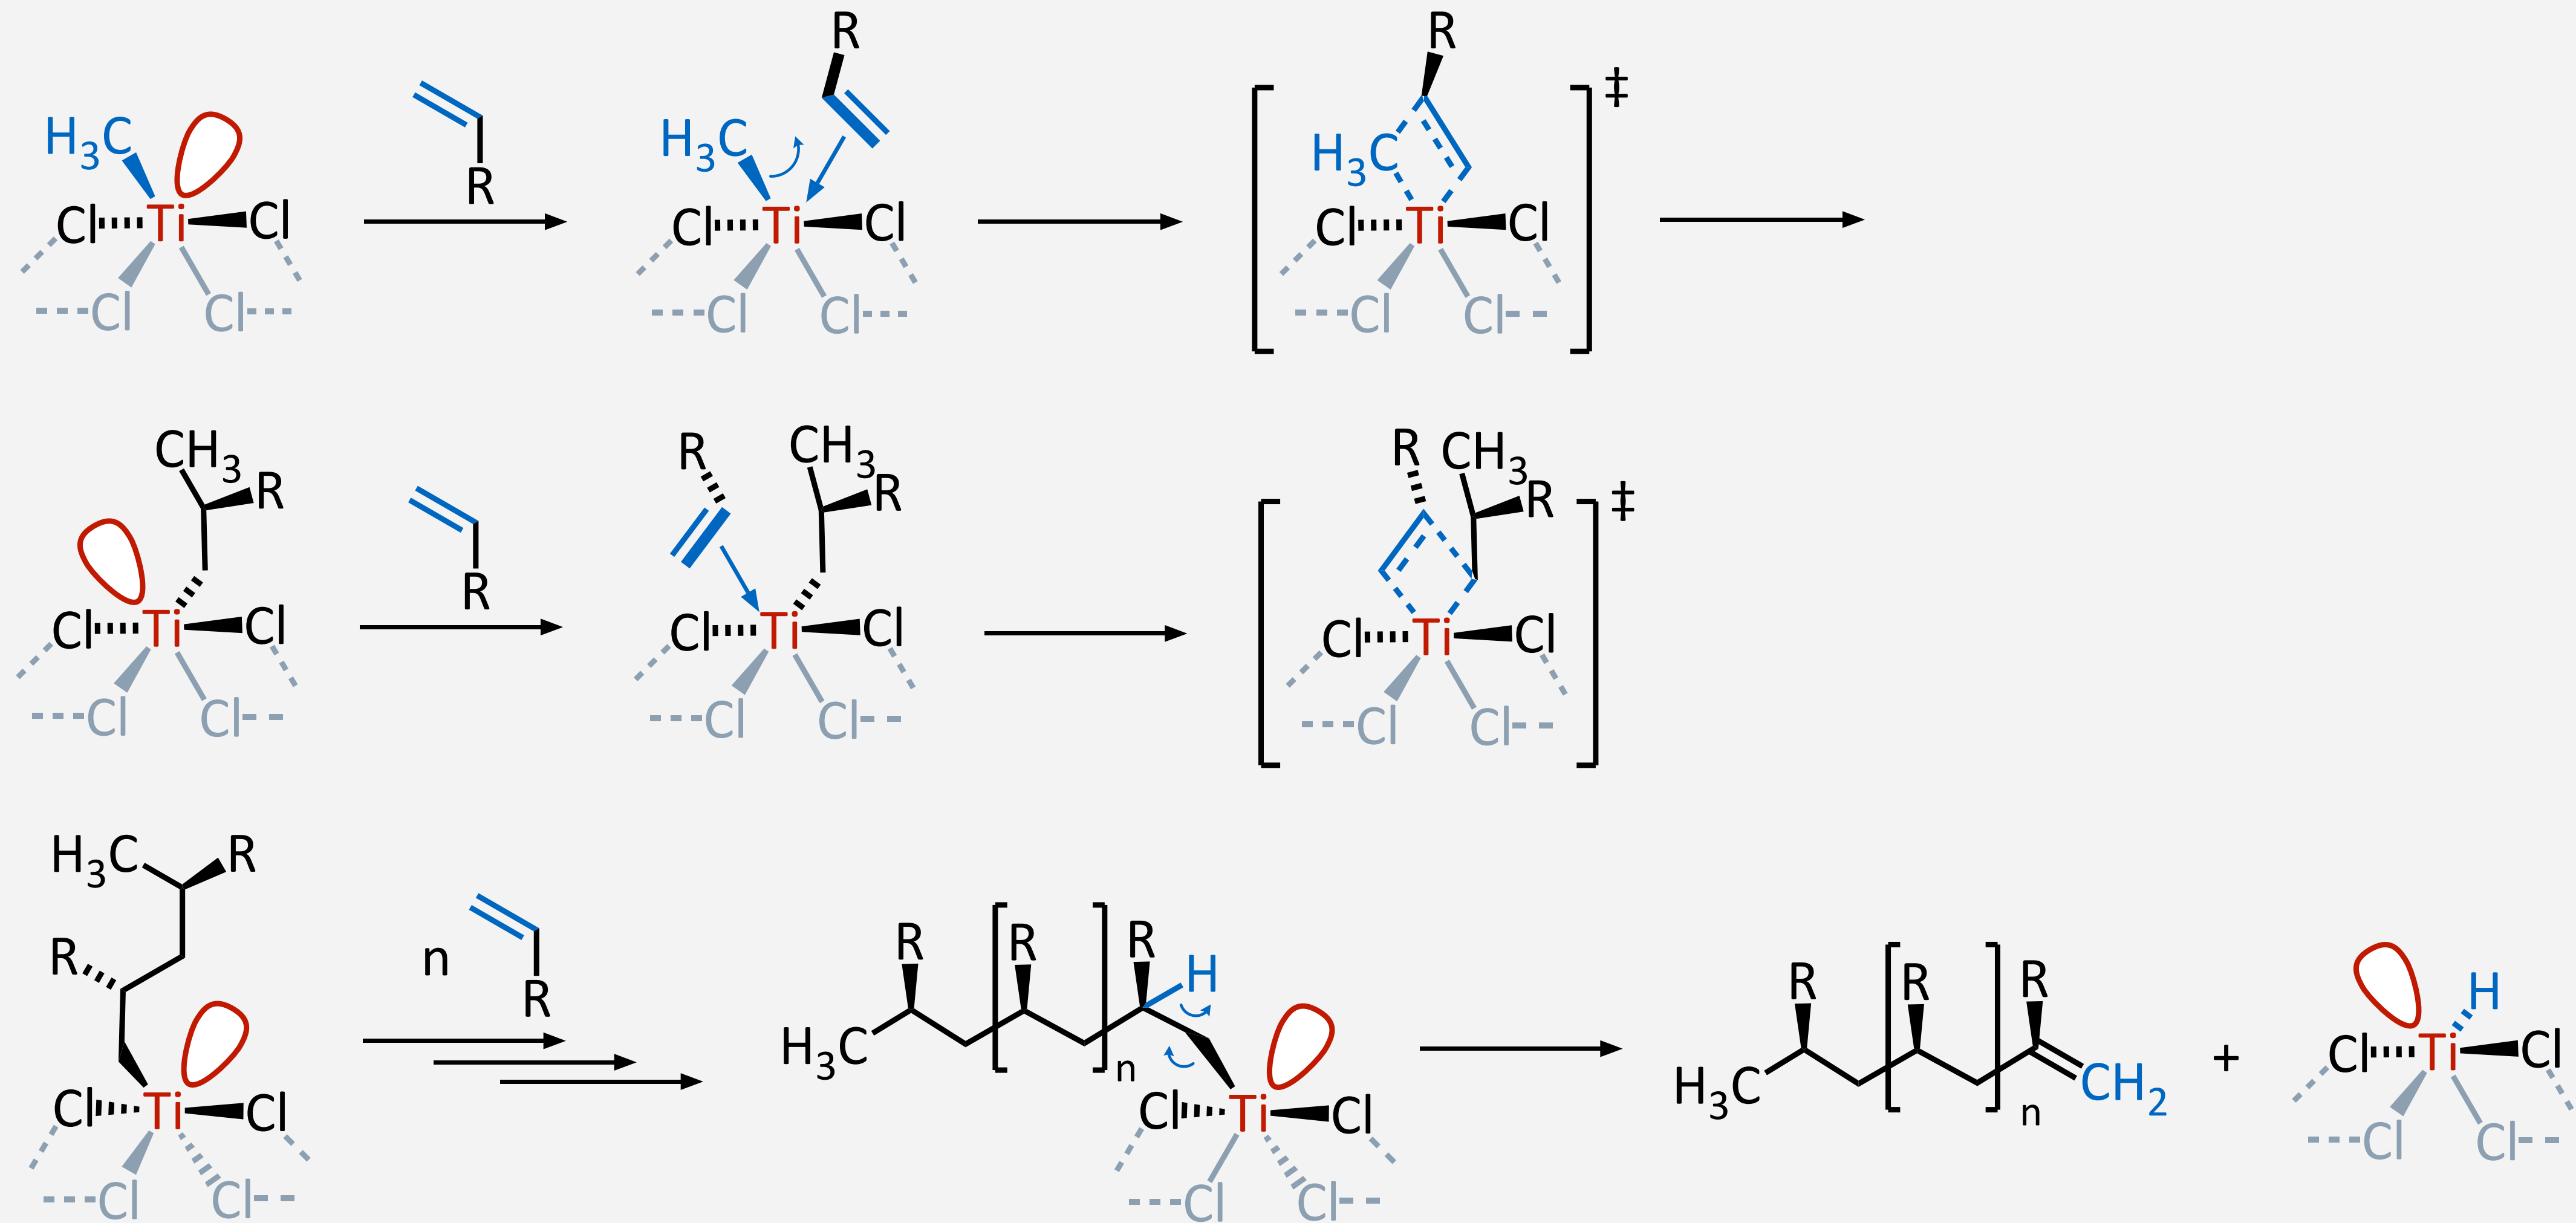

- migratory insertion means that polymer switches coordination site with every insertion step

Example of a Ziegler-Natta Polymerization

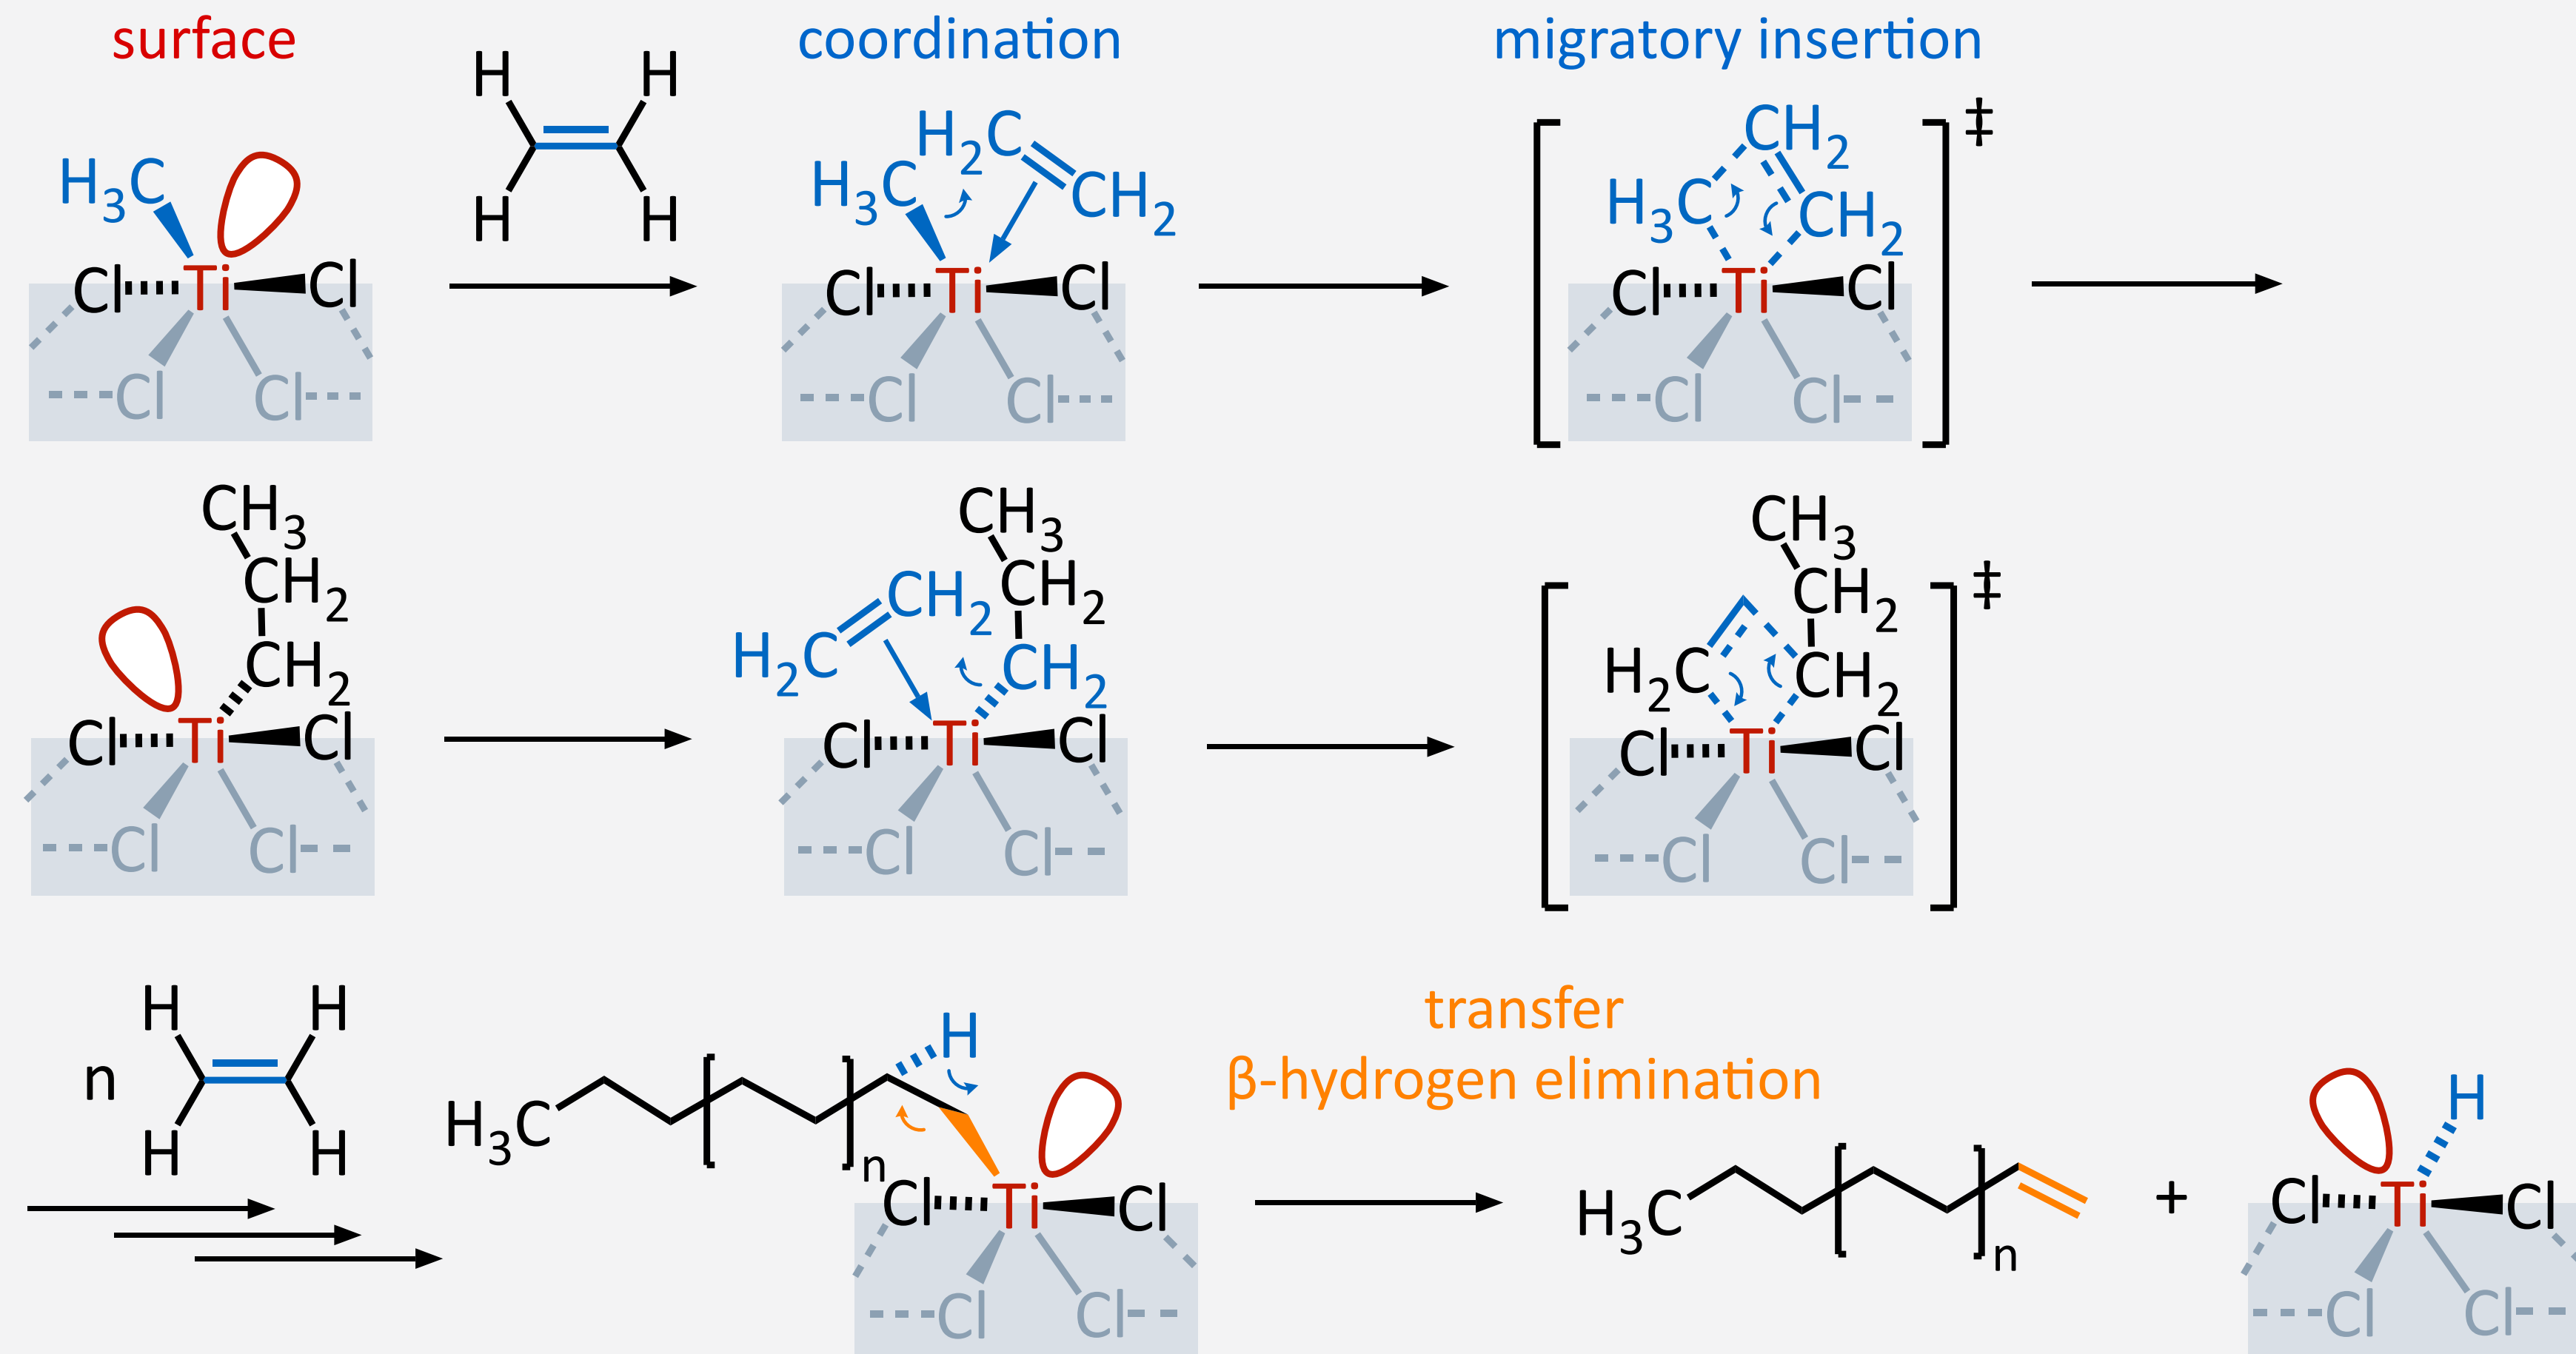

- Cossee Arlman mechanism: **monomer coordination** to **empty coordination site** on surface metal atom
- **migratory insertion** into Mt–C bond, means that **polymer switches coordination site at every step**
- **chain transfer** generates terminal **double bonds**, can result in branches when polymerized