

High Molecular Weight Protein-Like Semiflexible Chains via Bioorthogonal Polymerization of Coiled-Coil Peptides

Hanyuan Gao, Tianren Zhang, Matthew G. Langenstein, Weiran Xie, Samiksha Udan, Zihan Zhang, Jeffery G. Saven, Shi Bai, Darrin J. Pochan, Joseph M. Fox, and Xinqiao Jia*



Cite This: *Macromolecules* 2024, 57, 9585–9594



Read Online


ACCESS |

Metrics & More

Article Recommendations

Supporting Information

ABSTRACT: Peptides capable of forming homotetrameric coiled-coil bundles are utilized as monomeric building blocks (“bundlers”) to synthesize protein-like hybrid polymers consisting of covalently linked coiled-coil microdomains with regularly spaced ethylene glycol repeats via step-growth polymerization employing the highly efficient, bioorthogonal tetrazine (Tz) ligation with *trans*-cyclooctene (TCO). Polymerization of Tz and TCO-functionalized peptides in aqueous media under strict stoichiometry at Tz or TCO concentrations of 0.1 to 4.5 mM leads to the establishment of exceptionally long, semiflexible polymer chains with a Kuhn length of 6–7 nm and an apparent molecular weight up to 3 MDa. Bioorthogonal polymerization at bundlemer concentrations above 5 mM gives rise to physical gels through interchain entanglements. Hydrogels prepared at 10 mM exhibit an average elastic modulus of 400 Pa and a strain to failure of 300%. Copolymerization of coiled-coil peptides with distinct composition and thermal stability results in hydrogels that are thermally tunable. A solid-to-fluid transition occurs when one of the coiled-coil repeats melts. Upon cooling, solid-like properties are partially recovered through the intermolecular association of the helical peptides. Overall, tetrazine ligation has enabled the covalent polymerization of self-assembled coiled-coil motifs for the establishment of protein-like linear polymers with unprecedented molecular weight.

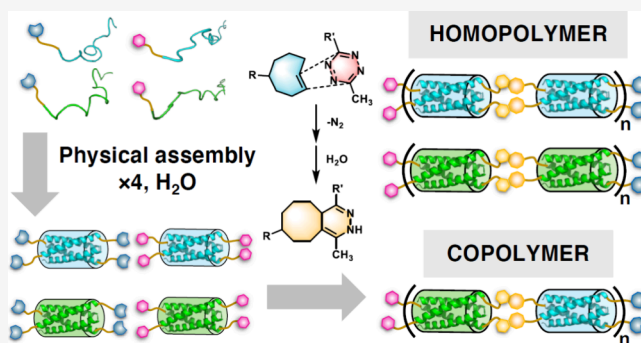

INTRODUCTION

The advances in organic chemistry, catalyst design, and polymerization methodologies have led to the development of a wide range of synthetic polymers with high molecular weight, variable composition and structure, and unique physical states and mechanical properties. Synthetic polymers, produced via step growth, chain growth, or ring-opening polymerization of small molecule compounds with chemically susceptible groups, consist of long chains of covalently linked monomeric repeat units.^{1–4} With the exception of polypeptides and certain types of nonamide-based polymers, such as poly(isocyanide)s and poly(*p*-phenylenevinylene),⁵ most synthetic polymers exist as random coils or extended chains; they normally do not fold into defined secondary structures seen in natural proteins. Although the precise placement of reactive handles or hydrogen bonding units along the polymer backbone or at chain termini has enabled the creation of synthetic polymers with complex molecular architecture, shape, and morphology,^{6–9} these nanoscale molecular structures lack the specificity, complexity, diversity, and flexibility seen in natural proteins.

Synthesized from natural amino acids through transcriptional and translational processes, proteins exhibit well-defined


secondary, tertiary, and quaternary structures in aqueous media through concerted noncovalent interactions, including H-bonding, hydrophobic interactions, van der Waals forces, and ionic interactions. The function of a particular protein is dependent on the peptide sequence as well as its unique higher-order structures.¹⁰ To achieve diverse functions, many natural proteins contain multiple structurally and functionally distinct domains or motifs. For example, the giant muscle protein titin (~3 MDa) consists of multiple folded immunoglobulin domains arranged in series alternating with unstructured unique sequences.^{11,12} The consecutive and reversible unfolding and refolding of the domains are crucial for titin to serve as a modular spring.¹³ On the other hand, structural proteins, such as keratins and vimentin, incorporate coiled-coil motifs, i.e., a superhelix of multiple α -helices twisted around each other, to provide mechanical strength to cells

Received: August 5, 2024

Revised: September 20, 2024

Accepted: September 26, 2024

Published: October 7, 2024



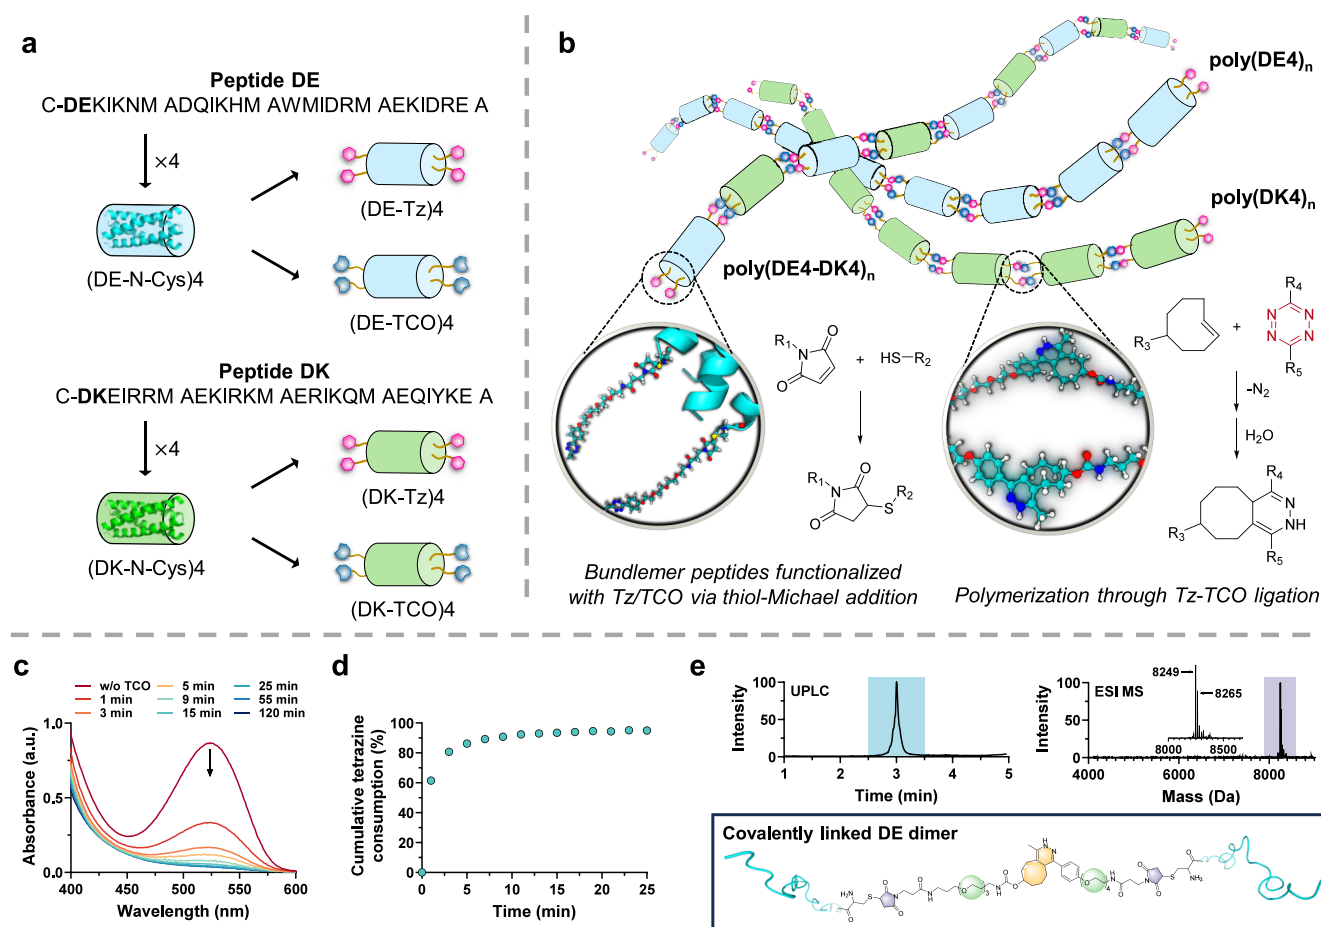


Figure 1. Bioorthogonal polymerization of coiled-coil peptides. (a) Cysteine-tagged peptides, DE and DK, are used to prepare Tz and TCO-functionalized derivatives that assemble into four-helical coiled-coils under aqueous conditions. The bundlemer contains two bioorthogonal handles on each end. (b) Tz and TCO groups are installed to the N-terminus of the peptide through the thiol-Michael reaction, and individual coiled-coils are linked together through the fast and highly efficient tetrazine-TCO ligation. (c) Attenuation of the tetrazine chromophore at 524 nm during bioorthogonal polymerization, as monitored by UV-vis spectroscopy. (d) Cumulative tetrazine consumption during polymerization as a function of reaction time, showing 95% conversion of tetrazine to the cycloadduct 25 min after the supramolecular monomers were mixed at a Tz or TCO concentration of 2.5 mM. (e) UPLC trace and deconvoluted ESI MS of poly(DE4)_n showing the presence of peptide dimer after poly(DE4)_n became denatured on the UPLC column. The second highest mass peak ($M+16$) is likely due to methionine oxidation. Figures were created using AlphaFold2,³⁰ Avogadro,³¹ and BioRender.com.

through the formation of rigid or semiflexible fibrous networks.¹⁴

The need for advanced materials with tunable properties and adaptive features has motivated researchers to exploit the utility of peptidic building blocks and motifs to create new materials with desired functions.¹⁵ Supramolecular polymerization of cyclic,¹⁶ amphiphilic, and β sheet-forming peptides^{17,18} into ordered nanostructures has yielded materials with high molecular weight (~ 200 MDa¹⁷), long-range order, and enhanced tunability. Because the assembly is driven by noncovalent interactions, the structures and properties of this type of material are dependent on pH, temperature, and solvent conditions.^{19,20} To prevent the polymeric peptide assembly from dissociating, the constituent building blocks must exhibit high affinity for each other, thereby imparting mechanical properties similar to conventional polymers established entirely by covalent bonds.²¹

Peptide-based polymers can be synthesized through covalent coupling of preassembled peptidic motifs.^{22,23} The resultant hybrid materials retain the reversible and dynamic properties of supramolecular motifs and at the same time are structurally

sound and mechanically robust.²⁴ Side-chain-to-side-chain polymerization of vertically stacked cyclic β -peptide rings via the formation of amide linkages gives rise to nanofibers composed of a single polymer strand that is tougher than natural silk.²⁵ Alternatively, linker-free, end-to-end polymerization of antiparallel homotetrameric coiled-coil peptide bundles via thiol-Michael addition leads to the formation of hybrid polymers that are exceptionally rigid with persistence lengths up to 40 μ m.²⁶ As one of the most abundant structural and functional motifs in nature, coiled-coils are essential for mediating strong and specific protein-protein interactions.¹⁰ With a basic heptad repeat, the constituent peptides for coiled-coils can be computationally identified.²⁷

To expand the range of material properties attainable by one-dimensional nanostructures, an alternative interbundle linking chemistry is explored for the preparation of polymeric coiled coils (PCCs). Herein, using customized, multistranded superhelices as unconventional monomers, we exploited the utility of tetrazine (Tz) ligation with *trans*-cyclooctene (TCO) for the preparation of semiflexible ultrahigh molecular weight PCCs. This reaction features fast kinetics, high selectivity at

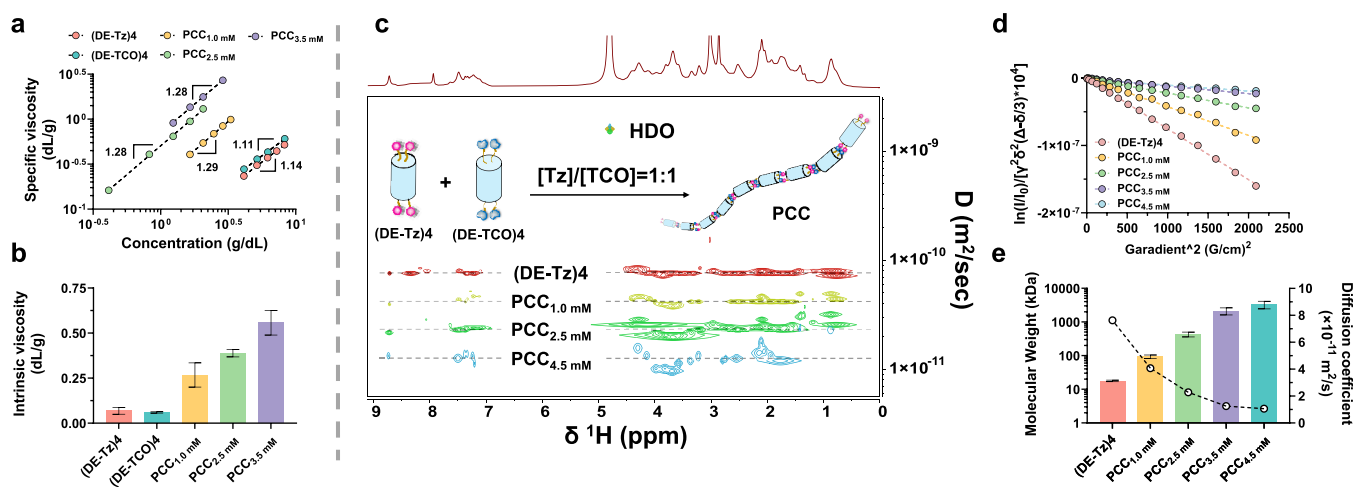


Figure 2. Evaluation of poly(DE4)_n molecular weight by dilute solution viscometry and diffusion-ordered NMR spectroscopy. (a) Specific viscosity as a function of solute concentration, confirming the maintenance of dilute solution regime. PCCs were prepared at Tz or TCO concentrations of 1.0 (PCC_{1.0} mM), 2.5 (PCC_{2.5} mM), and 3.5 mM (PCC_{3.5} mM). (b) Intrinsic viscosity for (DE-Tz)4, (DE-TCO)4, and PCCs prepared at various Tz/TCO concentrations (1.0, 2.5, and 3.5 mM). Error represents standard deviation. *n* = 3. (c) Stacked 2D DOSY spectra for monomer (DE-Tz)4 and PCCs synthesized at various Tz/TCO concentrations (1.0, 2.5, and 4.5 mM). The X-axis is the chemical shifts of ¹H (ppm) and the Y-axis is the diffusion coefficient (m²/sec). D₂O is used as the internal reference for viscosity control during the measurement. (d) Log plot of DOSY intensity attenuation at 3.97–3.99 ppm as a function of gradient squared for (DE-Tz)4 and PCCs synthesized at various Tz/TCO concentrations. Data are fitted to the Stejskal–Tanner equation, and the slope of the decay curve represents the diffusion coefficient. (e) Apparent molecular weight (bars) and diffusion coefficient (circles) for (DE-Tz)4 and PCCs. Error represents standard deviation. *n* = 15. The molecular weight was determined by fitting the DOSY diffusion coefficient to the standard curve reported by Bodor and Dudás.⁴⁷

low concentrations, and compatibility with biological systems.^{28,29} We strategically introduced flexible oligoethylene glycol (OEG3–4) linkers between the peptide backbone and bioorthogonal handles to afford semiflexible polymer chains. The PCCs were characterized experimentally and computationally to determine the secondary structure, diffusivity, molecular weight, and morphology. When polymerization was conducted at a relatively high bundlemer concentration, interchain entanglement of ultrahigh molecular weight, semiflexible peptidic polymers gave rise to elastic hydrogels that are mechanically robust.

RESULTS AND DISCUSSION

Formation of High Molecular Weight, Semiflexible PCC Rods. We have successfully applied tetrazine/TCO ligation, an inverse electron demand Diels–Alder reaction with a second order rate constant $k_2 > 10^3 \text{ M}^{-1} \text{ s}^{-1}$,^{28,32} to synthesize mechanically robust hydrogel fibers via step-growth polymerization using traditional poly(ethylene glycol)-based monomers.^{33–35} In this study, computationally designed peptides (“DE” and “DK”, Figure 1a) that form stable antiparallel homotetrameric bundles [(DE)4 and (DK)-4]^{26,36,37} were chosen as supramolecular monomers to produce PCCs via covalent step growth polymerization (Figure 1b). A cysteine residue was appended to the basic sequence at the N-terminus, through which the Tz or TCO functionality was introduced using maleimide-OEG4-tetrazine and maleimide-OEG3-TCO, respectively (Figures S1–S12). When assembled in water, the bundlemers contain precisely four identical functional groups evenly distributed on each end. Homopolymers were prepared using the DE peptide at a Tz/TCO molar ratio of 1/1 and monomer concentrations of 1.0–4.5 mM. At 2.5 mM, ~60% of tetrazine was consumed 1 min after mixing, as shown by the attenuation of the absorbance of the tetrazine chromophore (524 nm, Figure 1c). Tetrazine consumption

gradually leveled off after 10 min, and by 25 min, over 95% of tetrazine was converted to the cycloadduct (Figure 1d). A single peak at an elution time of 3 min with a molecular mass of 8249 Da was detected from ultra-performance liquid chromatography (UPLC)–tandem electrospray ionization mass spectrometry (ESI-MS, Figure 1e, Figure S13). During the experiment, all constituent bundles were denatured by acetonitrile, causing the polymer to dissociate into covalently linked dimeric peptides that were readily detectable. Overall, our results confirmed the accessibility of the bioorthogonal reactive groups and the high efficiency of the cycloaddition reaction.

Dilute solution viscometry was employed to indirectly assess the size of poly(DE4)_n under native conditions that preserve the secondary structure of the bundles. All measurements were performed in a good solvent (water) under a dilution solution regime with the polymer properly solvated, as evidenced by a logarithmic fit with a slope (concentration exponent) of ~1.3^{38–40} (Figure 2a), and negative Kraemer constant K_K ⁴¹ (Table S1). Intrinsic viscosity ($[\eta]$) was determined by fitting inherent and reduced viscosity to Huggins⁴² and Kreamer⁴³ Equations (Figure S14). As expected, the intrinsic viscosity of poly(DE4)_n was significantly higher than that for the monomeric bundlemers (DE-Tz)4 and (DE-TCO)4 (Figure 2b). Moreover, the intrinsic viscosity increased with the bundlemer concentration used during polymerization.

Because the translational diffusion coefficient of a molecular species is directly related to its molecular weight, we next employed diffusion-ordered spectroscopy (DOSY) to assess the poly(DE4)_n molecular weight under native conditions. In this experiment, the NMR signal attenuates as the applied magnetic field gradient strength (*g*) increases, following the Stejskal–Tanner equation⁴⁴ with a linear correlation between the logarithm of signal intensity (*I*/*I*₀) and *g*², the slope of which indicates self-diffusion coefficient (*D*_{DOSY}) (Figure 2d). The Stejskal–Tanner plots for signals from the aliphatic,

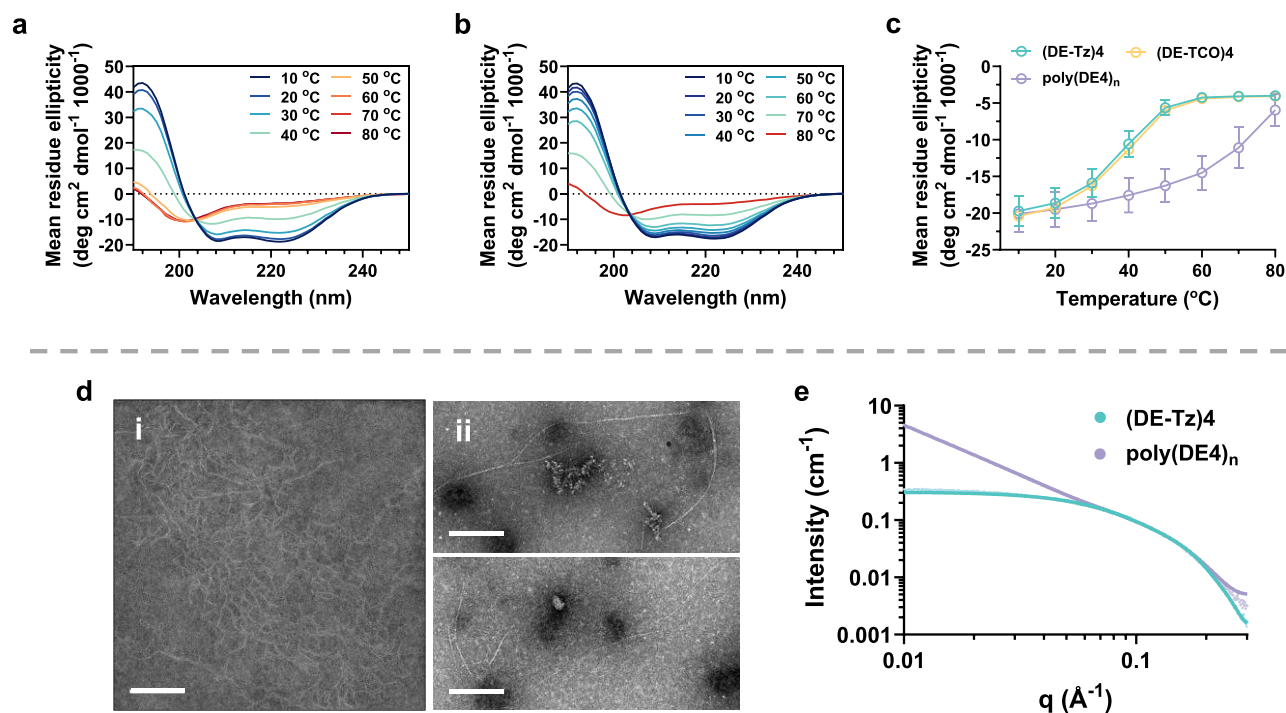


Figure 3. Characterization of the structure and morphology of poly(DE4)_n by circular dichroism (CD, a–c), transmission electron microscopy (TEM, d) and small-angle X-ray scattering (SAXS, e). (a) Representative CD spectra of (DE-Tz)₄ (a) and poly(DE4)_n (b) showing mean residue ellipticity (MRE) as a function of wavelength and temperature. The presence of the two minima at 208 and 222 nm confirms the formation of an α -helical structure. (c) Temperature-dependent MRE at 222 nm for (DE-Tz)₄, (DE-TCO)₄. The melting transition (T_m) for the coiled-coil building block is determined as 50–60 °C. (d) Visualization of poly(DE4)_n chains and aggregates by negative stain TEM. Poly(DE4)_n in DI water was either directly deposited on the TEM grid (i) or equilibrated in NaCl (1 M) prior to deposition (ii). Scale bar = 250 nm. (e) SAXS data curved fitted to a rigid cylinder model for (DE-Tz)₄ (cyan) and flexible cylinder model for poly(DE4)_n (purple).

aromatic, and amide regions all decayed linearly (Figure S15) for both the monomeric and polymeric species. D_{DOSY} decreased progressively from the monomer to the polymer and PCC prepared at a higher bundler concentration had a lower D_{DOSY} value (Table S2). In Figure 2c and Figure S16, 2D DOSY spectra for monomer (DE-Tz)₄ and poly(DE4)_n prepared at Tz (or TCO) concentrations of 1, 2.5, and 4.5 mM were overlaid for easy interpretation. In all experiments, the diffusion coefficient of the solvent (D₂O) was determined to be $1.62 \times 10^{-9} \text{ m}^2 \text{ s}^{-1}$, with a percent relative standard deviation of 4%, suggesting good viscosity control.⁴⁵ The DOSY cross-peaks of (DE-Tz)₄ were well-defined in the diffusional dimension while those for poly(DE4)_n prepared at higher Tz concentrations exhibited a relatively broader distribution, demonstrating a diversified range of polydispersity.⁴⁶

The assembled tetrameric bundles and the OEG linkers mimic the rigid and flexible regions of folded proteins, respectively. Therefore, to estimate poly(DE4)_n molecular weight, the average diffusion coefficient was fitted to a standard curve reported by Bodor and Dudás⁴⁷ for folded proteins (Figure 2e, Table S2). This method is valid because fitting the standard curve with the diffusion coefficient of the monomer (DE-Tz)₄ yielded 17.7 kDa, very close to the actual molecular weight of the monomer (Table S2). Consistent with the viscometry results, poly(DE4)_n prepared at a higher bundler concentration had a higher molecular weight. Importantly, polymerization at a Tz concentration of 4.5 mM led to the generation of poly(DE4)_n with an apparent molecular weight of over 3 million Da, with close to 200 coiled-coil repeats, each over 16 kDa. As shown in Figure 1c,d, a significant amount of

Tz was consumed immediately after (DE-Tz)₄ and (DE-TCO)₄ were mixed to produce PCC of low and intermediate molecular weight, forming two covalent linkages between neighboring bundles through end-to-end polymerization. The semiflexible nature of the PCC chains (see below) ensures an extended chain structure with the reactive ends well exposed for continued monomer addition, producing PCCs with exceptionally high molecular weight.^{33,48–50}

The DE peptide is designed to exhibit an α -helical coiled-coil conformation with D_2 symmetry in water, detectable by circular dichroism (CD) as two minima at 208 and 222 nm.⁵¹ Conjugation of Tz and TCO groups did not affect the ability of the peptide to self-assemble (Figure 3a, Figures S17 and S18). Both monomeric assemblies exhibited a melting temperature (T_m) of 50–60 °C, as determined by the appearance of absorbance at 200 nm corresponding to a random coil and the disappearance of the absorbance at 208 and 222 nm. Importantly, the secondary structure was preserved in the polymer product (Figure 3b). Comparison of the molar residue ellipticity (MRE) at 222 nm (Figure 3c) showed that poly(DE4)_n denatures (i.e., denaturation of the helices) at a significantly higher temperature (70–80 °C) than the bundlers (50–60 °C), suggesting stabilization of the helical conformation and strengthening of helix-to-helix association by covalent polymerization.^{26,52,53}

Examination of the polymerization product, cast on the grid directly from water, by transmission electron microscopy (TEM) with negative staining showed aggregates composed of semiflexible PCC chains (Figure 3d(i)). Examination under Cryo-TEM conditions also revealed substantial interchain association (Figure S21). Dilution and equilibration of

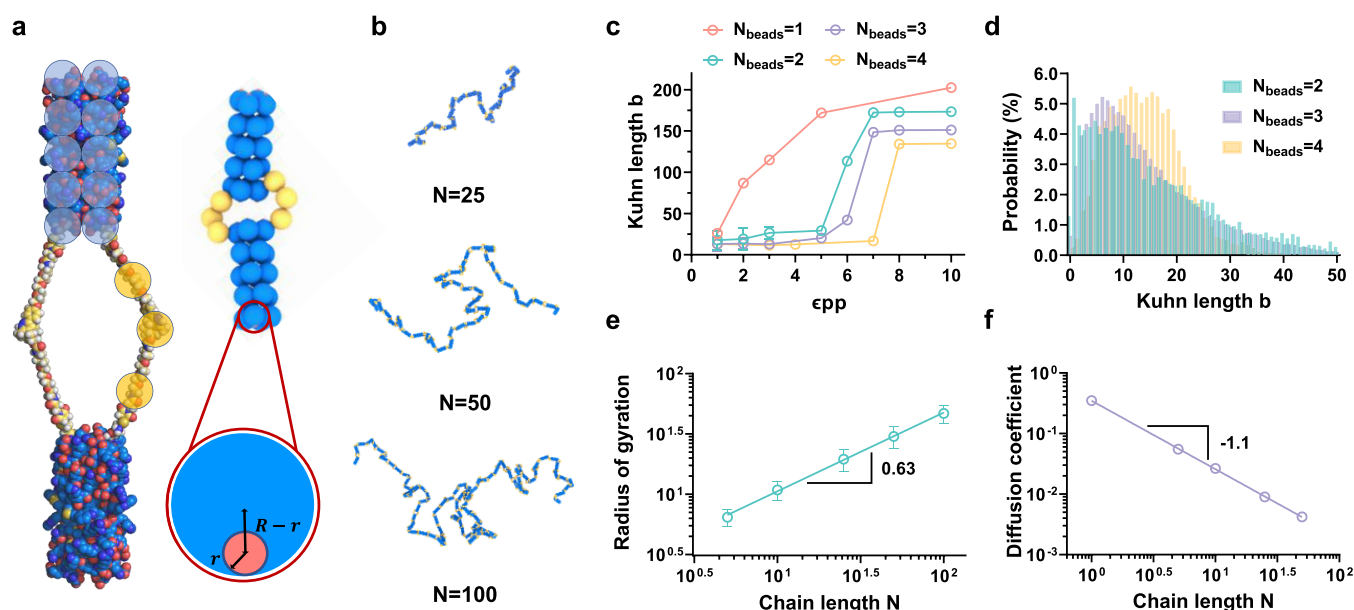


Figure 4. Coarse-grain (CG) modeling of polymeric coiled-coil peptides. (a) All-atom and coarse-grained representations of a linked dimer system wherein $r = 0.1 \sigma$, $R - r = 0.4 \sigma$. (b) CG chains with various number of bundlemer repeating units N and the length of linker is $N_{\text{beads}} = 3$. (c) Average Kuhn length b for the CG systems with different N_{beads} values at various attractive terminus interactions ϵ_{pp} , and the chain length is fixed at $N = 50$. (d) Kuhn length b distributions for the chains with different N_{beads} values at $N = 50$. The unit of the Kuhn length b is σ . (e) Chain conformations, radius of gyration R_g , as a function of the chain length N , and $N_{\text{beads}} = 3$. (f) Diffusion coefficient D as a function of chain length N at $N_{\text{beads}} = 3$. Error represents standard deviation. $n = 3$.

poly(DE4)_n in a NaCl solution prior to imaging significantly reduced polymer aggregation by charge screening, revealing well-dispersed single chains that appeared to be semiflexible (Figure 3d(ii)). This appearance is consistent with previously published semiflexible PCC chains prepared using maleimide functionalized bundlemer and tetrathiol pentaerythritol tetrakis(3-mercaptopropionate).²⁶ However, prior PCCs prepared using short-length interbundle coupling chemistry resulted in the formation of stiff molecular fibers with rigid-rod behavior. Therefore, the physical characteristics of the hybrid polymer are dependent on interbundle linker chemistry.

Small angle X-ray scattering (SAXS) was used to determine Kuhn lengths and cross-section radii of poly(DE4)_n (Figure 3e and Table S3). The (DE-Tz)4 building block fits reasonably well (reduced chi-squared, $\chi^2 = 1.43$) to a cylinder model with a length of 6.7 nm and a radius of 1.2 nm. This radius is consistent with the values for previously published bundlemers, while the length is consistent with a typical bundlemer ($l = 3.6\text{--}4.5 \text{ nm}$)^{26,36,37,54–56} plus extended OEG linkers at each N-termini. Treating poly(DE4)_n as a series of rigid bundlemer segments connected by flexible OEG linkers, we fitted it to a flexible cylinder model in SASview as has been previously done for semiflexible bundlemer rods.^{26,56} Additionally, given the relatively long and flexible nature of the OEG linker, with a total of 7 ethylene oxide repeats between adjacent bundlemers, it is unlikely for the polymer to have a singular fixed Kuhn length but instead a range of Kuhn lengths dependent on whether the OEG is extended or collapsed. By fitting the Kuhn length with a Gaussian distribution (Figure S22), our analyses revealed that poly(DE4)_n (reduced $\chi^2 = 1.12$) had a radius of 1.3 nm and an average Kuhn length of 6.3 nm with a standard deviation of 1.3 nm. This Kuhn length is slightly smaller than the previously reported $7.1 \pm 0.1 \text{ nm}$ for semiflexible bundlemer chains⁵⁶ linked with a 4-arm PEG linker but is still indicative of a single bundlemer persistence length.

Separately, a coarse-grained (CG) model was employed to microscopically investigate the conformation of doubly linked bundlemer chains (Figure 4a,b). Based on the rigid rod chain extrapolated from our previous study,²⁶ attractive interactions among the terminal residues of bundlemers and the intervening chemical linkers are critical in determining the stiffness of the chain. Therefore, both the terminus interaction energy, ϵ_{pp} , and the length of the linkers, N_{beads} , were varied to identify the most suitable parameters that can capture chain properties observed in the experiments. Herein, the Kuhn length, b , related to the flexibility of the chains served as a metric for comparison between simulations and experimental results. As shown in Figure 4c, a competing effect between N_{beads} and ϵ_{pp} was observed. For chains with $N_{\text{beads}} = 1$, the Kuhn length, b , continuously increased as the attractive interactions among the adjacent bundlemer termini became larger, ultimately reaching a plateau with increasing ϵ_{pp} , indicating rigid rod formation. In contrast, a sharp transition regime was observed for chains with a longer linker. As we explored the low ϵ_{pp} range, the Kuhn length for both $N_{\text{beads}} = 3$ and $N_{\text{beads}} = 4$ with $\epsilon_{\text{pp}} = 1.0$ were similarly close to the experimentally measured results. Moreover, for $N_{\text{beads}} = 3$, the Kuhn length distribution plot (Figure 4d) shows the highest probability around 6.0σ , which is approximately 6.0 nm in real units, in good agreement with SAXS analysis of experimentally produced chains in terms of local chain conformation.

We further interrogated the chain conformation of PCCs computationally by varying the number of bundlemer repeat units N while keeping $N_{\text{beads}} = 3$ and $\epsilon_{\text{pp}} = 1.0$. From the scaling of the radius of gyration (R_g) with N as $R_g \approx N^\nu$, the Flory exponent was determined as $\nu = 0.63$, suggesting that the modeled polymer chain was in a good solvent with relatively extended conformations (Figure 4e). The calculated ratio $\frac{R_g^2}{R_e^2} \approx 6.7$, where end-to-end distance $R_e \approx 91 \sigma$ for the chain

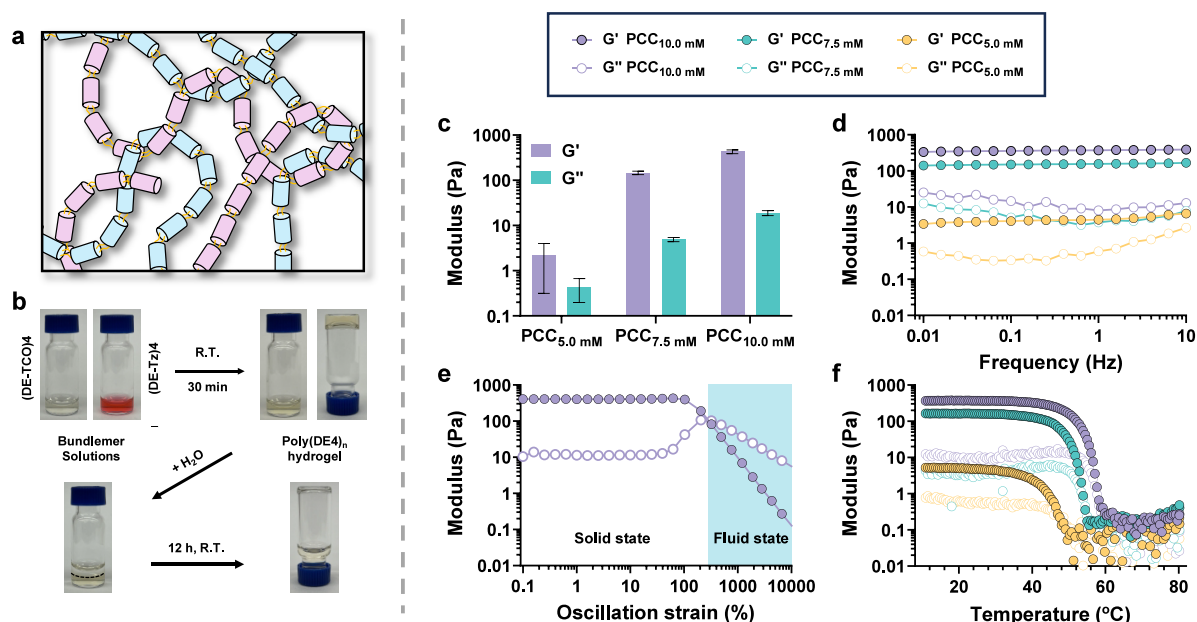


Figure 5. PCC hydrogels via intermolecular entanglement. (a) Schematic illustration of polymeric coiled-coil hydrogels via the entanglement of semiflexible polymer chains. Neighboring chains are contrasted in pink and cyan for easy interpretation. (b) Vial inversion experiment showing hydrogel formation after mixing of bioorthogonally functionalized coiled-coil peptides at a Tz/TCO ratio of 1:1 and hydrogel dissolution after the addition of water and overnight equilibration. (c) Bioorthogonal polymerization at a higher bundlemer concentration leads to the establishment of a stiffer hydrogel. The elastic (G') and loss (G'') moduli are determined from the time sweep experiment at 1 Hz and 1% strain. Error represents standard deviation. $n = 3$. (d) Hydrogel stiffness is independent of the oscillatory frequency. Frequency sweep experiments are conducted from 0.01 to 10 Hz with a fixed strain of 1%. (e) High oscillatory strain ($\sim 300\%$) is required to convert the elastic solid to a liquid. The crossover point of G' and G'' indicates the transition from solid to fluid states. The amplitude sweep experiments were performed at a fixed frequency of 1 Hz on hydrogels prepared at a Tz/TCO concentration of 10 mM. (f) Storage and loss moduli of peptidic hydrogels as a function of the temperature. The crossover points of G' and G'' represent the melting temperature of hydrogels.

with $N = 100$ was above the theoretical value 6.3 for flexible chain in a good solvent.⁵⁷ Furthermore, diffusion coefficient D , calculated from the mean square displacement (MSD) (Figure S23) of PCC chains decreased as N increased (Figure 4f), is consistent with experimental observations (Figure 2e). The scaling of D with N followed $D \approx N^{-1.1}$, which indicated a diffusive behavior within the Rouse regimes.³⁹ Overall, the simulations provide a molecular picture that PCCs consisting of covalently linked coiled-coil bundles behave like semiflexible polymers, even though the constituent bundlemer building blocks are inherently rigid due to the presence of flexible OEG linkers between neighboring bundles.

PCC Hydrogels via Interchain Entanglements. When polymerization was conducted at a Tz concentration of 5 mM, a transparent hydrogel with a yellow tint was obtained (Figure Sa,b, Video S1). The distinct pink-red color associated with the tetrazine chromophore disappeared rather rapidly (within minutes) after (DE-TCO)₄ and (DE-Tz)₄ were mixed. Characterization by oscillatory rheometry indicated a liquid-to-solid transition at 5 min (Figure S24a), with the storage modulus (G') significantly higher than the loss modulus (G''). After 20 min of polymerization, both G' and G'' values reached a plateau. The gelation kinetics and hydrogel stiffness are strongly dependent on the Tz concentration in feed (Figure 5c, Figure S24). When polymerization was conducted at a Tz concentration of 10 mM, hydrogels reached a G' of ~ 400 Pa. Although the supramolecular bundlemer building blocks are tetrafunctional, branching and cross-linking via the formation of a stable cycloaddition adduct is not possible owing to the high rigidity of the antiparallel homotetrameric coiled-coils.²⁶ Once one covalent bond between the bundlemers has formed,

a second reaction between the same pair is highly likely due to the proximity of the functional groups. Although the Tz/TCO reaction sites are separated from the ends of the rigid bundlemers by OEG7, these linkages are not sufficiently long to enable branching. As discussed above, owing to the presence of flexible OEG linkers between each bundle, these hybrid polymers exhibited a high chain flexibility. Thus, we reason that hydrogel formation is a direct result of physical entanglement of ultrahigh molecular weight PCCs. This hypothesis is supported by our experimental observations; the addition of copious amounts of water to the as-synthesized hydrogel led to complete dissolution overnight (Figure 5b).

We further analyzed the viscoelastic properties of these hydrogels over a wide range of frequencies (Figure 5d) and strains (Figure S25). The storage modulus remained constant at frequencies of 0.01–10 Hz and oscillation strain of 1%, indicating that the physical entanglement is long-lived. Unlike other entangled hydrogels that fail at very low strains,²³ this type of noncovalent hydrogel exhibits a solid-to-fluid transition at 300% strain (Figure 5e) that is attributable to the disentanglement of polymer chains. The solid-to-fluid transition was also observed with increasing temperature, and the transition occurred at a higher temperature for hydrogel prepared at a higher Tz concentration in the feed (Figure 5f). We hypothesized that as the temperature increased, poly-(DE4)_n became partially denatured via the disassembly of individual bundles, yielding low molecular weight, covalently coupled peptide homodimers (Figure 6a) that are unable to entangle.^{58,59} When the peptide solution was subsequently cooled to 10 °C, we did not observe any gel formation (Figure 6b–d).

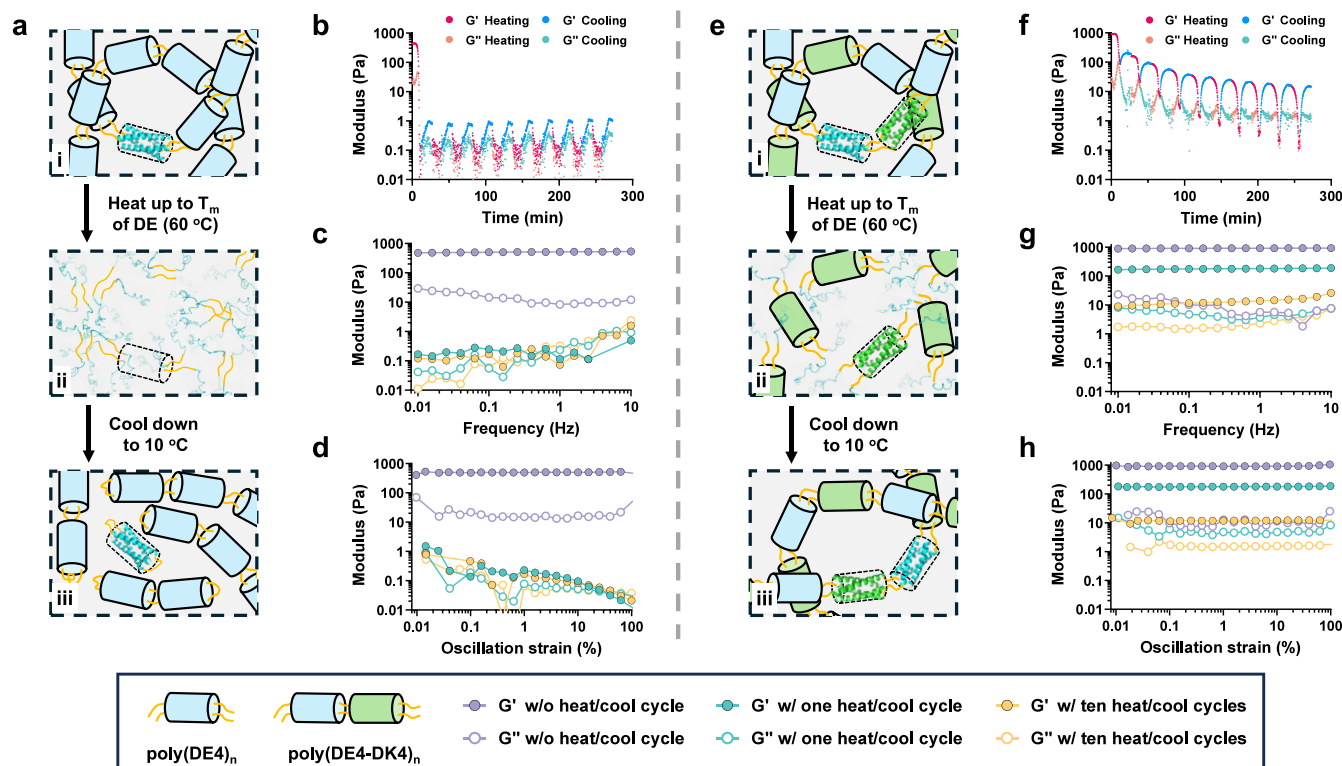


Figure 6. Effects of cyclic heating/cooling between 60 °C (T_m of DE4) and 10 °C on the mechanical properties of poly(DE4)_n and poly(DE4-DK4)_n hydrogels. (a) Proposed molecular structure of poly(DE4)_n hydrogels at ambient temperature (i), after heating to 60 °C (ii) and then cooling to 10 °C (iii). (b) Storage (G') and loss moduli (G'') were plotted as a function of time under temperature cycling. Time sweep experiments were conducted at a frequency of 0.1 Hz and a strain of 0.5%. The temperature was ramped up to 60 °C at 5 °C/min, held constant for 2 min, then ramped down at the same speed and held constant for 5 min. (c) Storage (G') and loss moduli (G'') were plotted as a function of frequency at a constant strain of 0.5% for hydrogels initially formed (purple), after the first (cyan) and the 10th (orange) heating/cooling cycle. (d) Storage (G') and loss moduli (G'') were plotted as a function of strain at a constant frequency of 0.1 Hz for hydrogels initially formed (purple), after the first (cyan) and the 10th (orange) heating/cooling cycles. (e) Proposed molecular structure of poly(DE4)_n hydrogels at ambient temperature (i), after heating to 60 °C (ii) and then cooling down to 10 °C (iii). (f) Storage (G') and loss moduli (G'') were plotted as a function of time under temperature cycling. Time sweep experiments were conducted at a frequency of 0.1 Hz and a strain of 0.5%. The temperature was ramped up to 60 °C at 5 °C/min, held constant for 2 min, then ramped down at the same speed and held constant for 5 min. (g) Storage (G') and loss moduli (G'') were plotted as a function of frequency at a constant strain of 0.5% for hydrogels initially formed (purple), after the first (cyan) and the 10th (orange) heating/cooling cycle. (h) Storage (G') and loss moduli (G'') were plotted as a function of strain at a constant frequency of 0.1 Hz for hydrogels initially formed (purple), after the first (cyan) and the 10th (orange) heating/cooling cycles. Figures were created using AlphaFold2³⁰ and BioRender.com.

To further demonstrate the versatility of the bioorthogonal strategy, (DE-Tz)4 was copolymerized with (DK-TCO)4 (Figure 1a, Figures S7–S12) that is compositionally distinct and thermally more stable (T_m = 70–80 °C, Figures S19 and S20). Polymerization at 10 mM led to the rapid formation of a physical gel with $G' \approx 1,000$ Pa (Figure 6e–h), presumably through the entanglement of high molecular weight poly(DE4-DK4)_n. When heated to 60 °C, G' gradually dropped below 100 Pa while G'' increased to just over 100 Pa, indicating transformation to a fluid (Figure 6f). Upon cooling to 10 °C, a sol–gel transition was observed, giving rise to a softer gel ($G' = 200$ Pa). The copolymer system can withstand multiple heating and cooling cycles with partial recovery of the initial gel stiffness. By the end of the 10th cycle, the recovered gel had G' and G'' of 20 and 2 Pa, respectively (Figure 6f–h). Exposure of poly(DK4)_n to the same heating/cooling regimen (60–10 °C) did not significantly alter the mechanical integrity of the hydrogel (Figure S26). However, cycling between 80 and 10 °C led to permanent disintegration of the network structure (Figure S27).

We speculate that at 60 °C, only the DE4 units were denatured; during the cooling cycle, the intact DK4 bundles serve as templates for the association of neighboring DE peptides, leading to the growth of high molecular weight products. However, when the neighboring units are not perfectly aligned, network defects are generated due to the inability of the DE peptides to reassemble. Repeated heating and cooling result in the accumulation of network defects, compromising the overall hydrogel mechanical properties. This is not the case for the homodimeric hydrogel system. At 60 °C, poly(DE4)_n dissociates to peptide dimers covalently coupled through a flexible OEG7 linker (Figure 1e, Figure S26). To re-establish the molecular structure of the “homopolymer” at 10 °C, four dimeric units must reassemble in an antiparallel fashion to allow supramolecular polymerization. The flexible OEG7 linker between the two identical peptides permits intramolecular association through back-folding, resulting in the formation of a “molecular capper” that distorts the overall reaction stoichiometry and prevents the restoration of the entangled network structure.

CONCLUSIONS

In summary, the rapid and highly efficient tetrazine-TCO ligation enabled the synthesis of polymeric coiled-coils with exceptional molecular weight. The long-chain hybrid polymer produced at a bundler concentration of 4.5 mM consists of up to 200 covalently linked rigid four-helical peptide bundles. Unlike the stiff, rod-like polymeric coiled-coils reported previously, the hybrid polymers developed here are semiflexible owing to the presence of defined PEG linkers between adjacent bundles. Polymerization at a monomer concentration greater than 4.5 mM resulted in hydrogel formation through entanglement of the semiflexible polymer chains. The hybrid polymer recapitulated key features of supramolecular polymers, including dynamic and reversible properties, and at the same time exhibited the robustness and stability of conventional covalently linked polymers. Physical gels established through intermolecular entanglements of the semiflexible polymeric chains behaved like covalent networks. While conventional flexible polymers unentangle readily through reptation, semiflexible chains disentangle due to correlated constraint release, which leads to equilibration of internal bending modes before polymers diffuse the full tube length.⁶⁰ The bioorthogonality of tetrazine ligation allows the synthesis of new nanometer-scale structures by combining bundler building blocks with diverse functionalities and structures. Given the tunability of stiffness and thermodynamic reversibility, the hybrid hydrogel system investigated here may find applications in 3D printing, cell culture, and drug release.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.macromol.4c01866>.

Synthetic procedures, characterization methods, coarse grain simulation, and supplemental figures (PDF)

Video S1 (MP4)

AUTHOR INFORMATION

Corresponding Author

Xinqiao Jia – Department of Materials Science and Engineering, Department of Biomedical Engineering, Department of Biological Sciences, and Delaware Biotechnology Institute, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0000-0002-3564-5576; Email: xjia@udel.edu

Authors

Hanyuan Gao – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0009-0006-3096-8460

Tianren Zhang – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States; Department of Chemistry, University of Pennsylvania, Philadelphia, Pennsylvania 19104, United States; orcid.org/0000-0003-2899-5727

Matthew G. Langenstein – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0000-0002-8742-111X

Weiran Xie – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States

Samiksha Udan – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States

Zihan Zhang – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0000-0002-5912-2497

Jeffery G. Saven – Department of Chemistry, University of Pennsylvania, Philadelphia, Pennsylvania 19104, United States; orcid.org/0000-0001-5027-7241

Shi Bai – Department of Chemistry and Biochemistry, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0000-0003-2126-450X

Darrin J. Pochan – Department of Materials Science and Engineering, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0000-0002-0454-2339

Joseph M. Fox – Department of Materials Science and Engineering and Department of Chemistry and Biochemistry, University of Delaware, Newark, Delaware 19716, United States; orcid.org/0000-0002-8258-1640

Complete contact information is available at:

<https://pubs.acs.org/doi/10.1021/acs.macromol.4c01866>

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This research was primarily/partially supported by the National Science Foundation (NSF) through the University of Delaware Materials Research Science and Engineering Center DMR-2011824. Additional support was received from the National Institutes of Health (NIDCD, R01DC014461; NIDCR R01DE029655), NSF (DMR 1809612), and Delaware Bioscience Center for Advanced Technology (DE-CAT 12A00448). Support was also provided by the Department of Energy (DOE) Office of Basic Energy Sciences, Biomolecular Materials Program under grant No. DE-SC0019355. Additional support for the simulation of solution behavior was provided under award DE-SC0019282. Computational studies were performed using allocation TG-CHE110041 from the Advanced Cyberinfrastructure Coordination Ecosystem: Services & Support (ACCESS) program, which is supported by National Science Foundation grants #1548562, #2138259, #2138286, #2138307, #2137603, and #2138296.

REFERENCES

- (1) Odian, G. *Principles of Polymerization*; John Wiley & Sons, 2004.
- (2) Ouchi, M.; Terashima, T.; Sawamoto, M. Precision control of radical polymerization via transition metal catalysis: from dormant species to designed catalysts for precision functional polymers. *Acc. Chem. Res.* **2008**, *41* (9), 1120–1132.
- (3) Worch, J. C.; Dove, A. P. Click Step-Growth Polymerization and E/Z Stereochemistry Using Nucleophilic Thiol-yne/-ene Reactions: Applying Old Concepts for Practical Sustainable (Bio)Materials. *Acc. Chem. Res.* **2022**, *55* (17), 2355–2369.
- (4) Honda, S.; Odelius, K.; Sardon, H. Organomediated polymerization. *Communications Chemistry* **2024**, *7* (1), 62.
- (5) Milton, M.; Deng, R.; Mann, A.; Wang, C.; Tang, D.; Weck, M. Secondary Structure in Nonpeptidic Supramolecular Block Copolymers. *Acc. Chem. Res.* **2021**, *54* (10), 2397–2408.
- (6) Harth, E.; Van Horn, B.; Lee, V. Y.; Germack, D. S.; Gonzales, C. P.; Miller, R. D.; Hawker, C. J. A facile approach to architecturally defined nanoparticles via intramolecular chain collapse. *J. Am. Chem. Soc.* **2002**, *124* (29), 8653–8660.

- (7) Foster, E. J.; Berda, E. B.; Meijer, E. W. Metastable supramolecular polymer nanoparticles via intramolecular collapse of single polymer chains. *J. Am. Chem. Soc.* **2009**, *131* (20), 6964–6966.
- (8) Schmidt, B. V.; Fechner, N.; Falkenhagen, J.; Lutz, J. F. Controlled folding of synthetic polymer chains through the formation of positionable covalent bridges. *Nat. Chem.* **2011**, *3* (3), 234–238.
- (9) Mato, Y.; Honda, K.; Ree, B. J.; Tajima, K.; Yamamoto, T.; Deguchi, T.; Isono, T.; Satoh, T. Programmed folding into spiro-multicyclic polymer topologies from linear and star-shaped chains. *Communications Chemistry* **2020**, *3* (1), 97.
- (10) Alberts, B.; Johnson, A.; Lewis, J.; Raff, M.; Roberts, K.; Walter, P. *Molecular Biology of the Cell*; Garland Science: New York, 2002.
- (11) Trinick, J. Cytoskeleton: Titin as a scaffold and spring. *Curr. Biol.* **1996**, *6* (3), 258–260.
- (12) Tskhovrebova, L.; Trinick, J. Titin: properties and family relationships. *Nat. Rev. Mol. Cell Biol.* **2003**, *4* (9), 679–689.
- (13) Wang, K.; Forbes, J. G.; Jin, A. J. Single molecule measurements of titin elasticity. *Prog. Biophys. Mol. Biol.* **2001**, *77* (1), 1–44.
- (14) Eldirany, S. A.; Lomakin, I. B.; Ho, M.; Bunick, C. G. Recent insight into intermediate filament structure. *Curr. Opin Cell Biol.* **2021**, *68*, 132–143.
- (15) Webber, M. J.; Appel, E. A.; Meijer, E. W.; Langer, R. Supramolecular biomaterials. *Nat. Mater.* **2016**, *15* (1), 13–26.
- (16) Hu, K.; Jiang, Y.; Xiong, W.; Li, H.; Zhang, P.-Y.; Yin, F.; Zhang, Q.; Geng, H.; Jiang, F.; Li, Z.; et al. Tuning peptide self-assembly by an in-tether chiral center. *Science Advances* **2018**, *4* (5), No. eaar5907.
- (17) Hartgerink, J. D.; Beniash, E.; Stupp, S. I. Self-Assembly and Mineralization of Peptide-Amphiphile Nanofibers. *Science* **2001**, *294* (5547), 1684–1688.
- (18) Cui, H.; Cheetham, A. G.; Pashuck, E. T.; Stupp, S. I. Amino Acid Sequence in Constitutionally Isomeric Tetrapeptide Amphiphiles Dictates Architecture of One-Dimensional Nanostructures. *J. Am. Chem. Soc.* **2014**, *136* (35), 12461–12468.
- (19) Yuan, C.; Ji, W.; Xing, R.; Li, J.; Gazit, E.; Yan, X. Hierarchically oriented organization in supramolecular peptide crystals. *Nature Reviews Chemistry* **2019**, *3* (10), 567–588.
- (20) Sinha, N. J.; Langenstein, M. G.; Pochan, D. J.; Kloxin, C. J.; Saven, J. G. Peptide Design and Self-assembly into Targeted Nanostructure and Functional Materials. *Chem. Rev.* **2021**, *121* (22), 13915–13935.
- (21) de Greef, T. F. A.; Meijer, E. W. Supramolecular polymers. *Nature* **2008**, *453* (7192), 171–173.
- (22) Tang, W.; Becker, M. L. Click[®] reactions: a versatile toolbox for the synthesis of peptide-conjugates. *Chem. Soc. Rev.* **2014**, *43* (20), 7013–7039.
- (23) Li, C.; Iscen, A.; Sai, H.; Sato, K.; Sather, N. A.; Chin, S. M.; Álvarez, Z.; Palmer, L. C.; Schatz, G. C.; Stupp, S. I. Supramolecular-covalent hybrid polymers for light-activated mechanical actuation. *Nat. Mater.* **2020**, *19* (8), 900–909.
- (24) Zhang, X. Supramolecular Polymer Chemistry: Past, Present, and Future. *Chin. J. Polym. Sci.* **2022**, *40* (6), 541–542.
- (25) Fears, K. P.; Kolel-Veetil, M. K.; Barlow, D. E.; Bernstein, N.; So, C. R.; Wahl, K. J.; Li, X.; Kulp, J. L.; Latour, R. A.; Clark, T. D. High-performance nanomaterials formed by rigid yet extensible cyclic β -peptide polymers. *Nat. Commun.* **2018**, *9* (1), 4090.
- (26) Wu, D.; Sinha, N.; Lee, J.; Sutherland, B. P.; Halaszynski, N. I.; Tian, Y.; Caplan, J.; Zhang, H. V.; Saven, J. G.; Kloxin, C. J.; et al. Polymers with controlled assembly and rigidity made with click-functional peptide bundles. *Nature* **2019**, *574* (7780), 658–662.
- (27) Woolfson, D. N. Coiled-Coil Design: Updated and Upgraded. *Subcell Biochem* **2017**, *82*, 35–61.
- (28) Blackman, M. L.; Royzen, M.; Fox, J. M. Tetrazine ligation: fast bioconjugation based on inverse-electron-demand Diels-Alder reactivity. *J. Am. Chem. Soc.* **2008**, *130* (41), 13518–13519.
- (29) Scinto, S. L.; Bilodeau, D. A.; Hincapie, R.; Lee, W.; Nguyen, S. S.; Xu, M.; am Ende, C. W.; Finn, M. G.; Lang, K.; Lin, Q.; et al. Bioorthogonal chemistry. *Nature Reviews Methods Primers* **2021**, *1* (1), 30.
- (30) Jumper, J.; Evans, R.; Pritzel, A.; Green, T.; Figurnov, M.; Ronneberger, O.; Tunyasuvunakool, K.; Bates, R.; Židek, A.; Potapenko, A.; et al. Highly accurate protein structure prediction with AlphaFold. *Nature* **2021**, *596* (7873), 583–589.
- (31) Hanwell, M. D.; Curtis, D. E.; Lonie, D. C.; Vandermeersch, T.; Zurek, E.; Hutchison, G. R. Avogadro: an advanced semantic chemical editor, visualization, and analysis platform. *Journal of Cheminformatics* **2012**, *4* (1), 17.
- (32) Dicker, K. T.; Song, J.; Moore, A. C.; Zhang, H.; Li, Y.; Burris, D. L.; Jia, X.; Fox, J. M. Core-shell patterning of synthetic hydrogels via interfacial bioorthogonal chemistry for spatial control of stem cell behavior. *Chem. Sci.* **2018**, *9* (24), 5394–5404.
- (33) Liu, S.; Zhang, H.; Remy, R. A.; Deng, F.; Mackay, M. E.; Fox, J. M.; Jia, X. Meter-long multiblock copolymer microfibers via interfacial bioorthogonal polymerization. *Adv. Mater.* **2015**, *27* (17), 2783–2790.
- (34) Liu, S.; Moore, A. C.; Zerdoum, A. B.; Zhang, H.; Scinto, S. L.; Zhang, H.; Gong, L.; Burris, D. L.; Rajasekaran, A. K.; Fox, J. M.; et al. Cellular interactions with hydrogel microfibers synthesized via interfacial tetrazine ligation. *Biomaterials* **2018**, *180*, 24–35.
- (35) George, O. J.; Song, J.; Benson, J. M.; Fang, Y.; Zhang, H.; Burris, D. L.; Fox, J. M.; Jia, X. Tunable Synthesis of Hydrogel Microfibers via Interfacial Tetrazine Ligation. *Biomacromolecules* **2022**, *23* (7), 3017–3030.
- (36) Zhang, H. V.; Polzer, F.; Haider, M. J.; Tian, Y.; Villegas, J. A.; Kiick, K. L.; Pochan, D. J.; Saven, J. G. Computationally designed peptides for self-assembly of nanostructured lattices. *Sci. Adv.* **2016**, *2* (9), No. e1600307.
- (37) Guo, R.; Sinha, N. J.; Misra, R.; Tang, Y.; Langenstein, M.; Kim, K.; Fagan, J. A.; Kloxin, C. J.; Jensen, G.; Pochan, D. J.; et al. Computational Design of Homotetrameric Peptide Bundle Variants Spanning a Wide Range of Charge States. *Biomacromolecules* **2022**, *23* (4), 1652–1661.
- (38) Morris, E. R.; Cutler, A. N.; Ross-Murphy, S. B.; Rees, D. A.; Price, J. Concentration and shear rate dependence of viscosity in random coil polysaccharide solutions. *Carbohydr. Polym.* **1981**, *1* (1), 5–21.
- (39) Rubinstein, M.; Colby, R. H. *Polymer physics*; Oxford university press, 2003.
- (40) Shahbazi, M.; Jäger, H.; Ettelaie, R.; Chen, J. Construction of 3D printed reduced-fat meat analogue by emulsion gels. Part I: Flow behavior, thixotropic feature, and network structure of soy protein-based inks. *Food Hydrocolloids* **2021**, *120*, No. 106967.
- (41) O'Sullivan, J.; Murray, B.; Flynn, C.; Norton, I. The effect of ultrasound treatment on the structural, physical and emulsifying properties of animal and vegetable proteins. *Food Hydrocolloids* **2016**, *53*, 141–154.
- (42) Huggins, M. L. The Viscosity of Dilute Solutions of Long-Chain Molecules. IV. Dependence on Concentration. *J. Am. Chem. Soc.* **1942**, *64* (11), 2716–2718.
- (43) Kraemer, E. O. Molecular Weights of Celluloses and Cellulose Derivates. *Industrial & Engineering Chemistry* **1938**, *30* (10), 1200–1203.
- (44) Stejskal, E. O.; Tanner, J. E. Spin Diffusion Measurements: Spin Echoes in the Presence of a Time-Dependent Field Gradient. *J. Chem. Phys.* **1965**, *42* (1), 288–292.
- (45) Li, W.; Chung, H.; Daeffler, C.; Johnson, J. A.; Grubbs, R. H. Application of 1H DOSY for Facile Measurement of Polymer Molecular Weights. *Macromolecules* **2012**, *45* (24), 9595–9603.
- (46) Viéville, J.; Tanty, M.; Delsuc, M.-A. Polydispersity index of polymers revealed by DOSY NMR. *J. Magn. Reson.* **2011**, *212* (1), 169–173.
- (47) Dudás, E. F.; Bodor, A. Quantitative, Diffusion NMR Based Analytical Tool To Distinguish Folded, Disordered, and Denatured Biomolecules. *Anal. Chem.* **2019**, *91* (8), 4929–4933.
- (48) Tsarevsky, N. V.; Sumerlin, B. S.; Matyjaszewski, K. Step-Growth “Click” Coupling of Telechelic Polymers Prepared by Atom Transfer Radical Polymerization. *Macromolecules* **2005**, *38* (9), 3558–3561.

- (49) Grieshaber, S. E.; Farran, A. J.; Lin-Gibson, S.; Kiick, K. L.; Jia, X. Synthesis and Characterization of Elastin-Mimetic Hybrid Polymers with Multiblock, Alternating Molecular Architecture and Elastomeric Properties. *Macromolecules* **2009**, *42* (7), 2532–2541.
- (50) Grieshaber, S. E.; Farran, A. J.; Bai, S.; Kiick, K. L.; Jia, X. Tuning the properties of elastin mimetic hybrid copolymers via a modular polymerization method. *Biomacromolecules* **2012**, *13* (6), 1774–1786.
- (51) Wallimann, P.; Kennedy, R. J.; Miller, J. S.; Shalongo, W.; Kemp, D. S. Dual Wavelength Parametric Test of Two-State Models for Circular Dichroism Spectra of Helical Polypeptides: Anomalous Dichroic Properties of Alanine-Rich Peptides. *J. Am. Chem. Soc.* **2003**, *125* (5), 1203–1220.
- (52) Gazi, A. D.; Bastaki, M.; Charova, S. N.; Gkoukoulia, E. A.; Kapellios, E. A.; Panopoulos, N. J.; Kokkinidis, M. Evidence for a Coiled-coil Interaction Mode of Disordered Proteins from Bacterial Type III Secretion Systems*. *J. Biol. Chem.* **2008**, *283* (49), 34062–34068.
- (53) Ren, L.; Lu, X.; Li, W.; Yan, J.; Whittaker, A. K.; Zhang, A. Thermoresponsive Helical Dendronized Poly(phenylacetylene)s: Remarkable Stabilization of Their Helicity via Photo-Dimerization of the Dendritic Pendants. *J. Am. Chem. Soc.* **2023**, *145* (45), 24906–24921.
- (54) Haider, M. J.; Zhang, H. V.; Sinha, N.; Fagan, J. A.; Kiick, K. L.; Saven, J. G.; Pochan, D. J. Self-assembly and soluble aggregate behavior of computationally designed coiled-coil peptide bundles. *Soft Matter* **2018**, *14* (26), 5488–5496.
- (55) Sinha, N. J.; Wu, D.; Kloxin, C. J.; Saven, J. G.; Jensen, G. V.; Pochan, D. J. Polyelectrolyte character of rigid rod peptide bundlemer chains constructed via hierarchical self-assembly. *Soft Matter* **2019**, *15* (48), 9858–9870.
- (56) Sinha, N. J.; Shi, Y.; Tang, Y.; Kloxin, C. J.; Saven, J. G.; Faraone, A.; Jensen, G. V.; Pochan, D. J. Intramolecular structure and dynamics in computationally designed peptide-based polymers displaying tunable chain stiffness. *Physical Review Materials* **2021**, *5* (9), No. 095601.
- (57) des Cloizeaux, J.; Jannink, G. *Polymers in Solution: Their Modelling and Structure*; Oxford Science Publications, 1991.
- (58) Sautaux, J.; Marx, F.; Gunkel, I.; Weder, C.; Schrettl, S. Mechanically robust supramolecular polymer co-assemblies. *Nat. Commun.* **2022**, *13* (1), 356.
- (59) Peng, Y. H.; Hsiao, S. K.; Gupta, K.; Ruland, A.; Auernhammer, G. K.; Maitz, M. F.; Boye, S.; Lattner, J.; Gerri, C.; Honigsmann, A.; et al. Dynamic matrices with DNA-encoded viscoelasticity for cell and organoid culture. *Nat. Nanotechnol.* **2023**, *18*, 1463–1473.
- (60) Lang, P.; Frey, E. Disentangling entanglements in biopolymer solutions. *Nat. Commun.* **2018**, *9* (1), 494.