

MSE-238
Structure of Materials

Week 8 - Diffraction
Spring 2025

Marianne Liebi (MX/PSI)

Ecole Polytechnique Fédérale de Lausanne

EPFL

Overview

Diffraction:

- The scattering vector
- Ewald sphere
- Interaction with different radiation
- sample types and measurement methods
- influence of imperfect microstructure

mixed with repetition of crystallography on examples

- hard sphere model
- interstitial sites
- crystal symmetry
- crystal planes, family of planes
- quasi-crystal

→(Hammond Chapter 8-10)

→ Phil Willmott, “Introduction to Synchrotron Radiation” Chapter 6

Scattering/Diffraction: the scattering vector


scattering vector q

$$q = k_0 - k$$


see similarity to the reciprocal lattice vector

$$K = k - k_0$$

→ Laue condition: $K = q$
constructive interference

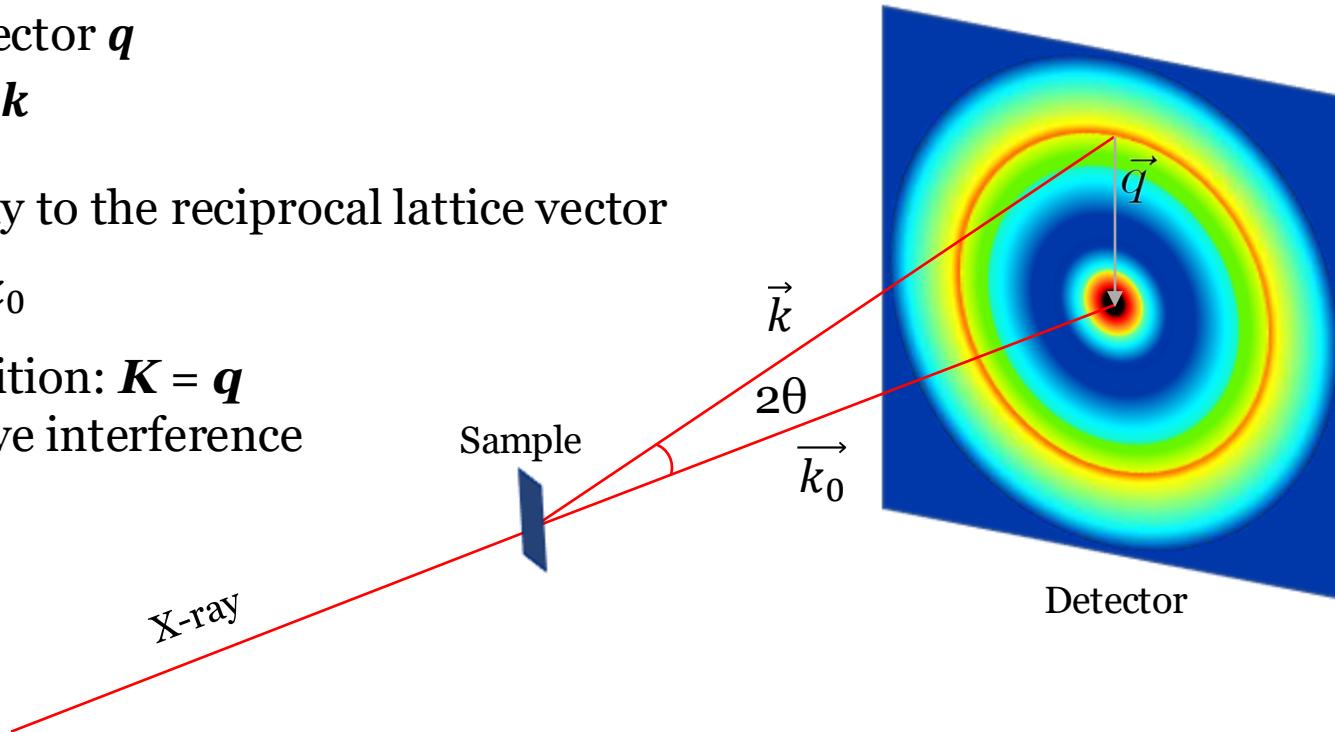


Repetition: The reciprocal space lattice

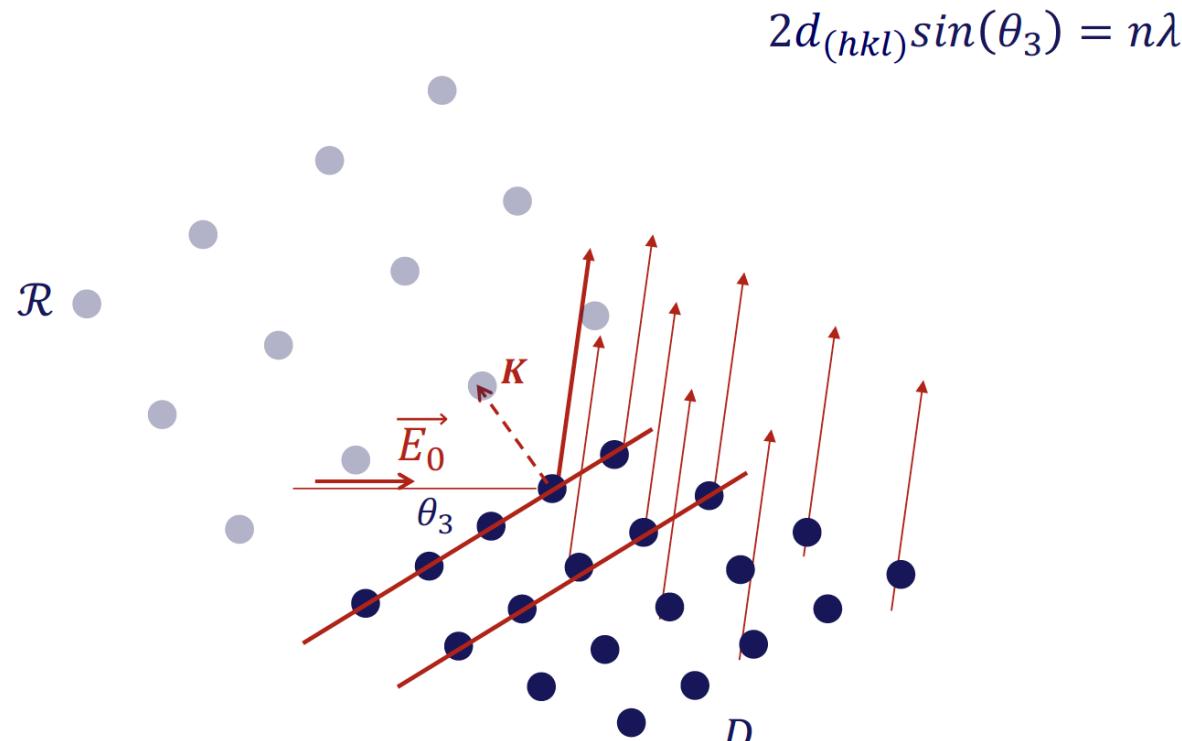

reciprocal lattice vector $\mathbf{K} = \mathbf{k} - \mathbf{k}_0$

Elastic scattering

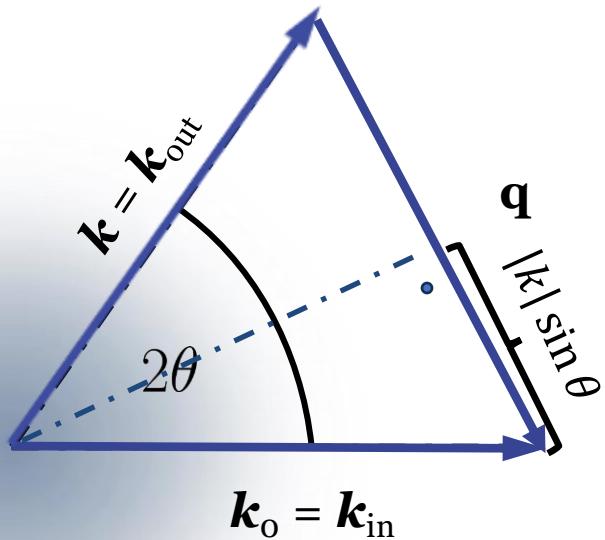

wave vector $\mathbf{k} = \frac{2\pi}{\lambda}$

elastic scattering: no loss in photon energy but direction of the photon can change with a scattering angle 2θ

$$|\mathbf{k}_{\text{in}}| = |\mathbf{k}_{\text{out}}|$$


scattering vector $\mathbf{q} = \mathbf{k}_0 - \mathbf{k}$

$$q = 2|k| \sin \theta = \frac{4\pi \sin \theta}{\lambda}$$

Scattering/Diffraction

scattering vector \mathbf{q}

$$\mathbf{q} = \mathbf{k}_0 - \mathbf{k}$$

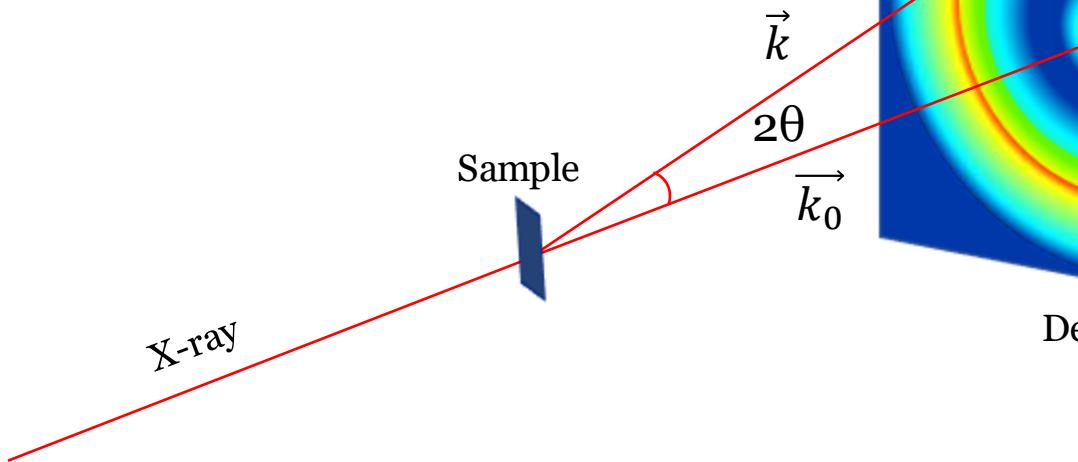

X-ray energy mostly given in keV

Electronvolt = eV

Energy of an electron after being accelerated from rest in a potential of 1 V

$$1 \text{ eV} = 1.6022 \times 10^{-19} \text{ J}$$

$$|\vec{q}| = q = \frac{4\pi \sin(\theta)}{\lambda}$$

light $\lambda = 400$ to 600 nm
X-ray tube $\lambda = 1$ to 2 Å



Cu K α = 1.5406 Å
synchrotron $\lambda = 0.1$ to 5 Å
thermal neutrons $\lambda = 1$ to 10 Å
electrons $\lambda = 0.025$ Å

$$E = hc / \lambda$$

h is Planck's constant (6.6261×10^{-34} Js)
 c is the speed of light (2.9979×10^8 m/s).

$$\lambda [\text{\AA}] = 12.3984/E [\text{keV}]$$

Bragg law

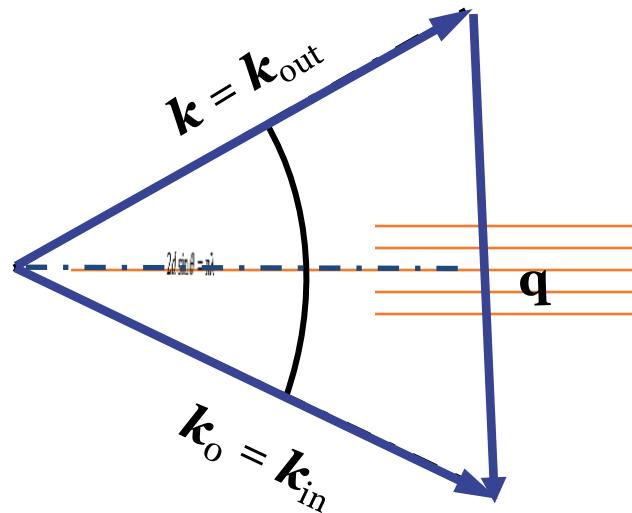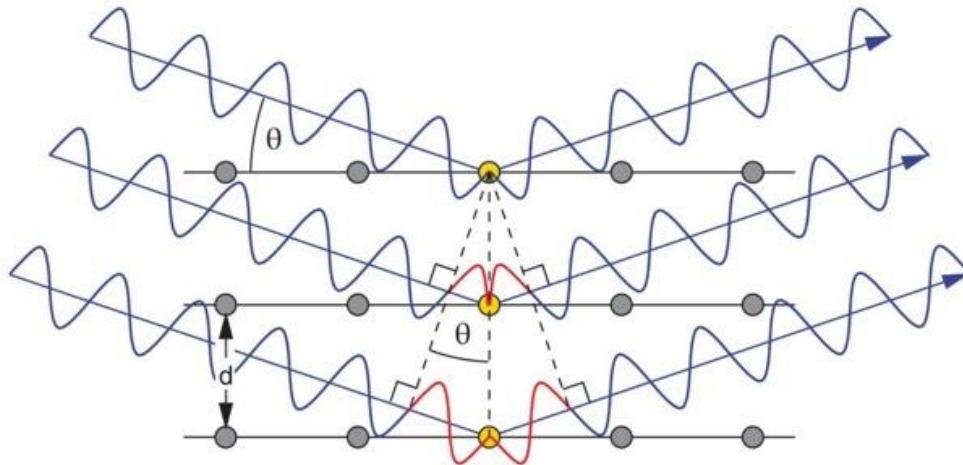

The scattering vector \mathbf{q} always lies perpendicular to the scattering planes if the Bragg condition is fulfilled

the angle subtended by $\mathbf{k}_{\text{in}} = 2\pi/\lambda$ (or \mathbf{k}_{out}) and the scattering planes is θ .

The scattering angle is 2θ


Bragg law: $2d \sin \theta = n\lambda$

$$|\mathbf{q}| = q = \frac{4\pi \sin(\theta)}{\lambda}$$

$$d = n \frac{2\pi}{q}$$

independent of wave length
(experimental condition)

Bragg condition and the Ewald sphere

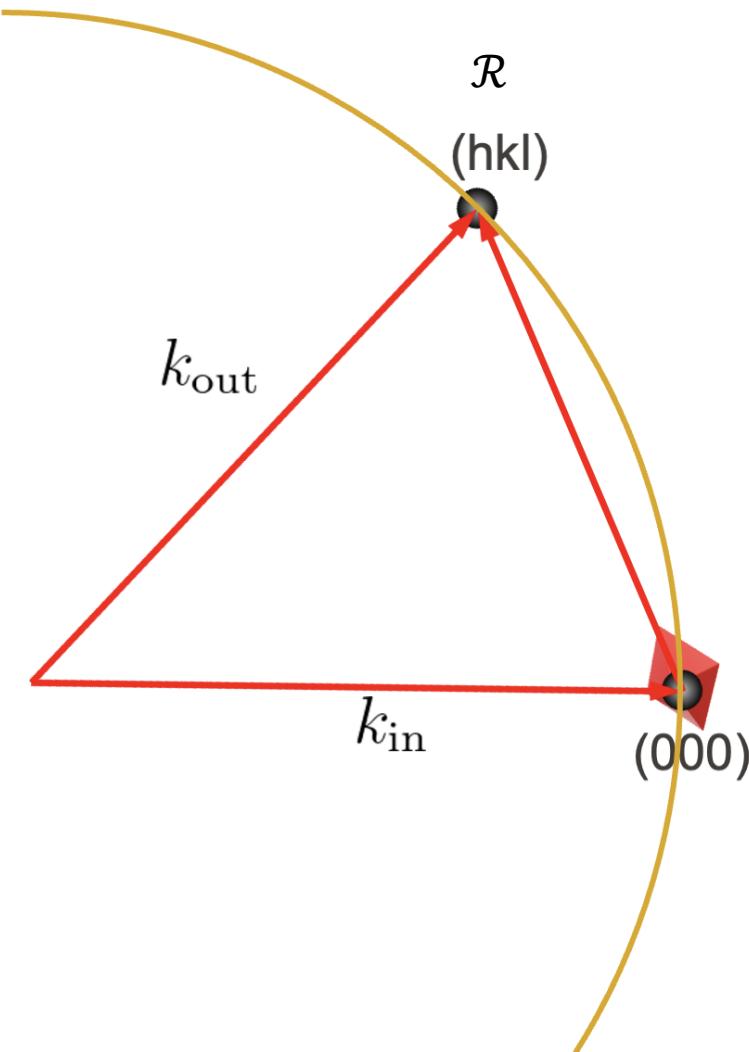

elastic scattering: $|k_{in}| = |k_{out}| = 2\pi/\lambda$

To see a diffraction peak @ (hkl) :

the Bragg points (000) , which is at the position of the direct incoming beam

and the Bragg point (hkl) from the reciprocal space lattice

must lie on a sphere of radius equal $|k|$ (the wave vector of the experiment) in reciprocal space \mathcal{R} , the so called Ewald sphere

Join at menti.com | use code 3848 6882

Radius of Ewald sphere: X-rays vs. electrons?

Which radiation?


visible light will not be a good probe since the wavelength is 400nm-700nm, which is much bigger than the distance between the atoms, typically of the order of a few 10^{-10} m. For instance,

- the lattice parameter of the element Ni is $3.6 \cdot 10^{-10}$ m,
- the size of an atom is about $1.4 \cdot 10^{-10}$ m.

	Energy	wavelength
Neutrons	1 – 5 meV (cold)	9 - 4 Å
	25 – 50 meV (thermal)	1.8 – 1.3 Å
Xrays	100keV	0.12 Å (hard Xrays)
	40 keV	0.31 Å
	5 keV	2.48 Å (soft Xrays)
Electrons	200 keV	0.025 Å

The Ewald sphere

Bragg law defines on a purely geometrical basis for which angles constructive interference **can** occur

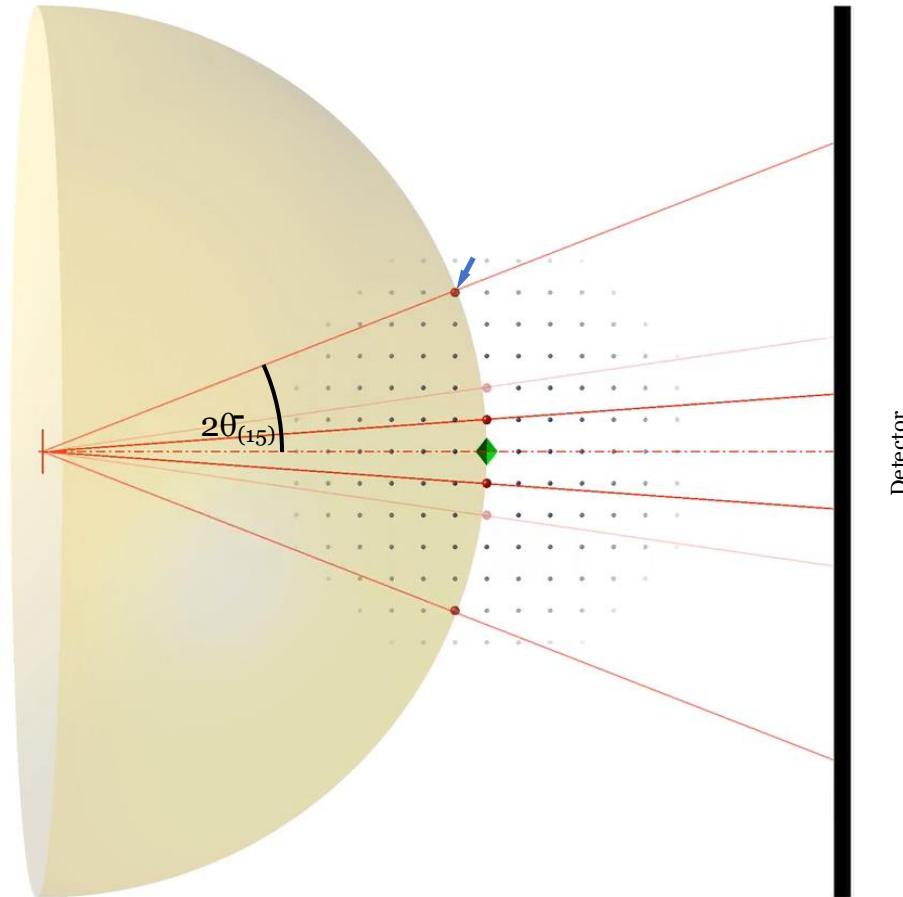


Philip Willmott: Synchrotron and X-ray Free Electron Laser (Part 2)

Sample types

single
crystal




$$2d_{(hkl)} \sin(\theta_3) = n\lambda$$

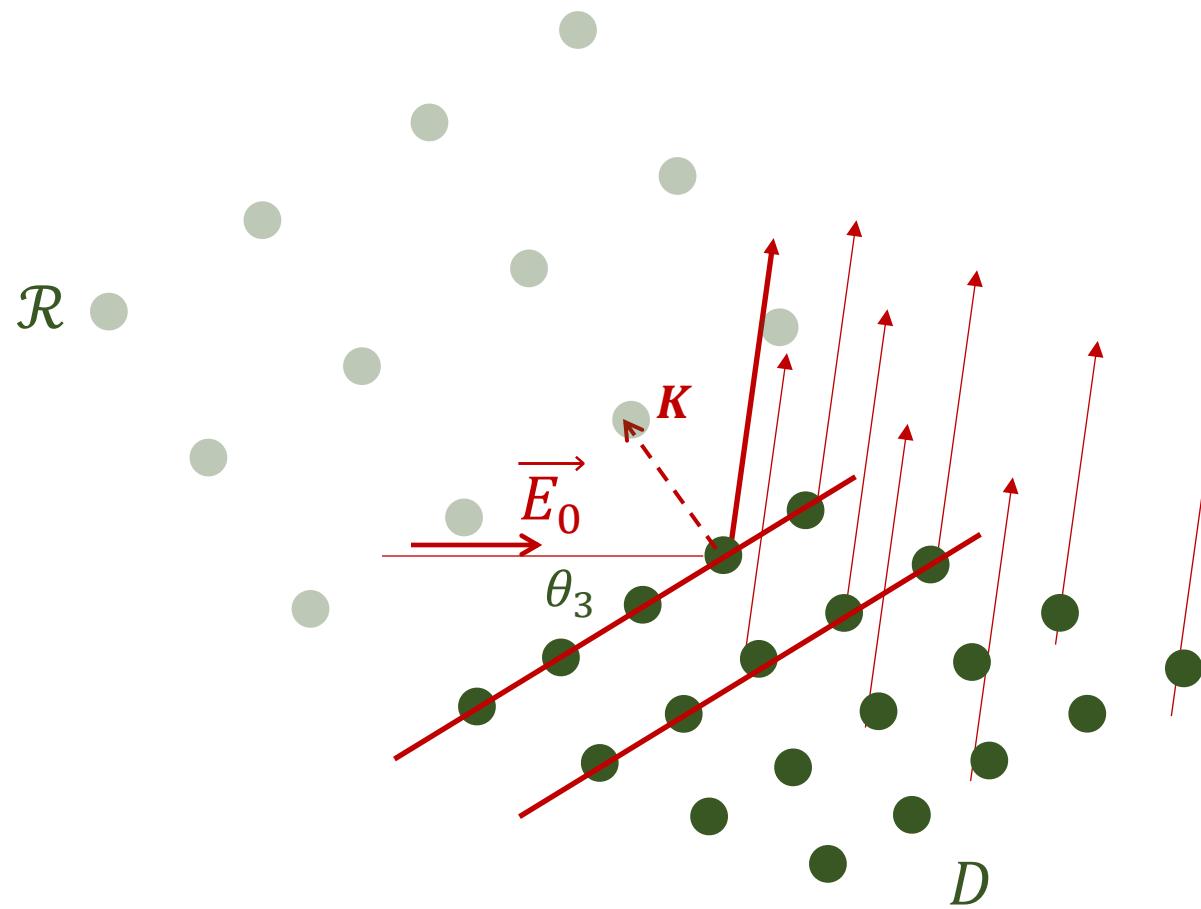

Single crystal diffraction – rotation method



- monochromatic radiation is used
- By rotating the crystal around an axis perpendicular to the incident beam (ϕ), diffraction maxima pass through the surface of the Ewald sphere and are registered on a 2D x-ray detector

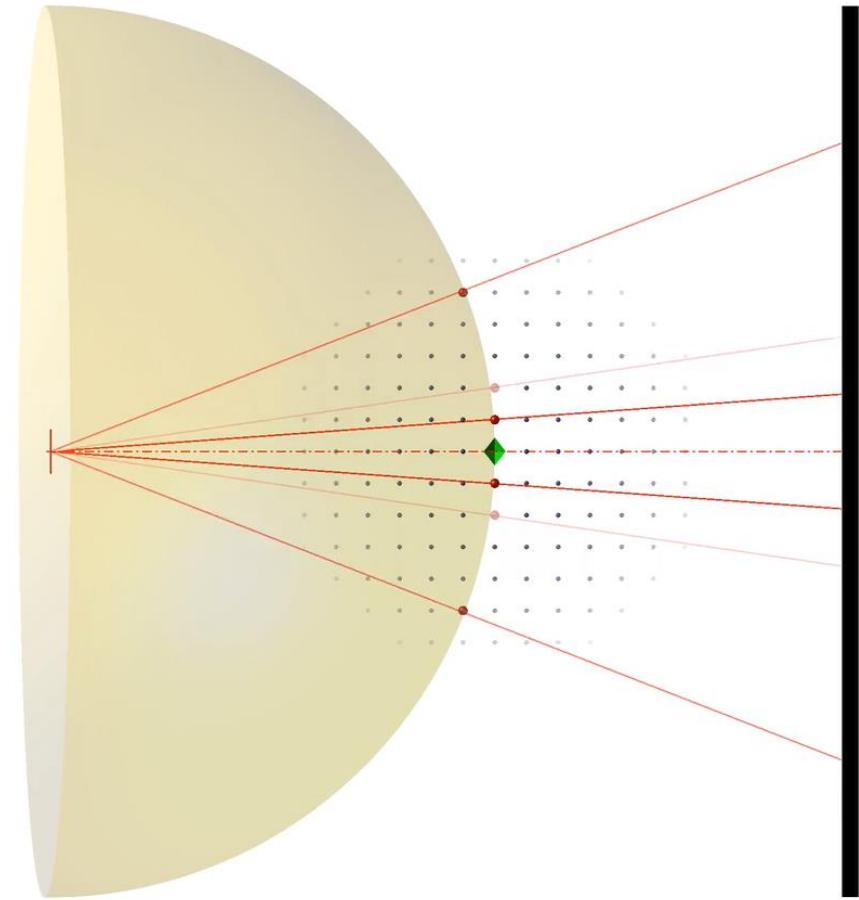

Application: protein crystallography

study the three-dimensional structure of biological macromolecules.

Data collection: wave length = 0.097nm, Canadian Light Source - 1 second per frame, total of ~360 frames, step size 0.5 degrees

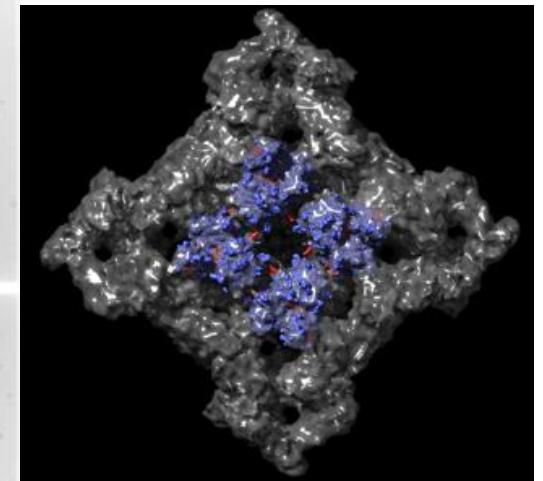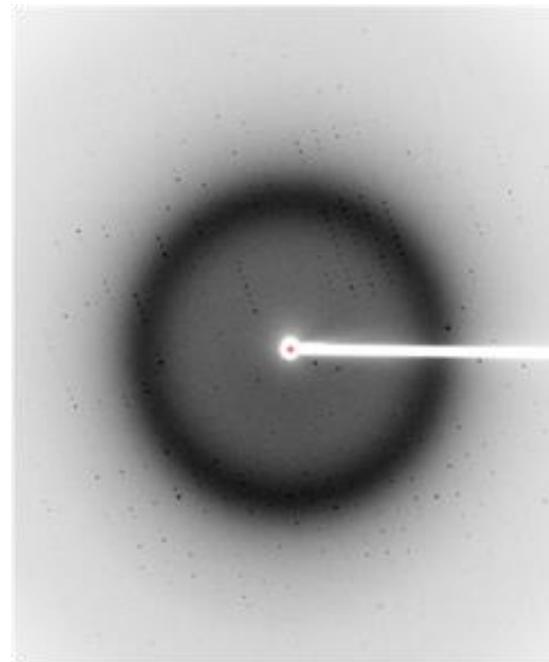


Courtesy: F. Van Petegem, UBC, Canada

For structure determination from single crystal diffraction one needs to retrieve...
in order to solve this problem, the space group will restrict the model **fewer atoms** because symmetry will automatically place equivalent atoms.
→ Refine the structure more efficiently using fewer parameters.

to reach higher resolution in the structure determination one needs....

Single crystal diffraction – Laue diffraction

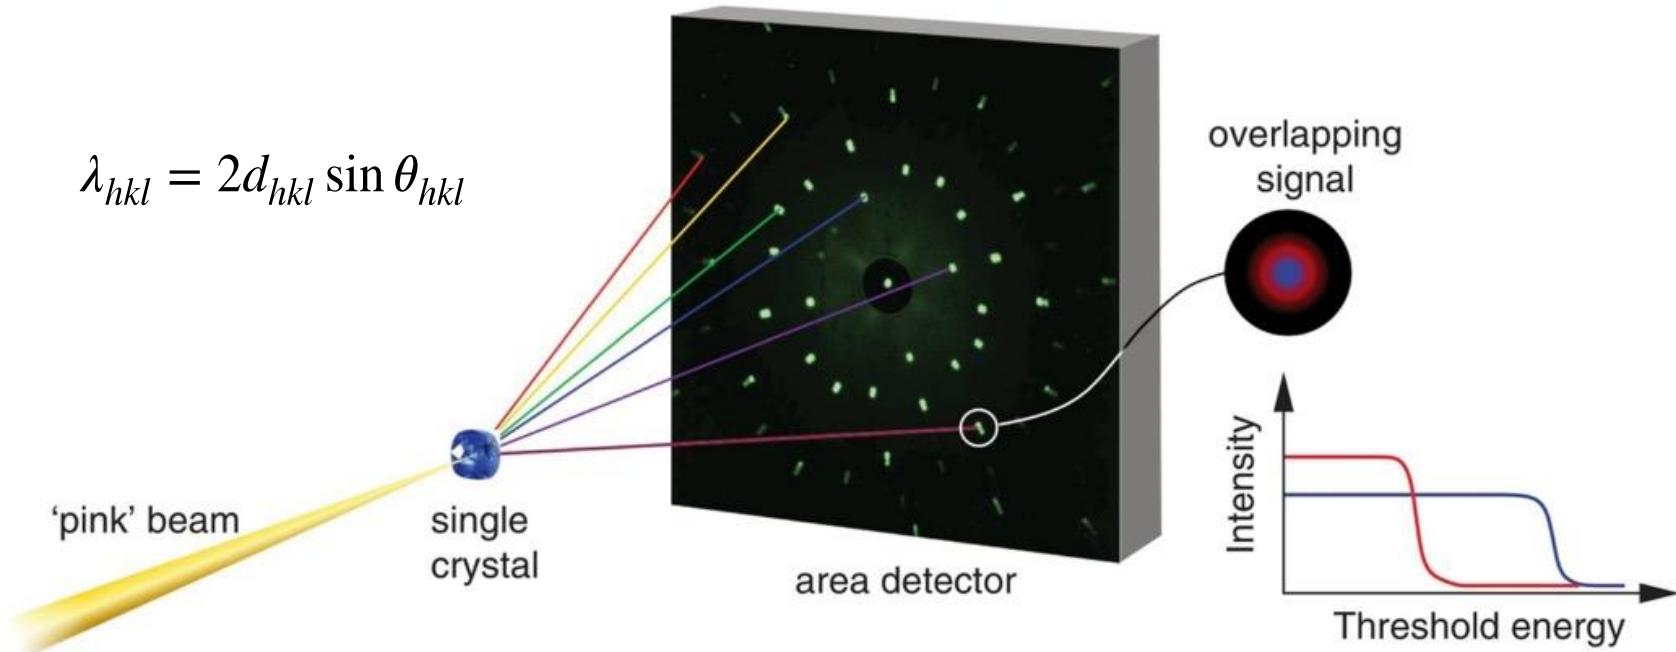

- Pink beam: many wavelengths
- Bragg equation fulfilled for multiple combinations of d and θ

Single crystal diffraction – Laue diffraction

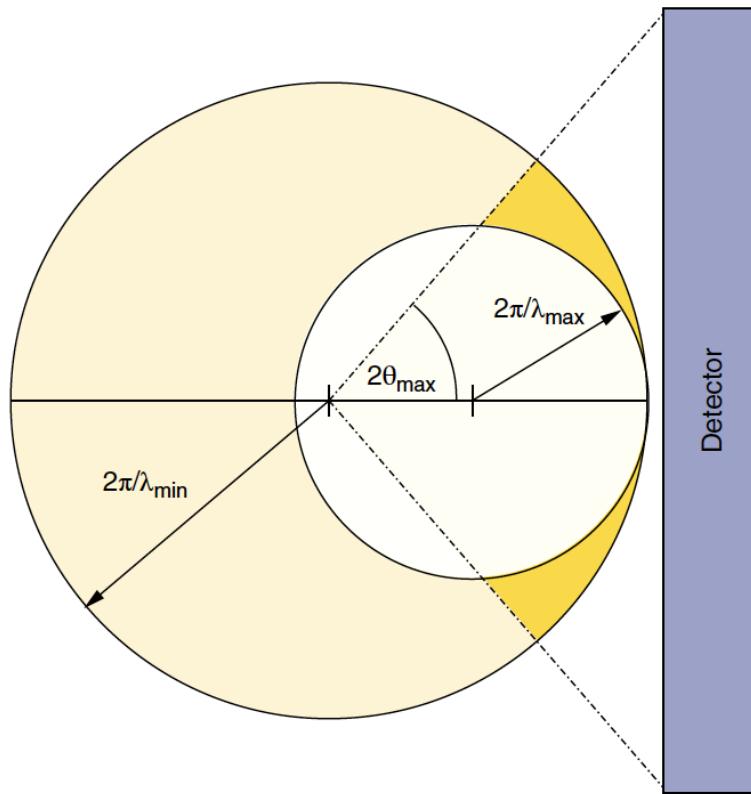



Figure 6.31 The volume of reciprocal space that can be simultaneously accessed in Laue diffraction, shown here in bright yellow, depends on the range of photon energies of the polychromatic beam and the maximum angle that can be subtended by the area detector.

Sample types

single
crystal




twinned
crystal






crystal with
mosaic spread



textured
sample

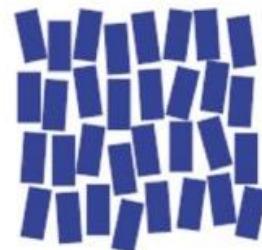

powder
sample

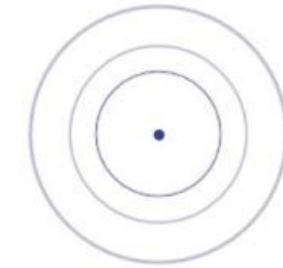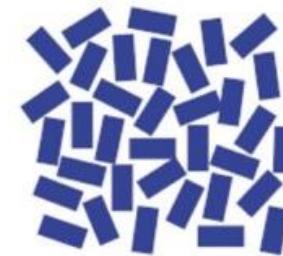

Material structure?

- Solid materials: Structures at different length scales


Example: metal




Part of a turbine - Ni
(10 cm)




Grains
(mm)

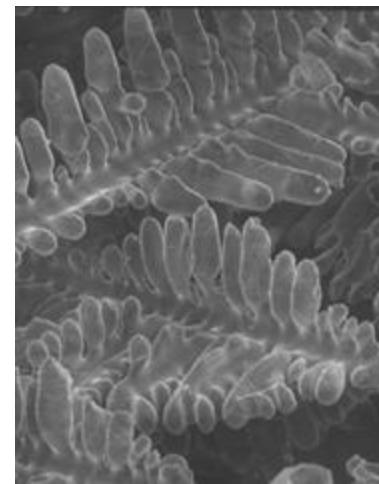

Dendrites
(10-100 mm)

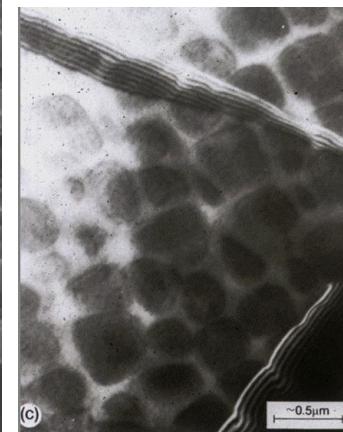

Alloys Ni_3Al
(10-100 nm)

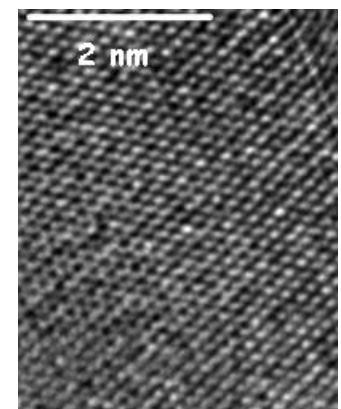

Atoms
(0.1 nm)


XRD

Imperfect microstructure


- large crystal with perfect atomic arrangement give rise to perfectly sharp peak (except of instrumental broadening)
- imperfections such as grain boundaries, defects at dislocations, stacking faults, stresses → peak broadening, as well as possibly peak position shifts

The hard sphere model

- 2D configuration:

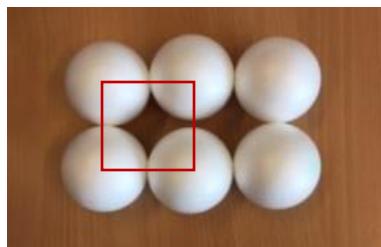



- 3D configuration:

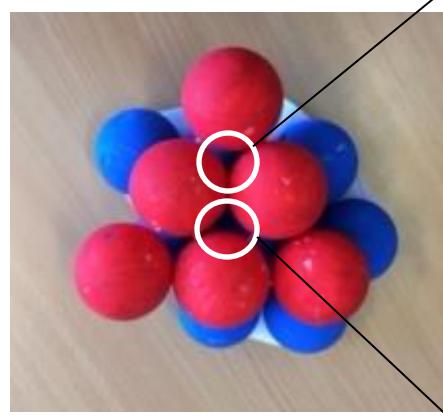


2 possibilities:




MSE-238

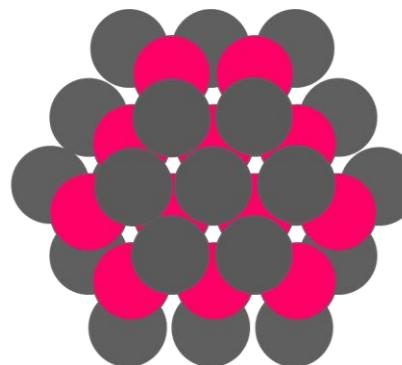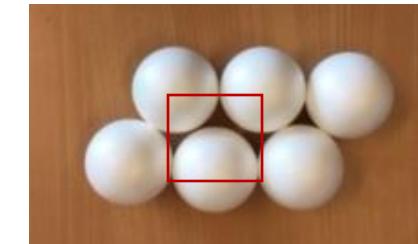


A-B-A

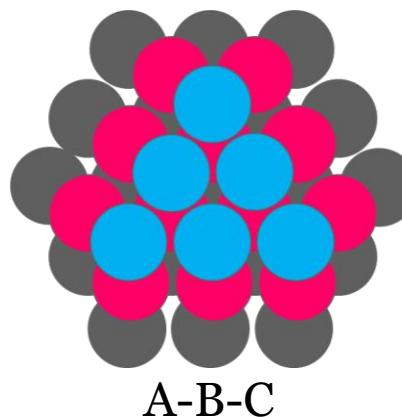

A-B-C

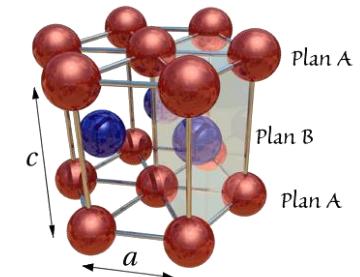


Hexagonal Compact

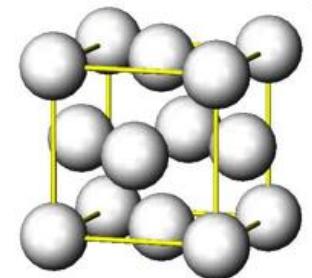


Face-centered Cubic
(= cubic-closed packed)

23

Single crystals: defects!

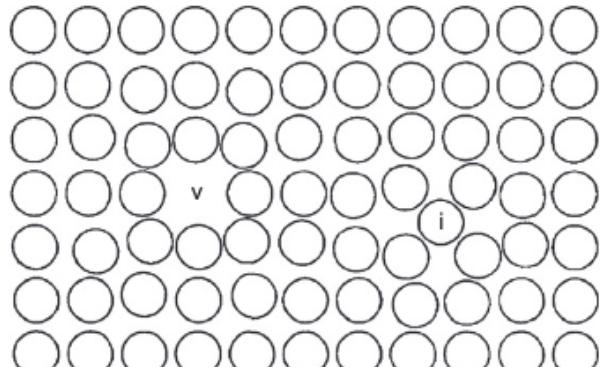

point defects in a simple cubic crystal

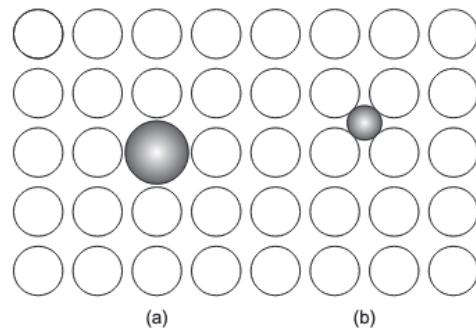



impurities

Hull, D. & Bacon, D. J. Defects in Crystals. *Introd. to Dislocations* (2011)



XRD: Impurity and disorder

Consider crystal with original crystal atoms \bullet and impurity species \circ (or holes)



Impurity atoms at random lattice sites

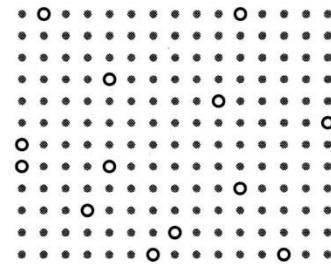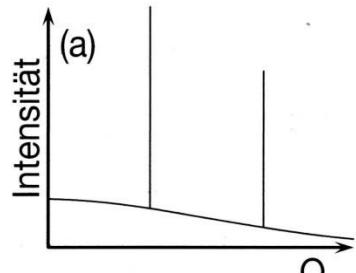



Impurity atoms at preferred lattice sites

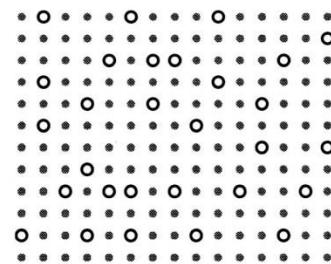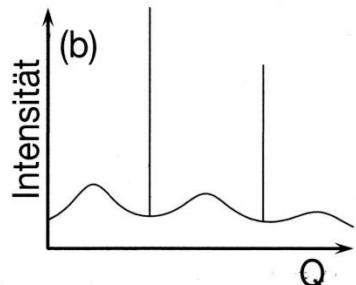



Impurity atoms at preferred lattice sites, long range order

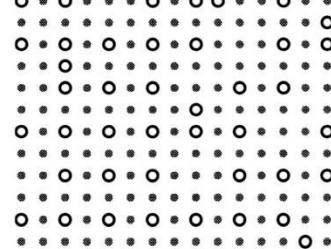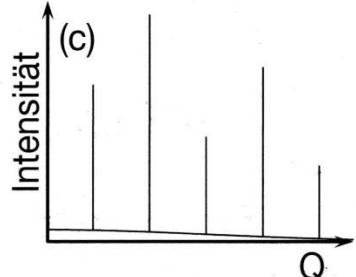



Impurity atoms tending to cluster

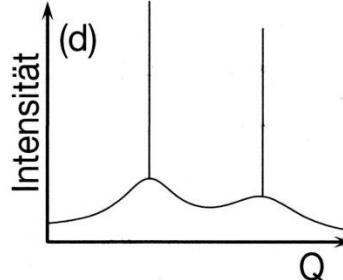


Impurity atoms residing in clusters

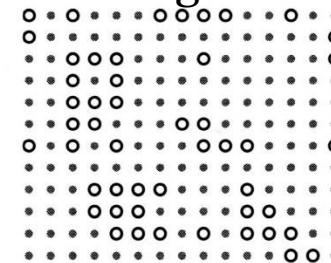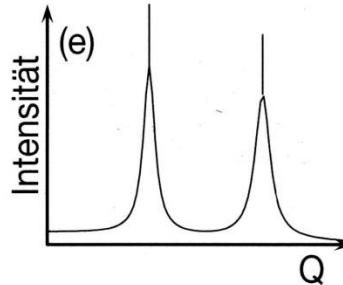



FCC structure as hard sphere model

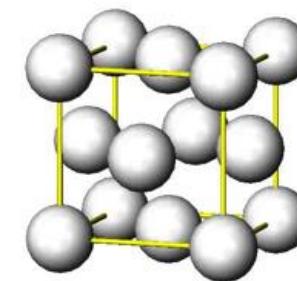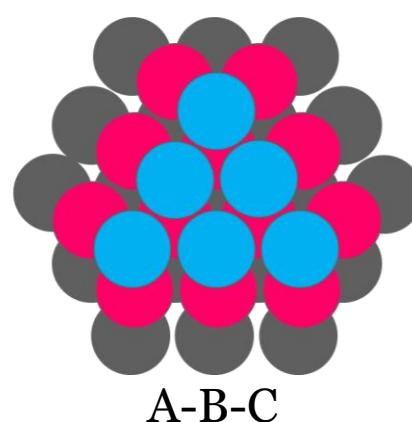

Face-centered Cubic
(= cubic-closed packed)

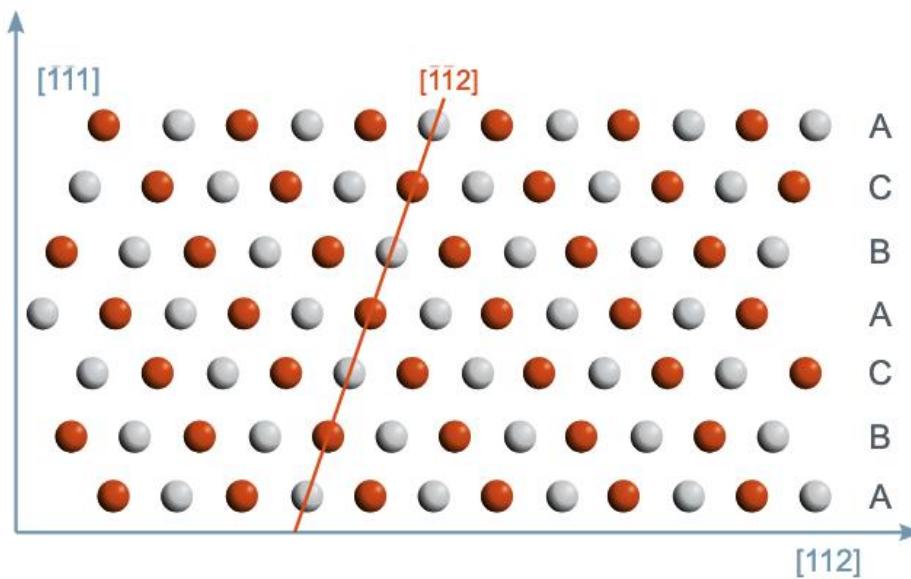


Single crystals: defects!

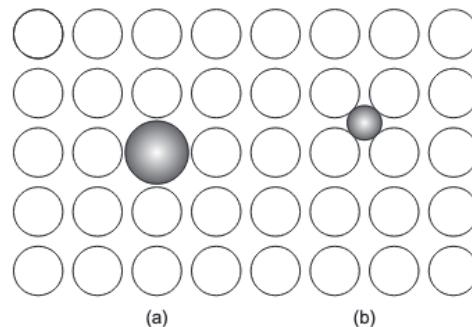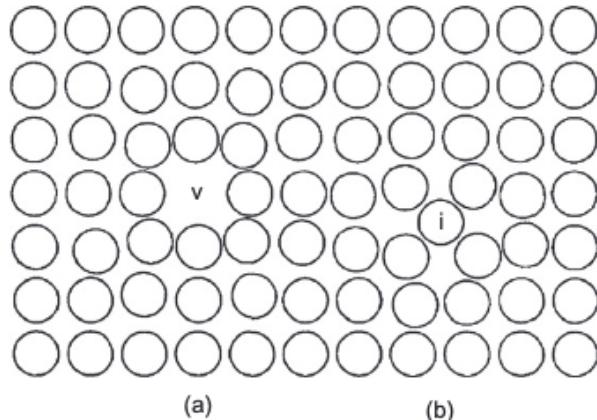

point defects in a simple cubic crystal


impurities

Hull, D. & Bacon, D. J. Defects in Crystals. *Introd. to Dislocations* (2011)

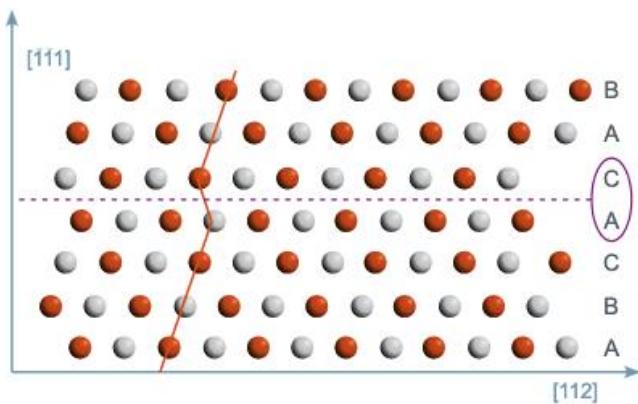

planar defect: stacking fault


<https://nte.mines-albi.fr/>

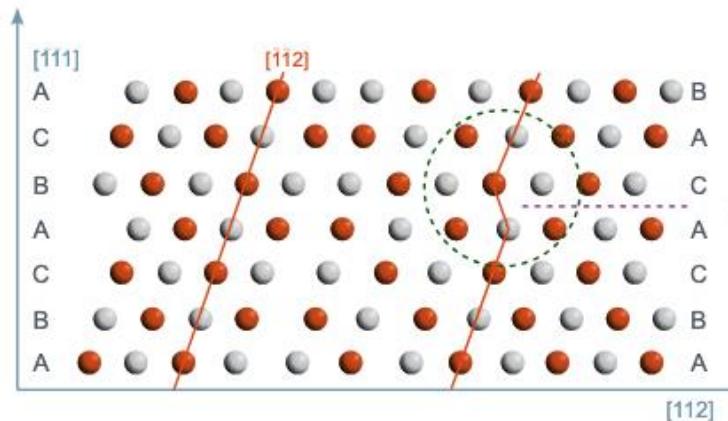

partial dislocation



Polycrystalline material grain boundaries

grain boundaries

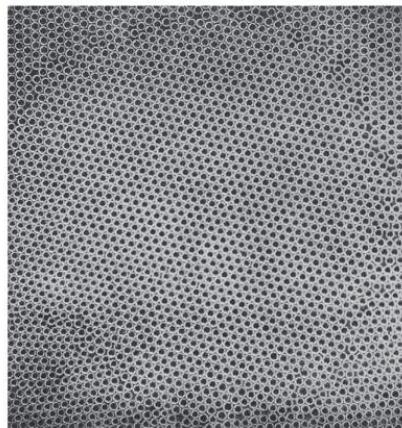

grain boundaries are both sources and traps for point defects and dislocations. Grain boundaries also play an important role in plastic deformation as they can induce dislocations under the action of a stress and constitute as well obstacles to the movement of dislocations.

Hull, D. & Bacon, D. J. Defects in Crystals. *Introd. to Dislocations* (2011)

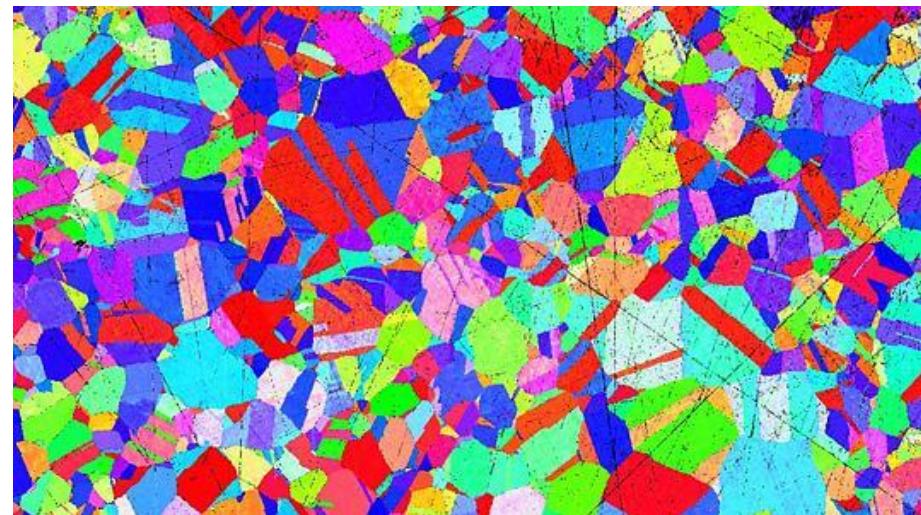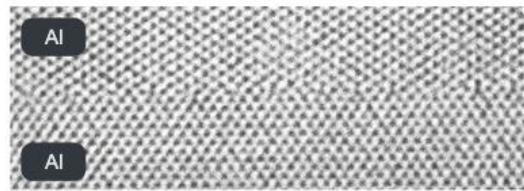



Optical micrographic views of a stainless steel showing grains and grain boundaries constituting (left) and grain boundaries (right) viewed using a TEM (interface between aluminium and -aluminium at top; and aluminium and-germanium at bottom).

<https://nte.mines-albi.fr/>


electron back scatter diffraction (EBSD) shows different orientations of grains

Twins

a twin refers to a crystal that is composed of two or more domains (individual crystal parts) that are **related by a specific symmetry operation**, but not part of the crystal's internal symmetry (space group). These domains **share some lattice points**.

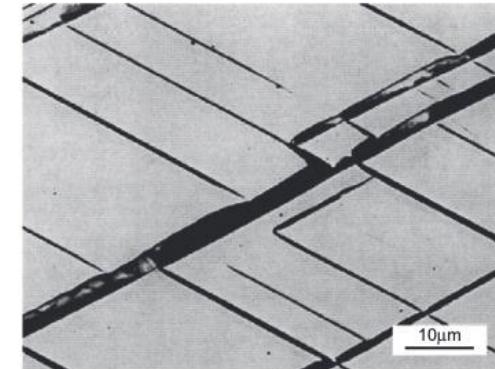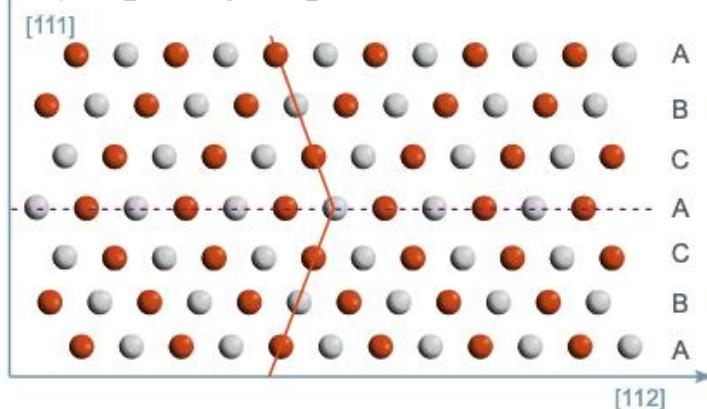

deformation twins in silicon iron

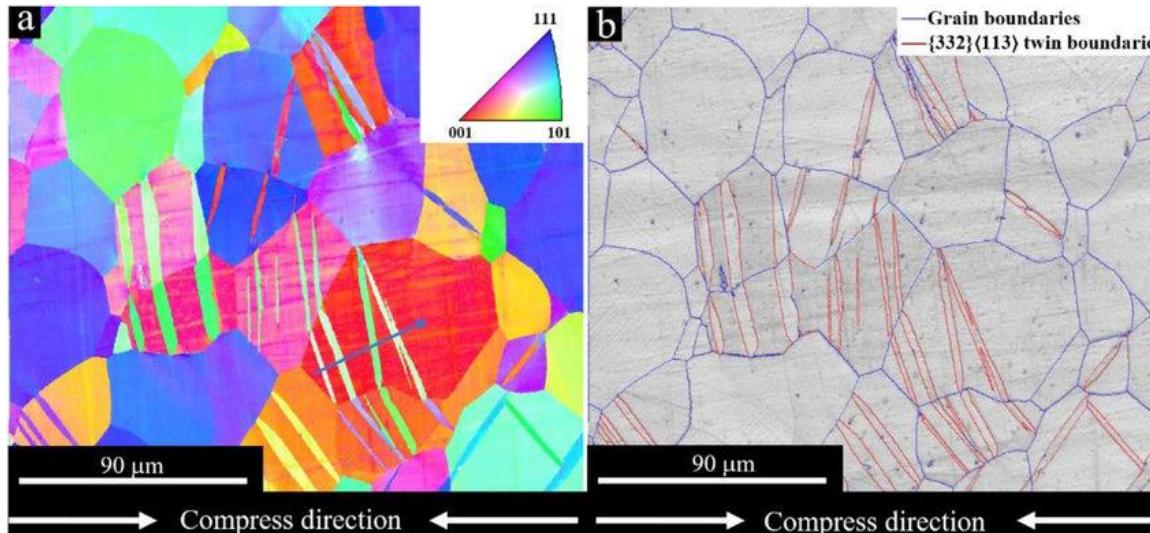


Yang et al. J. of
Materials Science &
Technology 73 (2021)
52-60

Sample types

single
crystal




twinned
crystal



crystal with
mosaic spread




textured
sample

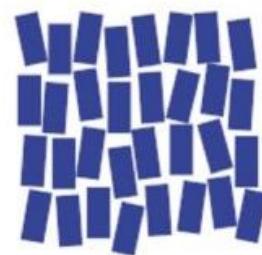

Textured sample and pole figure

Ti-Ni-Zr alloy thin films
(interesting for hydrogen storage)

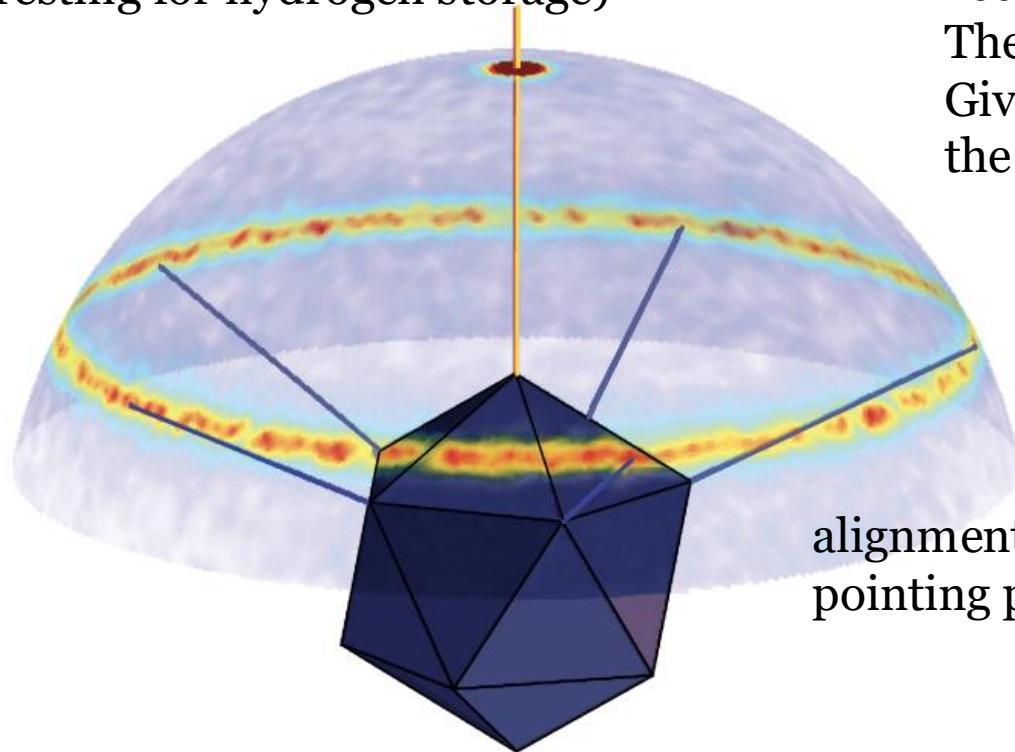

Given a specific set of reciprocal lattice vectors, $\{hkl\}$
The pole figure $P_{hkl}(q)$
Gives the probability of finding that plane in the direction, q

alignment of one of the symmetry axis pointing perpendicular out of the thin film

illustrated here is the structure of a icosahedron which has a five-fold symmetry
→ is this a crystal system?

Symmetry operations in 2D

For discrete objects, rotational symmetries can only be discrete: $\frac{2\pi}{n}$

and they rotational symmetry must be compatible with a translational symmetry!

$n=1 \rightarrow$ 1-fold, no symmetry


$n=2 \rightarrow$ 2-fold, 180° rotation

$n=3 \rightarrow$ 3 fold, 120° rotation


$n=4 \rightarrow$ 4 fold, 90° rotation

$n=6 \rightarrow$ 6 fold, 60° rotation

what about 5-fold?

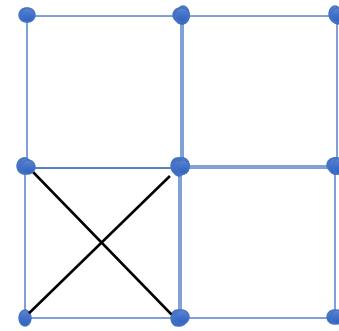


4-fold

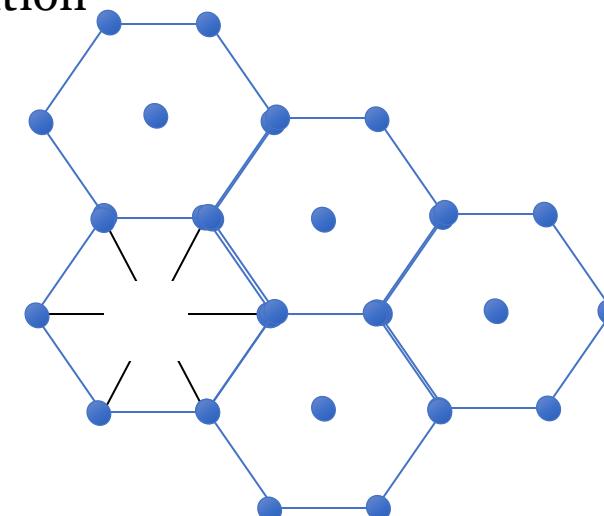

6-fold


and mirror symmetry (m)

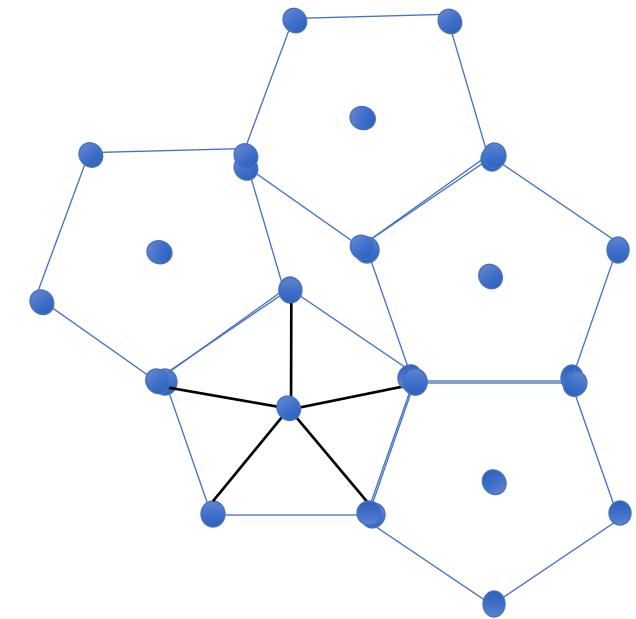

Patterns with 5-fold symmetry → Quasicrystals


A quasiperiodic crystal (quasicrystal) is a structure that is ordered but not periodic.

A quasi-crystalline pattern can continuously fill all available space, but it lacks translational symmetry

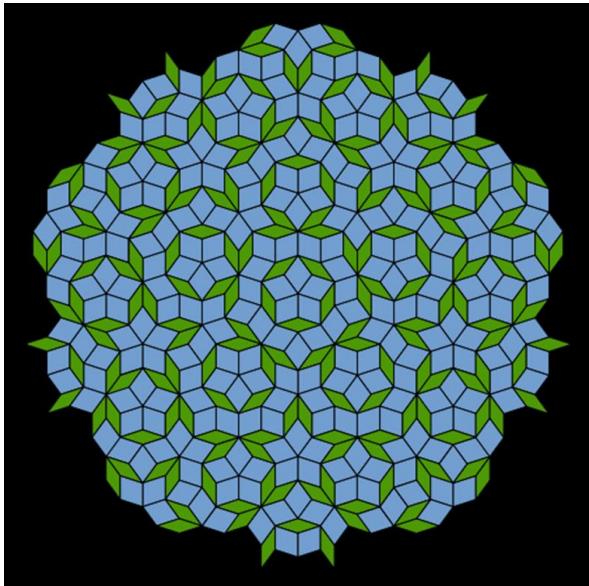


Penrose tiling gives a quasicrystal

http://en.wikipedia.org/wiki/Penrose_tiling

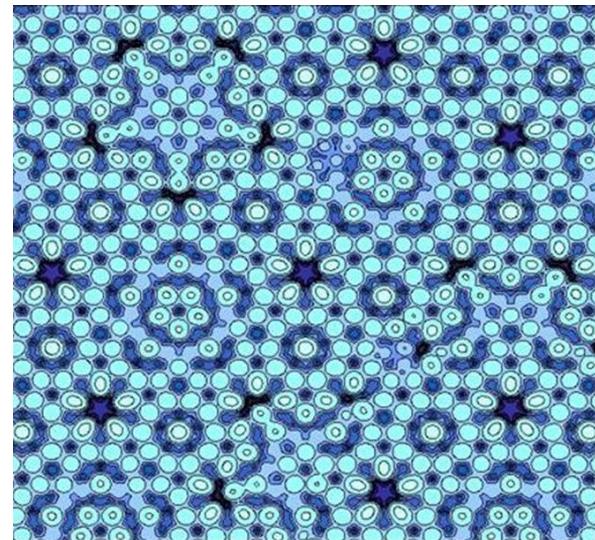


Atomic model of an aluminium-palladium-manganese (Al-Pd-Mn) quasicrystal surface.


Textured samples: orientation information

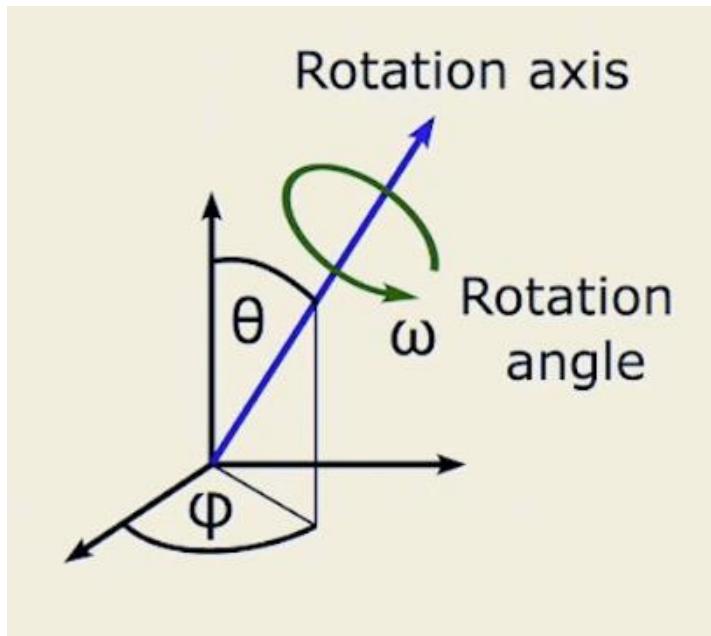


axis-angle representation of 3D orientation
one vector defining the axis, and an angle defining the rotation around it

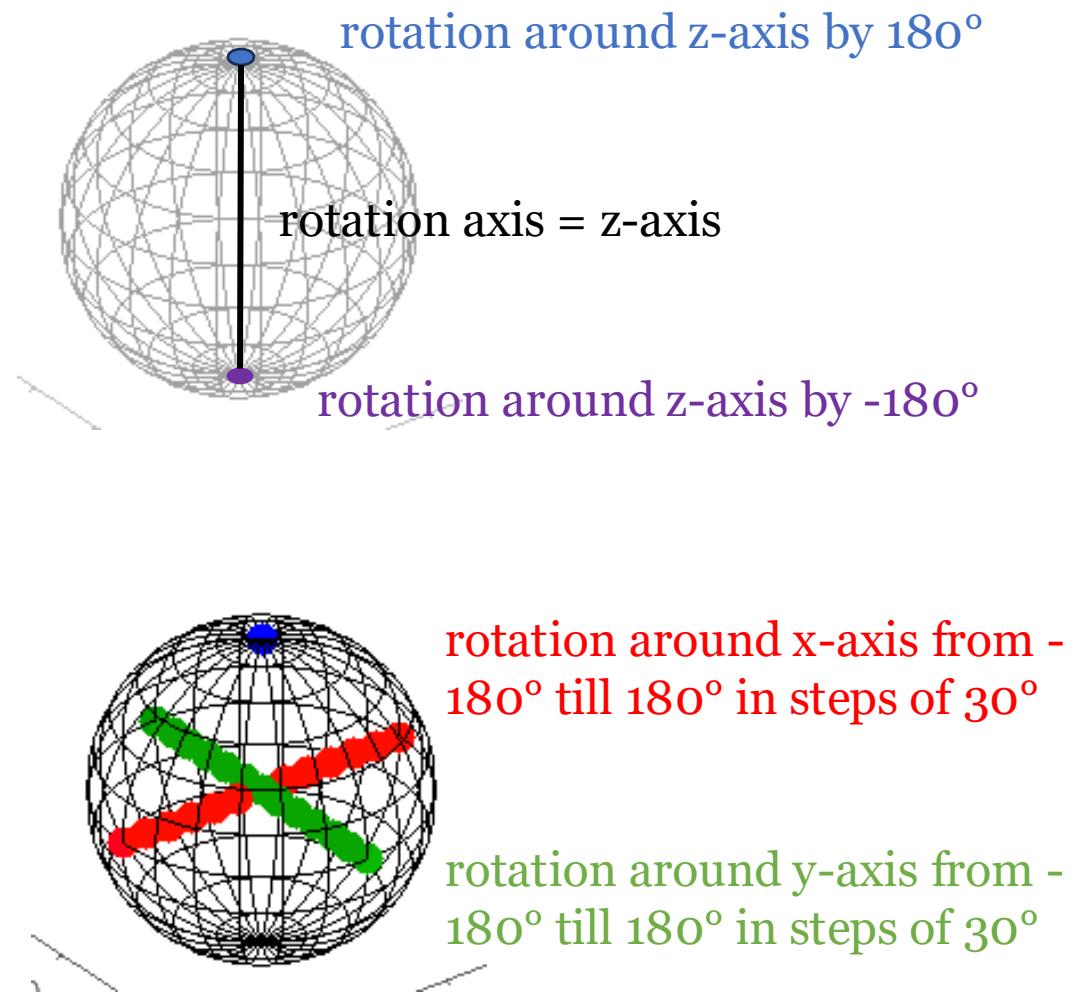

Textured samples: orientation information

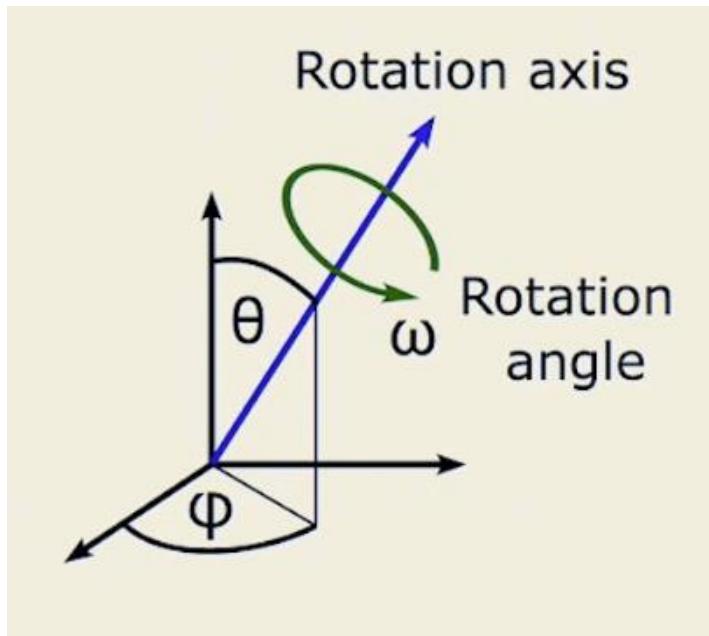

axis-angle representation of 3D orientation
one vector defining the axis, and an angle defining the rotation around it

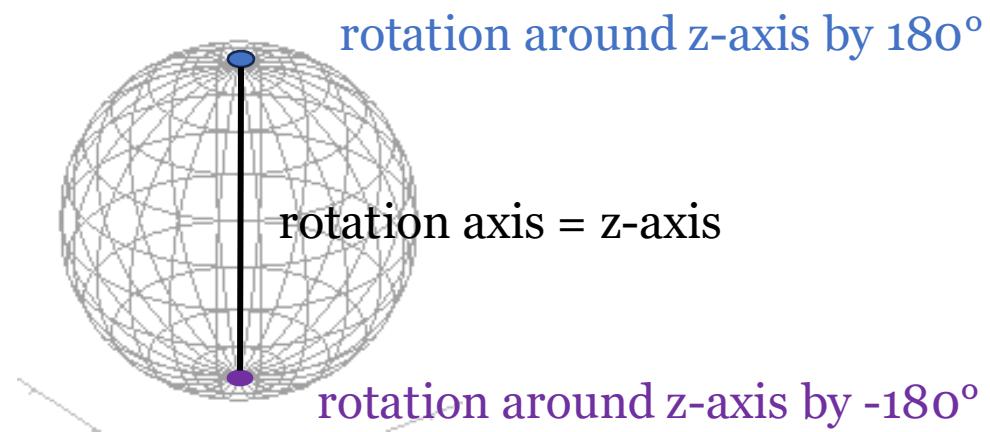

if there is a two-fold **symmetry** around that axis, rotation of 0° and 180° and -180° are equivalent!

what defines if certain orientations are equivalent?

crystal system

Cubic

$a = b = c$
 $\alpha = \beta = \gamma = 90^\circ$

Tetragonal

$a = b \neq c$
 $\alpha = \beta = \gamma = 90^\circ$

Orthorhombic

$a \neq b \neq c$
 $\alpha = \beta = \gamma = 90^\circ$

Trigonal or
rhombohedral

$a = b = c$
 $\alpha = \beta = \gamma \neq 90^\circ$

Hexagonal

$a = b \neq c$
 $\alpha = \beta = 90^\circ; \gamma = 120^\circ$

Monoclinic

$a \neq b \neq c$
 $\alpha = \gamma = 90^\circ \neq \beta$

Triclinic

$a \neq b \neq c$
 $\alpha \neq \beta \neq \gamma$


Bravais lattices



Simple
cubic



Face-centered
cubic




Body-centered
cubic




Simple
tetragonal




Body-centered
tetragonal




Simple
orthorhombic




Body-centered
orthorhombic




Base-centered
orthorhombic



Face-centered
orthorhombic



Rhombohedral




Hexagonal



Simple
Monoclinic



Base-centered
monoclinic



Triclinic

defining symmetry

4x 3-fold axis
3x 4-fold axis

4-fold axis

3x 2-fold axis












3-fold axis

6-fold axis

2-fold axis


1-fold axis

32 Point groups in 3D

Triclinic and Monoclinic	Orthorhombic	Tetragonal	Hexagonal		Cubic (Isometric)
 C_1 1		 C_4 4	 C_3 3	 C_6 6	 T 23
 C_1h 1		 C_{4h} 4/m	 S_6 3	 C_{6h} 6/m	 T_h m3
 C_2 2	 D_2 222	 D_4 422	 D_3 32	 D_6 622	 O 432
 C_s m	 C_{2v} 2mm	 C_{4v} 4mm	 C_{3v} 3m	 C_{6v} 6mm	 T_d $\bar{4}3m$
 C_{2h} 2/m	 D_{2h} mmm	 D_{4h} 4/mmm	 D_{3d} $\bar{3}m$	 D_{6h} 6/mmm	 O_h m $\bar{3}m$
		 S_4 $\bar{4}$		 C_{3h} 6	
		 D_{2d} 42m	MSE-238	 D_{3h} 6m2	


Point symmetry elements examples

orthorhombic

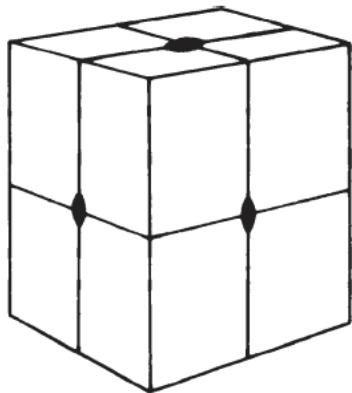

- 3 times 2-fold axis, perpendicular to the faces
- three mirror planes parallel to faces planes

cubic

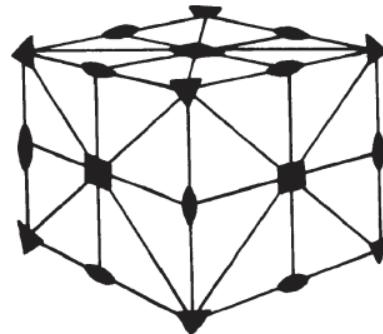


→ highest symmetry, makes it hard to see!

- 3 times 4-fold axis perpendicular to the faces
- 4 times 3-fold axis between opposite cube corners
- 6 times 2-fold axis between opposite center of edges
- 9 mirror planes
- 3 parallel to faces planes
- 6 parallel to the face diagonals plus center of inversion and rotointversions!


Orientation of a crystal and crystal symmetry

orthorhombic

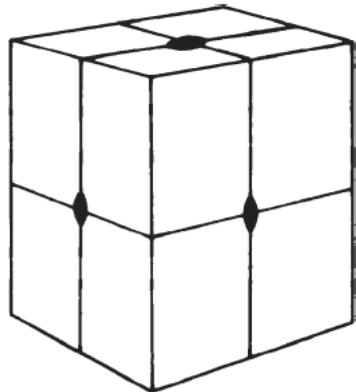


→ 3 times 2-fold axis,
perpendicular to the faces
222

→ three mirror planes
parallel to faces planes

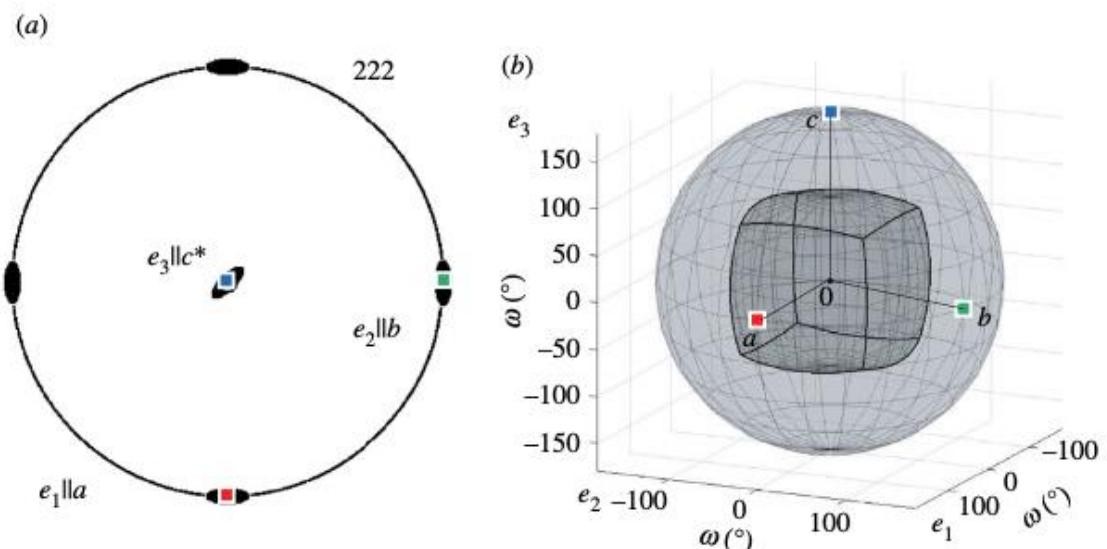


for plotting all possible orientation, only a subset of the sphere is needed → called the fundamental zone

Orientation of a crystal and crystal symmetry

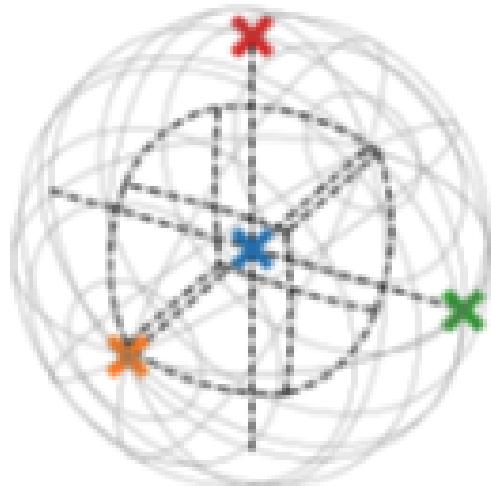


point group 222

crystal system

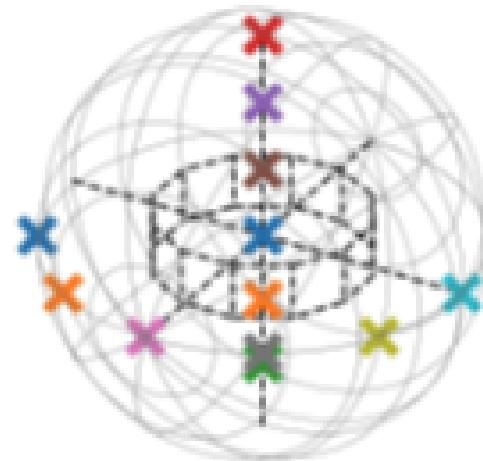

622

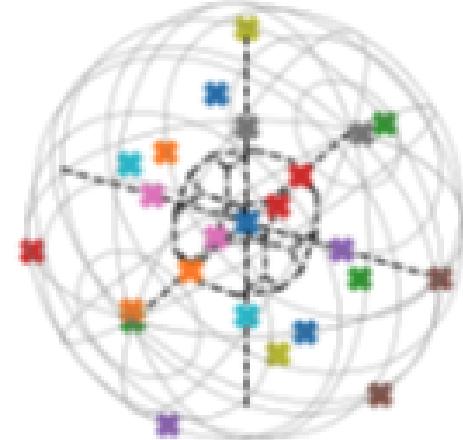

432

the more symmetry elements a point group has, the smaller is the fundamental zone since more and more orientation become equivalent


→ this also means for a full dataset in single crystal diffraction fewer orientations of a crystal need to be measured if there is a higher symmetry

Outer shape and symmetry: Biomineral


Roman snail shell




polycrystalline material

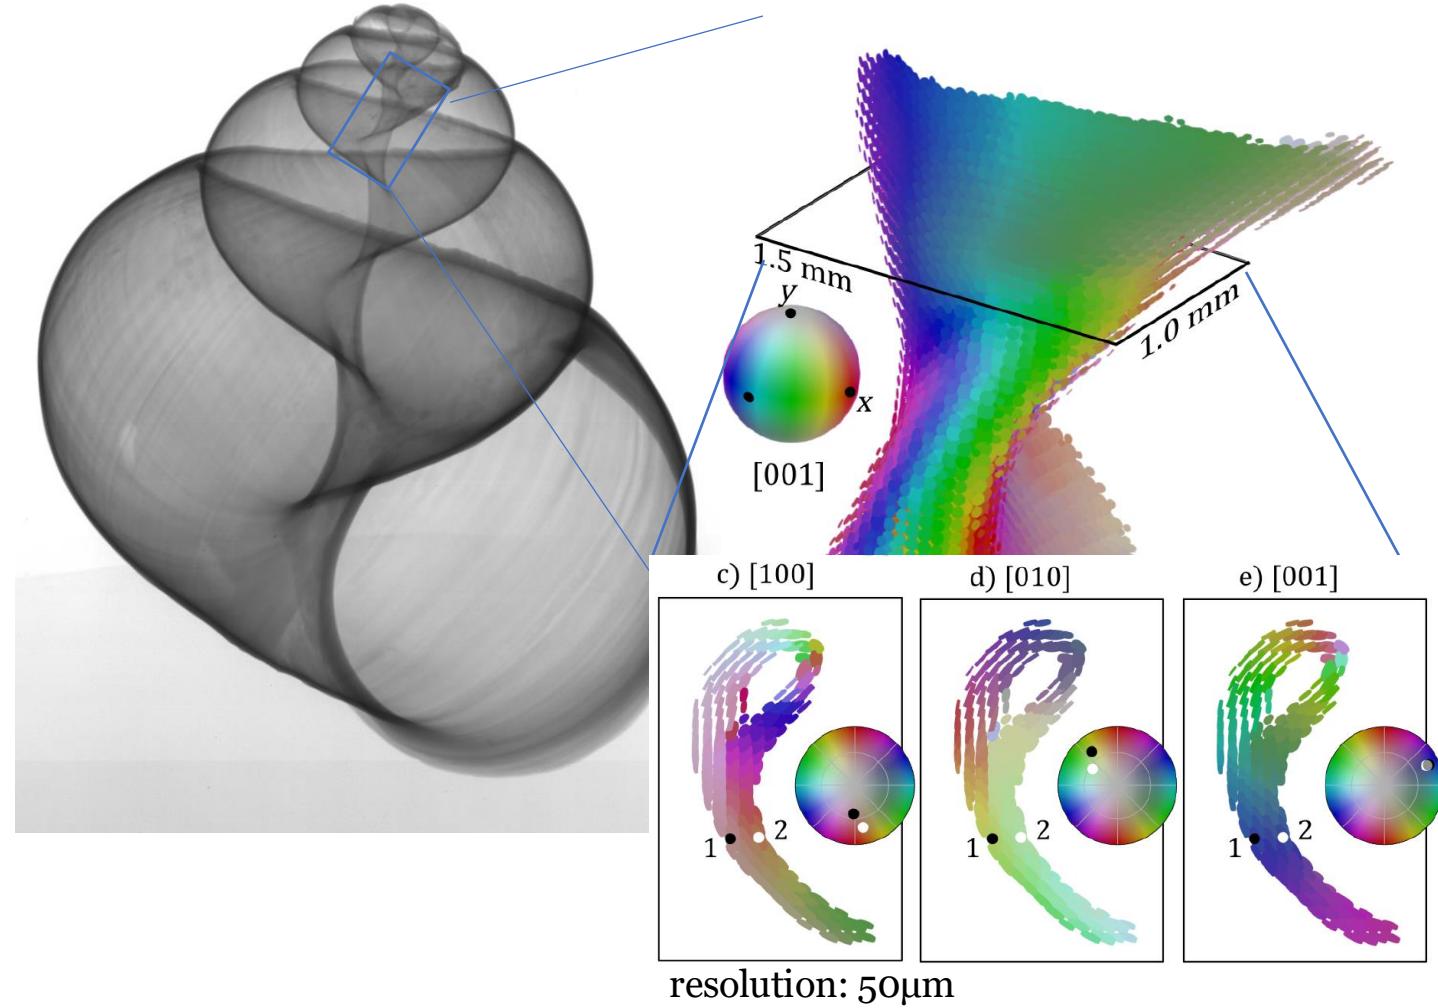

Roman snail shell: local texture as mosaic single crystal

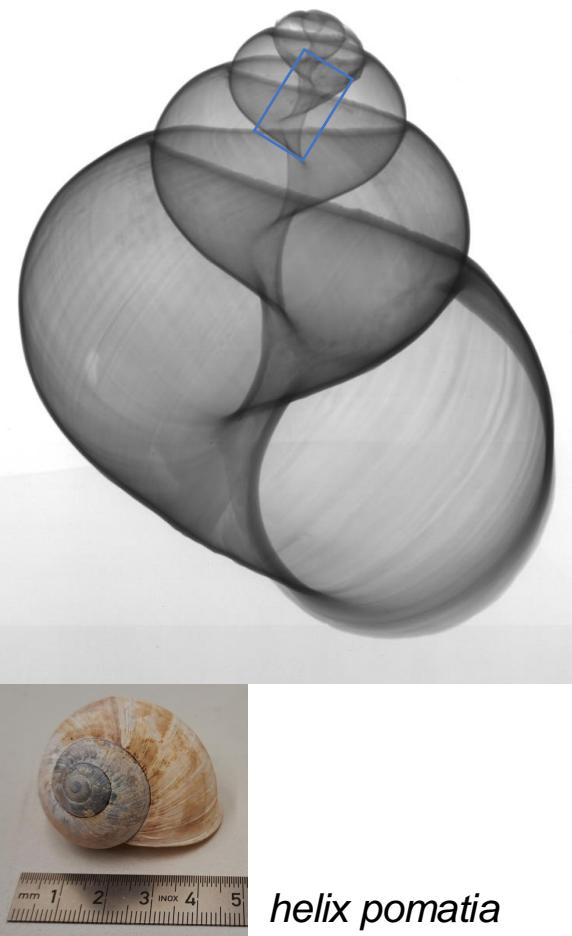

polycrystalline material

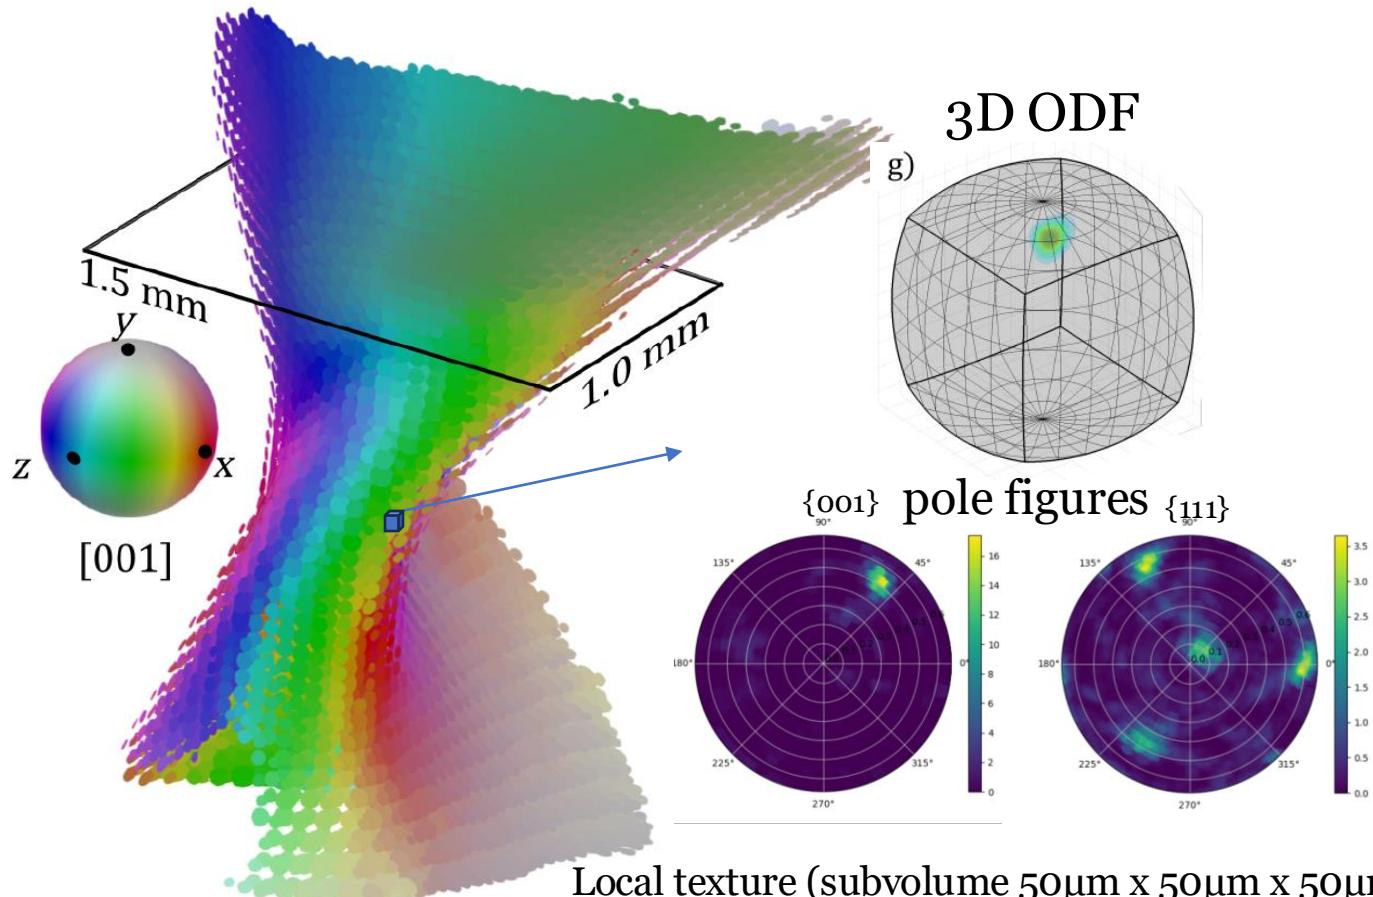

Local texture (subvolume $50\mu\text{m} \times 50\mu\text{m} \times 50\mu\text{m}$)
mosaic single-crystal like
with $\sim 10^\circ$ spread


M. Carlsen *et al.* Applied Crystallography 2025

Sample types

single
crystal




twinned
crystal



crystal with
mosaic spread





textured
sample

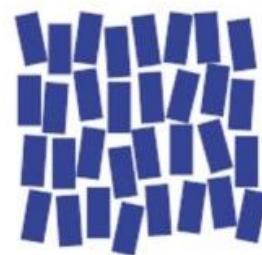

Fibre texture: drawn metal wire

drawn metal wire made of stainless steel

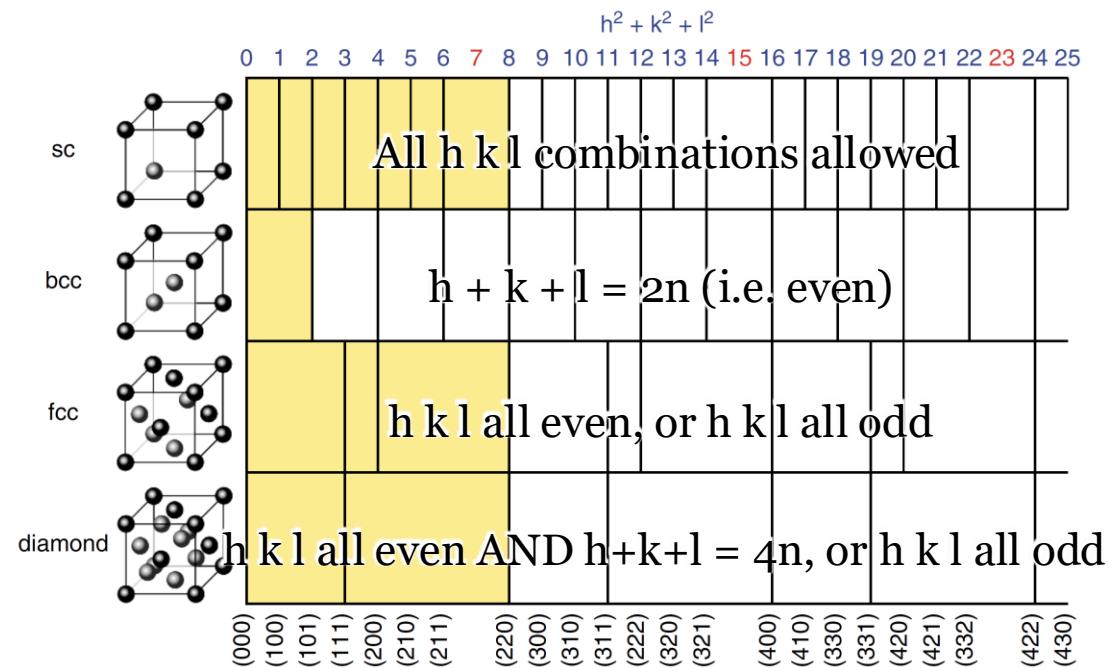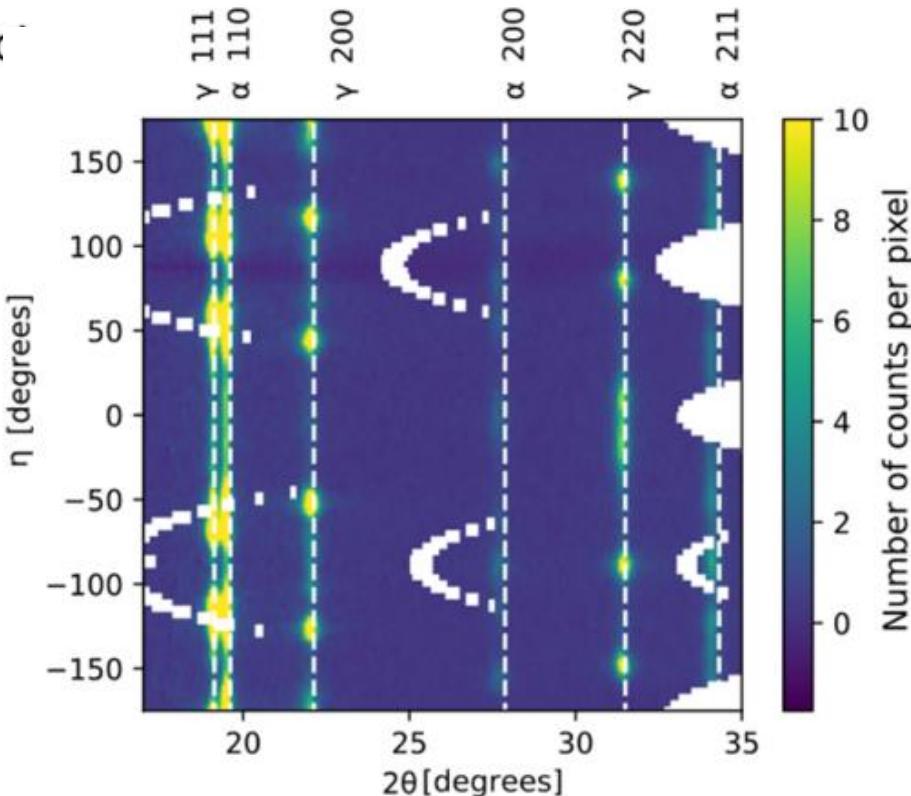



what is the crystal system of the α phase?
 what is the crystal system of the γ phase?

Carbon: 0.12% maximum
 Manganese: 2.00% maximum
 Phosphorus: 0.045% maximum
 Sulfur: 0.030% maximum
 Silicon: 1.00% maximum
 Chromium: 17.0–19.0%
 Nickel: 8.0–10.0%
 Nitrogen: 0.10% maximum
 Iron: Balance

Fibre texture: drawn metal wire

drawn metal wire made of stainless steel






there is 0.12% carbon inside that material, in which phase do you expect it to be?

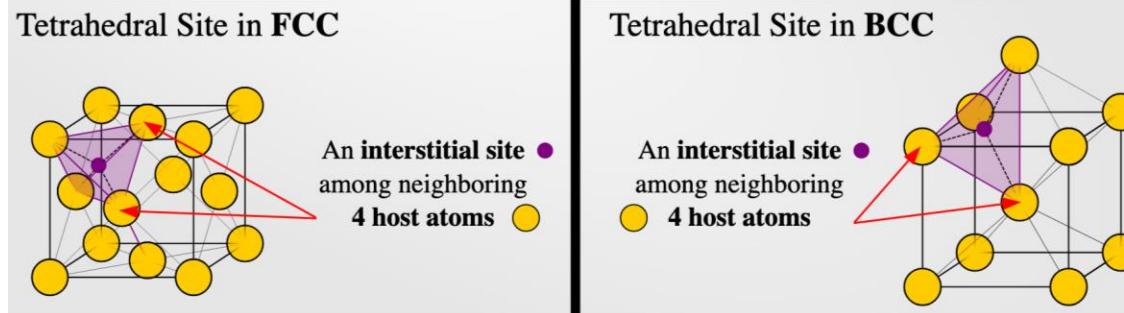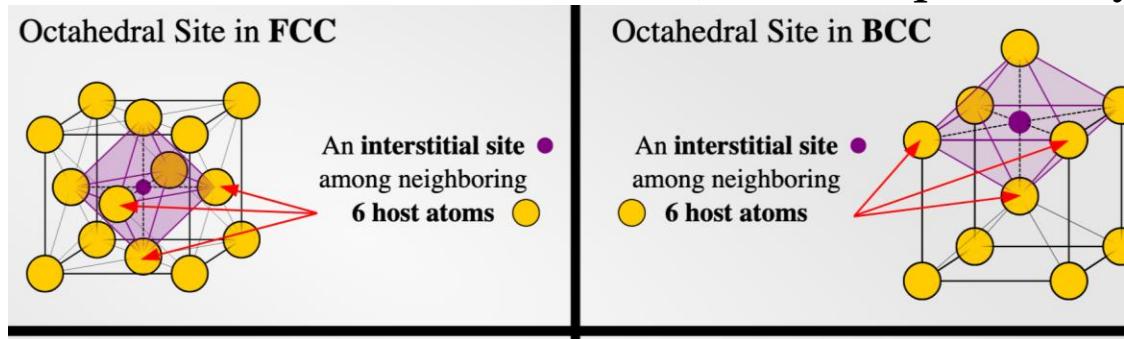

Crystal Structure	FCC	BCC
Number and Size of Octahedral Voids	4 voids, $r = 0.414 R$	6 voids, $r = 0.155 R$
Number and Size of Tetrahedral Voids	8 voids, $r = 0.225 R$	12 voids, $r = 0.291 R$


Carbon: 0.12% maximum
 Manganese: 2.00% maximum
 Phosphorus: 0.045% maximum
 Sulfur: 0.030% maximum
 Silicon: 1.00% maximum
 Chromium: 17.0–19.0%
 Nickel: 8.0–10.0%
 Nitrogen: 0.10% maximum
 Iron: Balance

Fibre texture: drawn metal wire

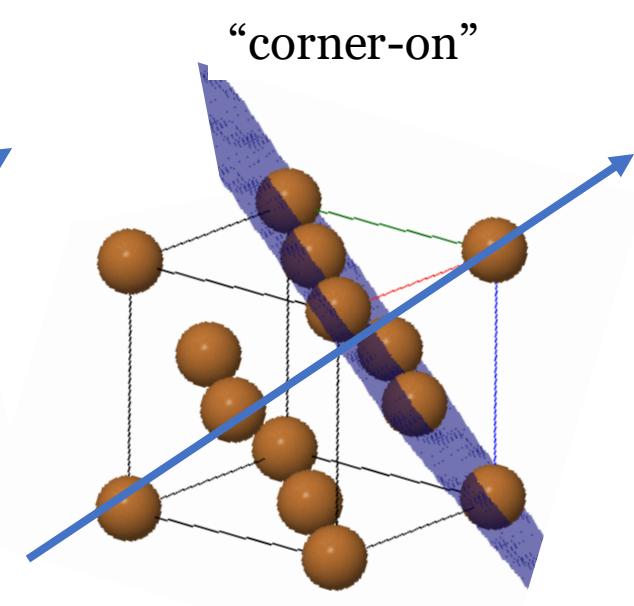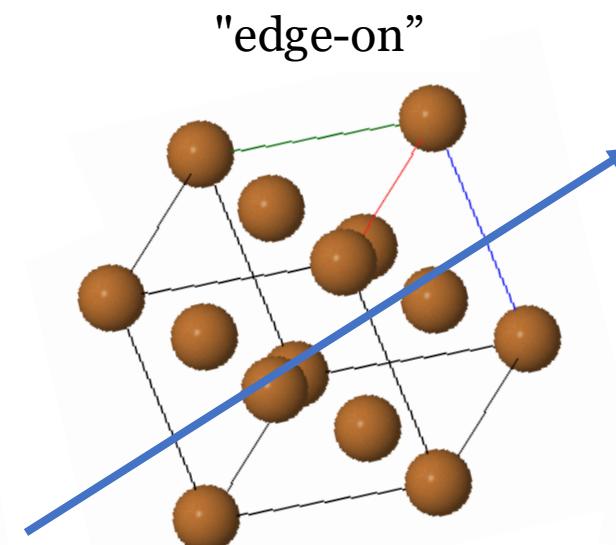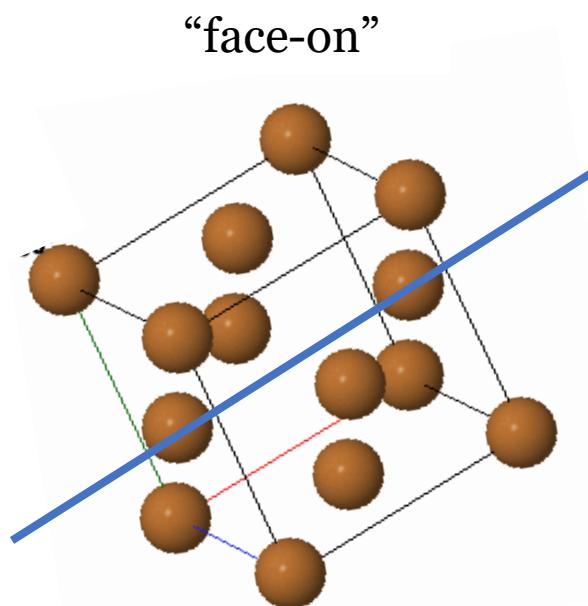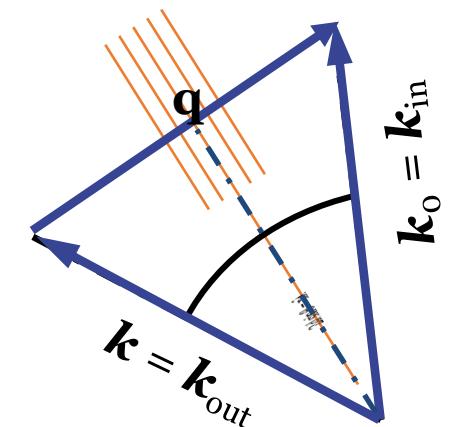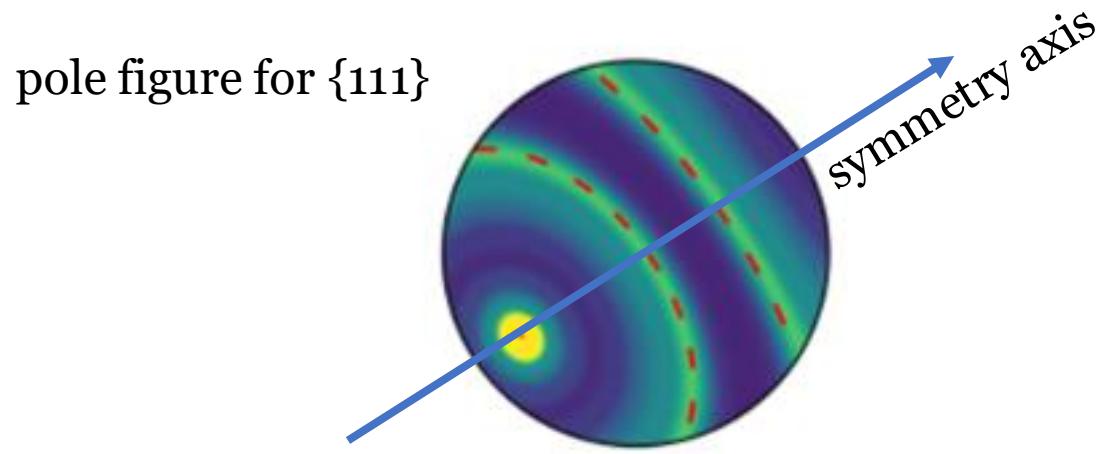


Texture analysis



- The pole figure
 - Given a specific set of reciprocal lattice vectors, $\{hkl\}$
 - The pole figure gives the probability of finding that plane in the direction, q

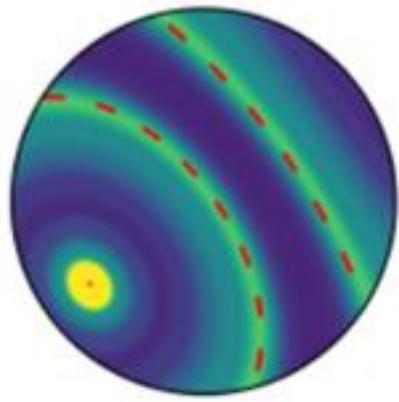

fiber texture: peaks smear into a ring

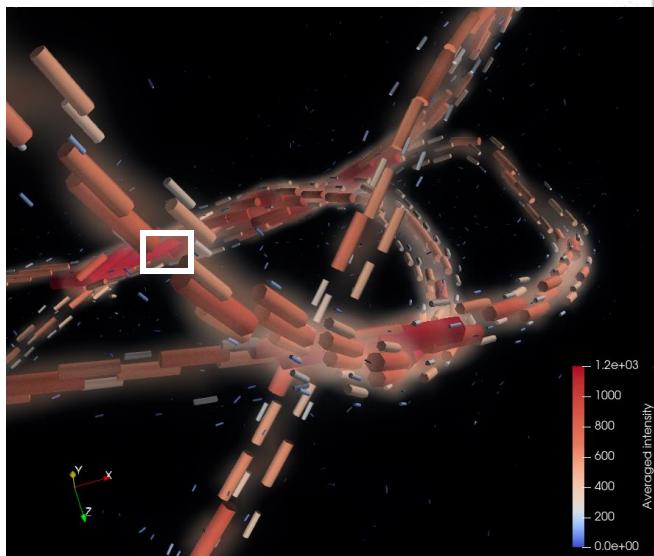


3D orientation distribution function (ODF)
how is the crystal lattice oriented with
respect to the actual sample

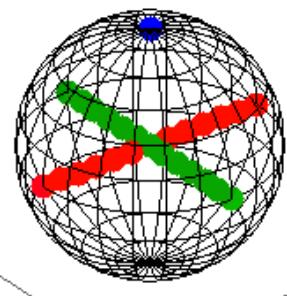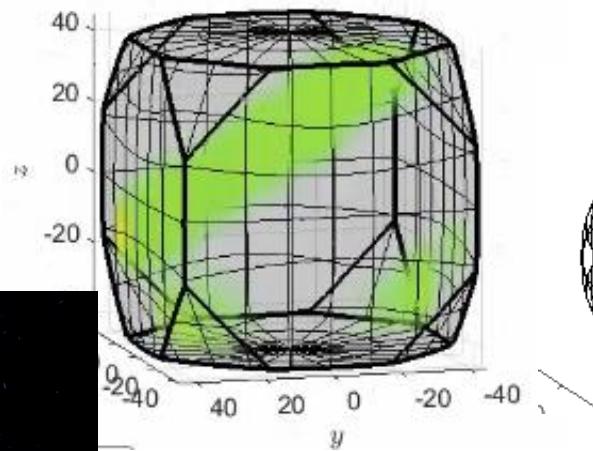


fiber texture: fixed
symmetry axis, but free
rotation around
→ a line

Texture analysis

- The pole figure
 - Given a specific set of reciprocal lattice vectors, $\{hkl\}$
 - The pole figure gives the probability of finding that plane in the direction, q


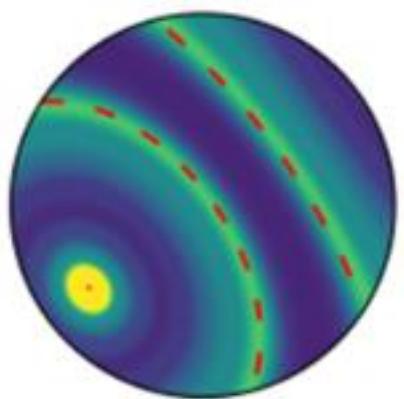


- The inverse pole figure
 - Given a specific direction y in the sample (here: the wire direction = draw direction)
 - The inverse pole figure gives the probability that y falls in a certain lattice orientation.

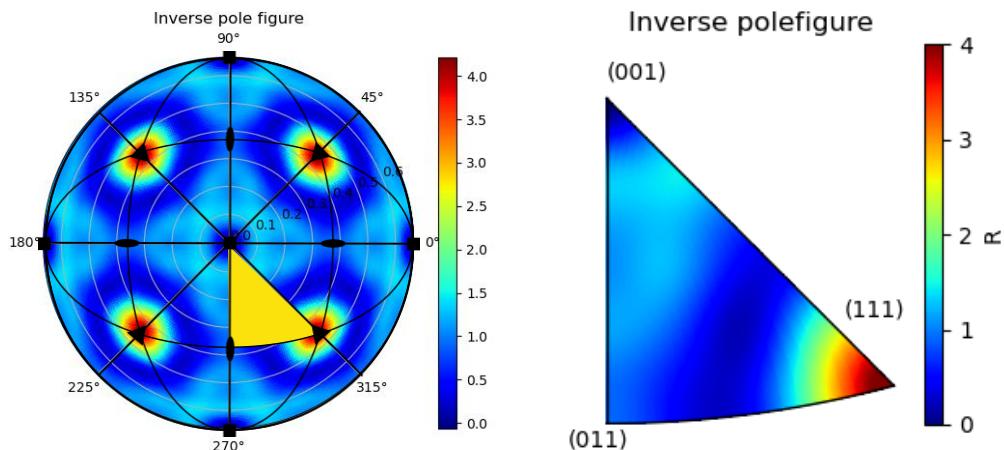

Inverse pole figures


electron back-scattered diffraction (EBSD)
on a cut with the surface normal to the wire direction
inverse pole figure map

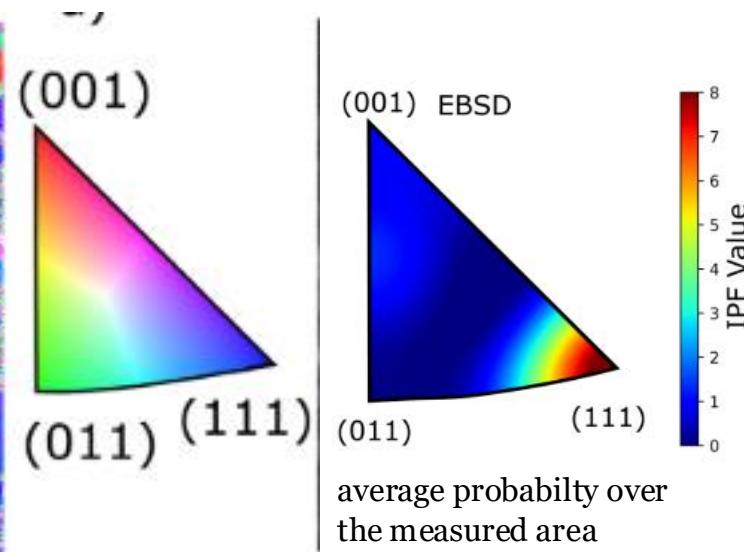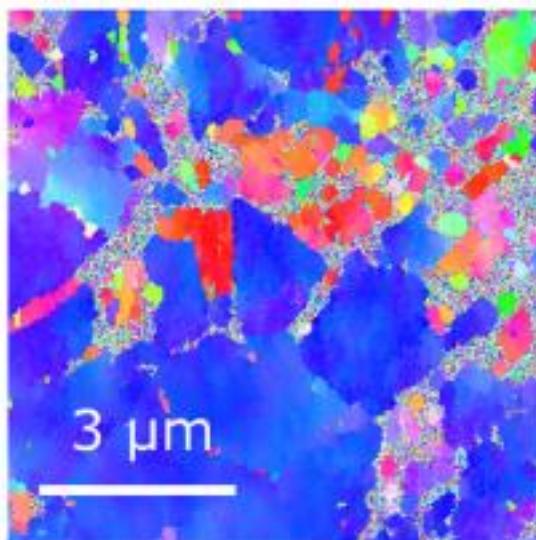

fcc

MSE-238

inverse pole figure map of the
snail shell


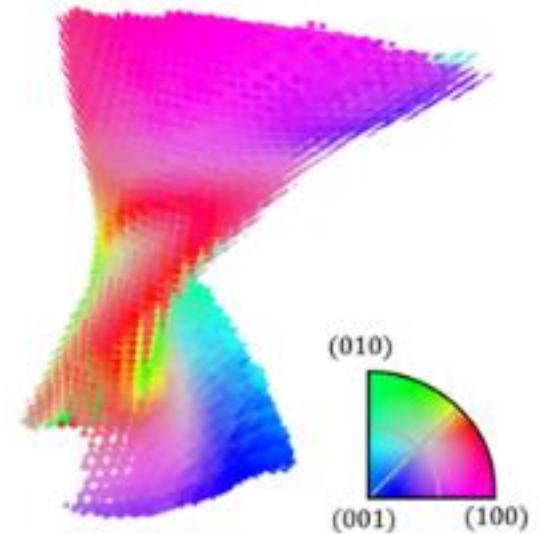


orthorhombic


note that the portion from the
circle shown depends on crystal
symmetry!

Fibre texture are very common

cellulose fiber

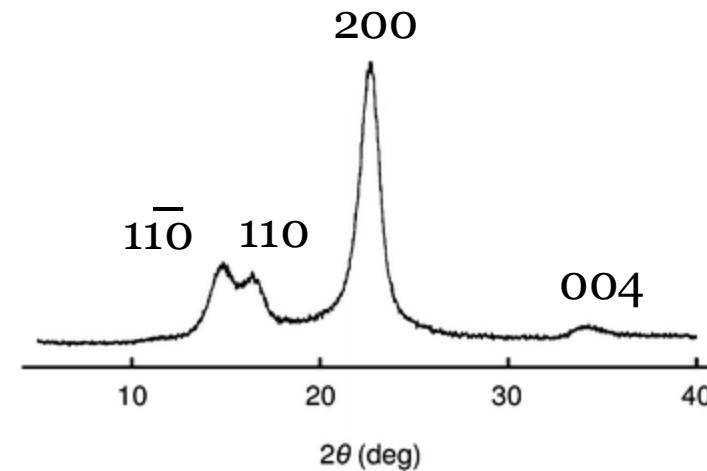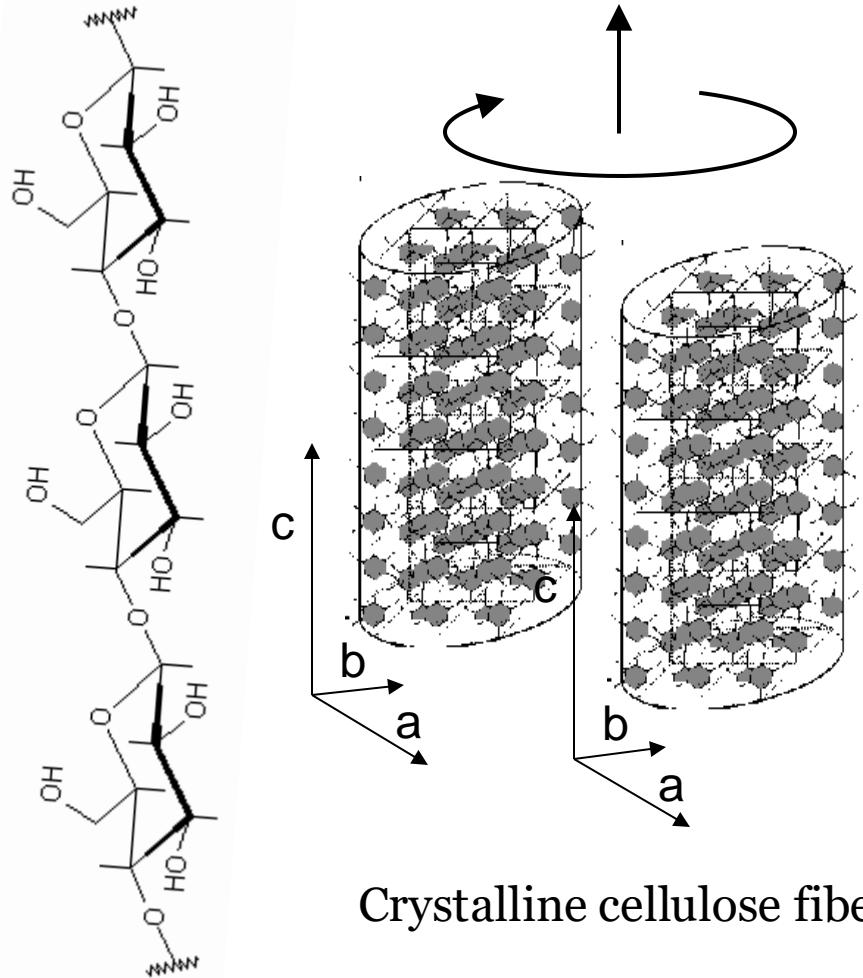

2D diffraction pattern
→ information of crystalline orientation

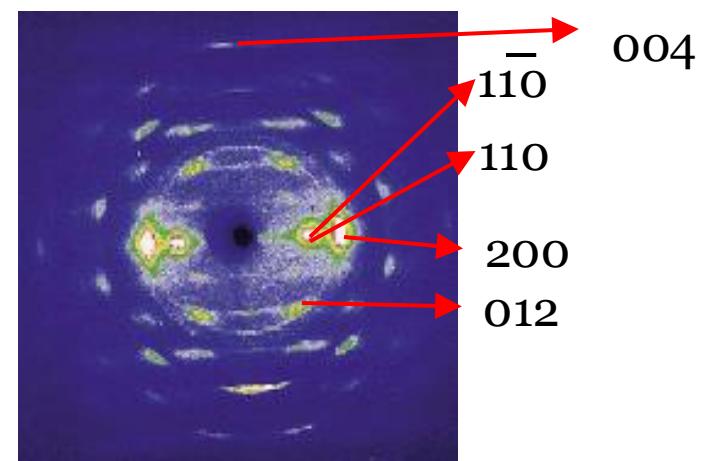


Sample types


single
crystal




twinned
crystal





crystal with
mosaic spread





textured
sample

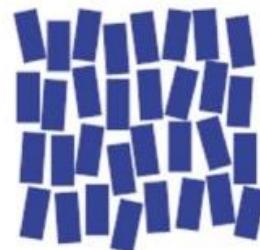

powder
sample

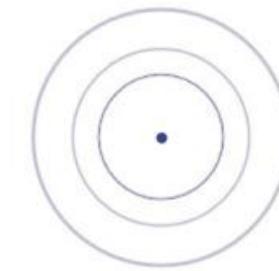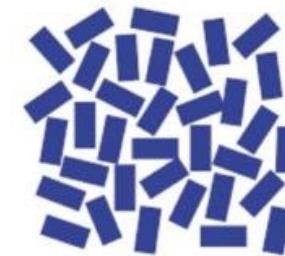


Powder diffraction

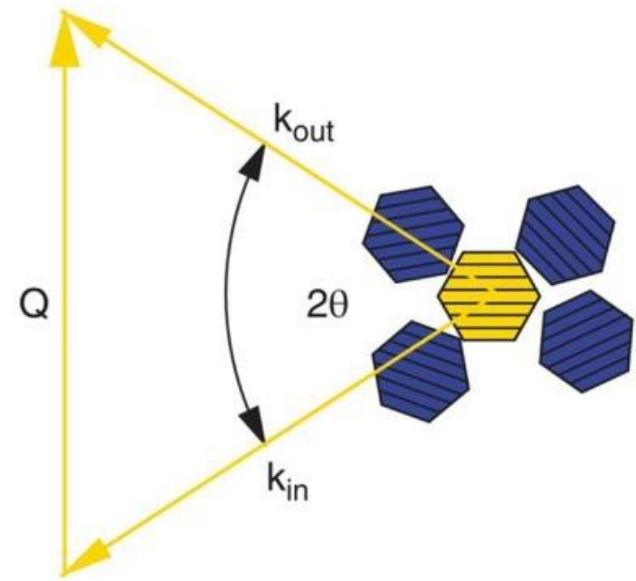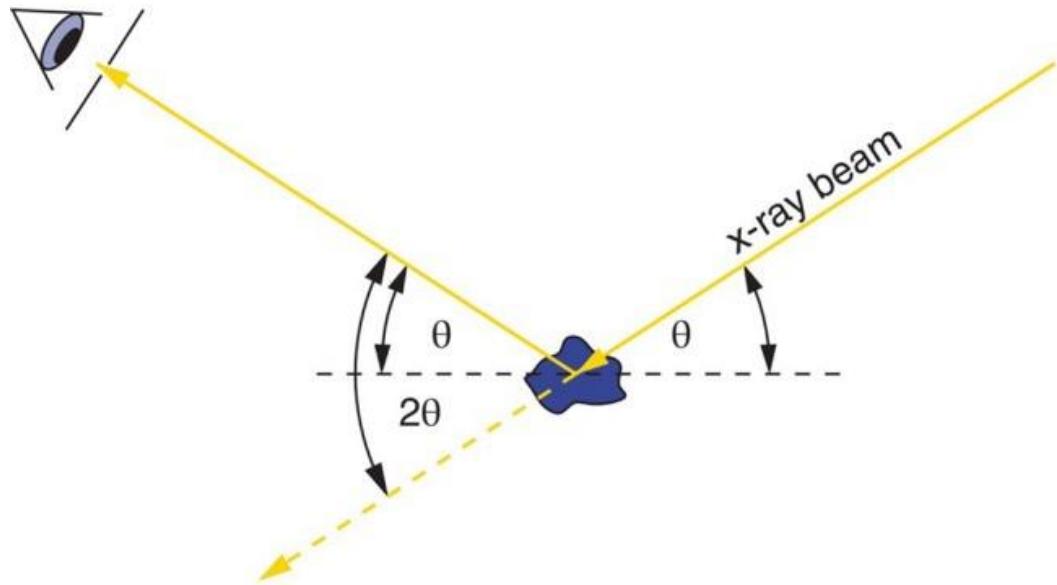

Conditions for diffraction in a powder sample. A detector will only see a diffracted signal if the d_{hkl} spacing, the orientation of the crystallite, and the angle of the detector 2θ to the incident x-ray beam lead to the diffraction condition being satisfied. This is fulfilled by the yellow-highlighted crystallite.

Single Crystal Diffraction

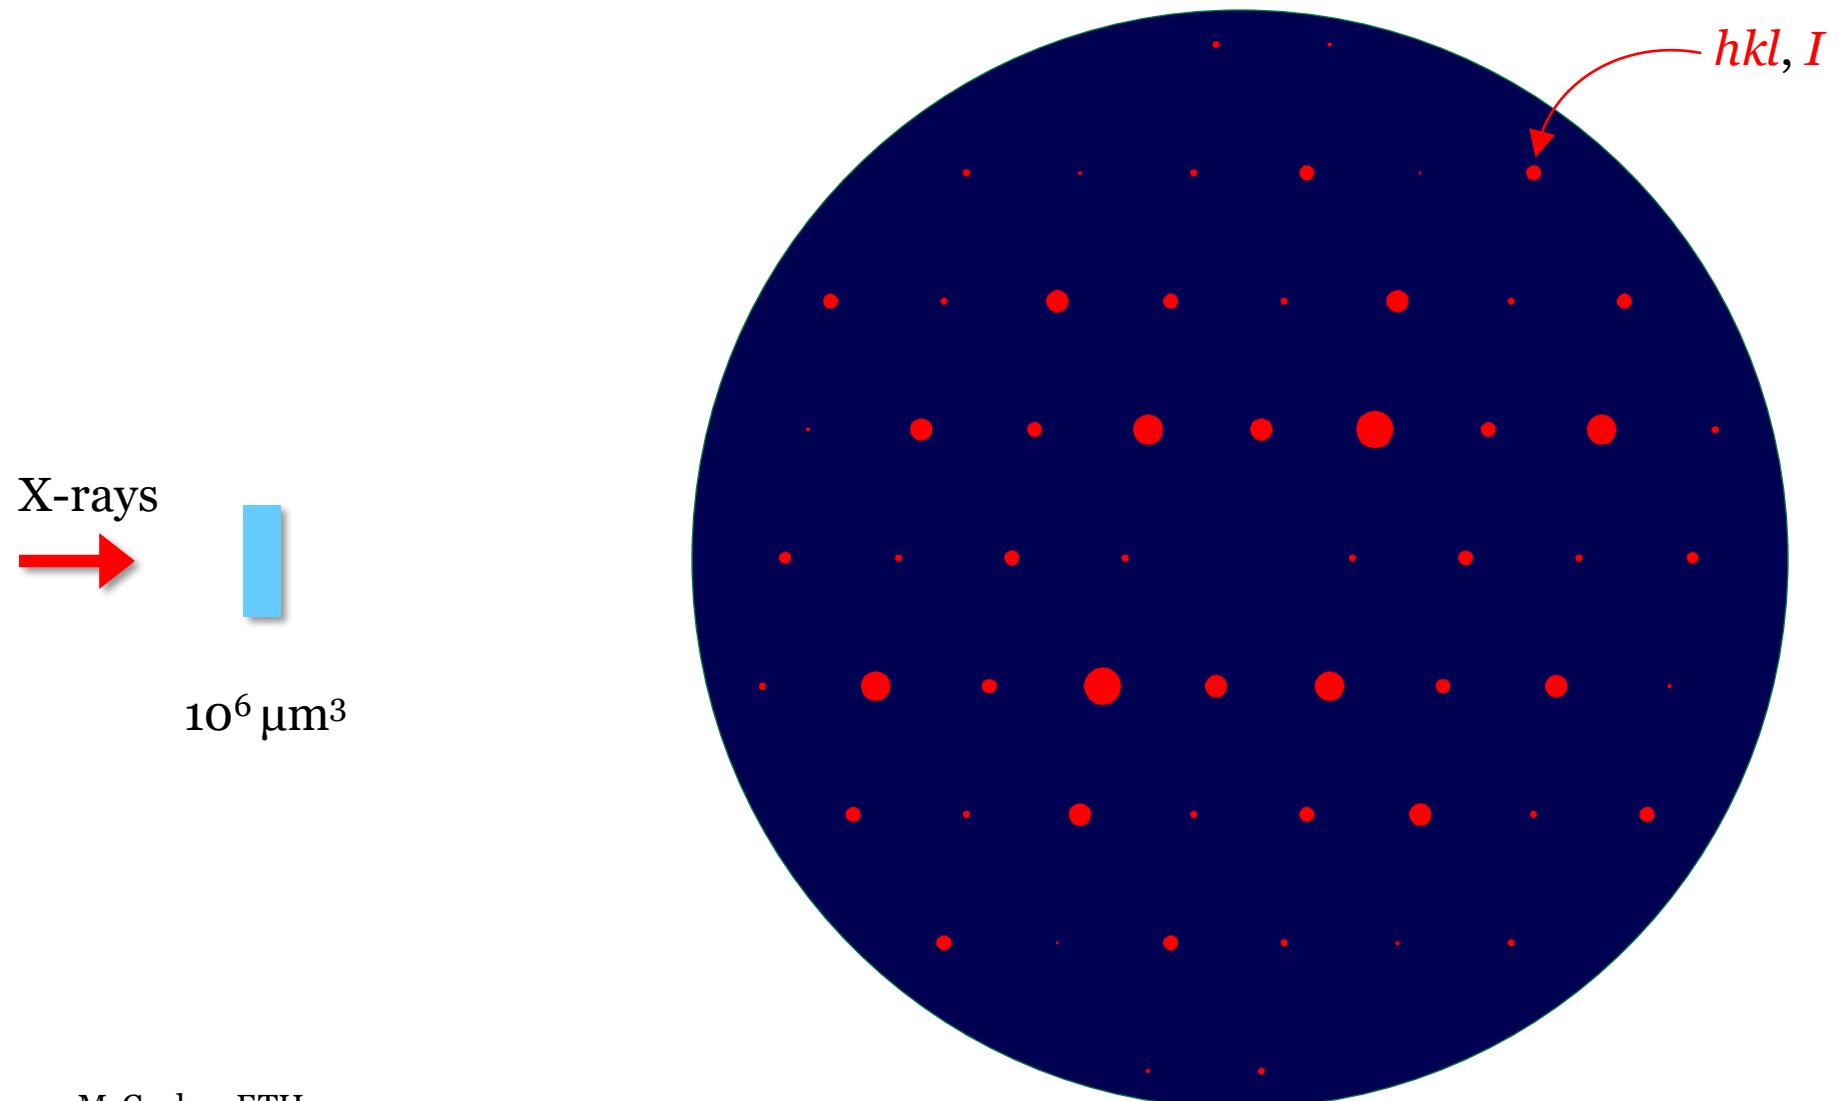


Powder Diffraction

X-rays




$1 \mu\text{m}^3$


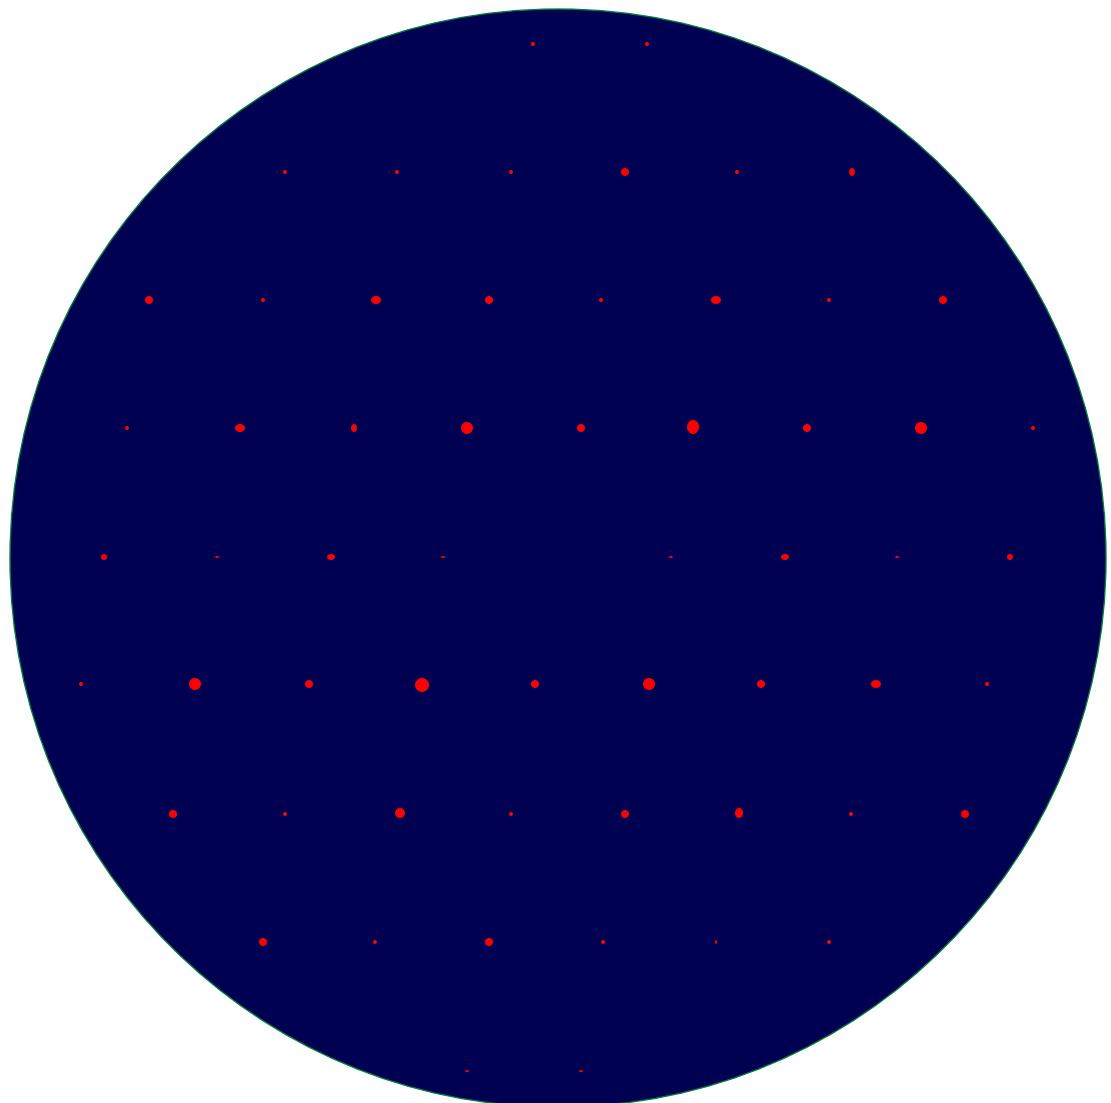


Powder Diffraction



X-rays

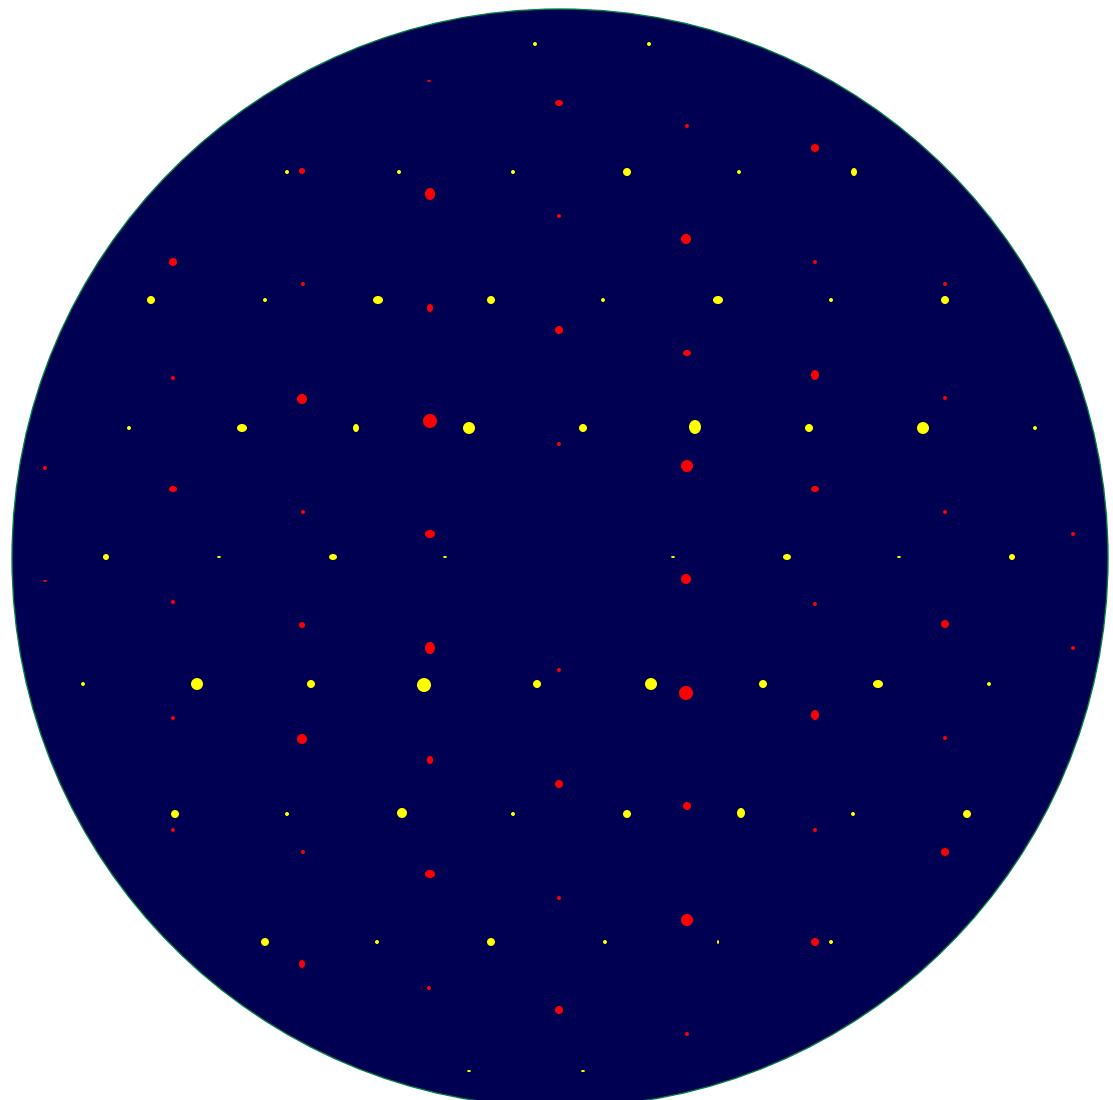

Powder Diffraction

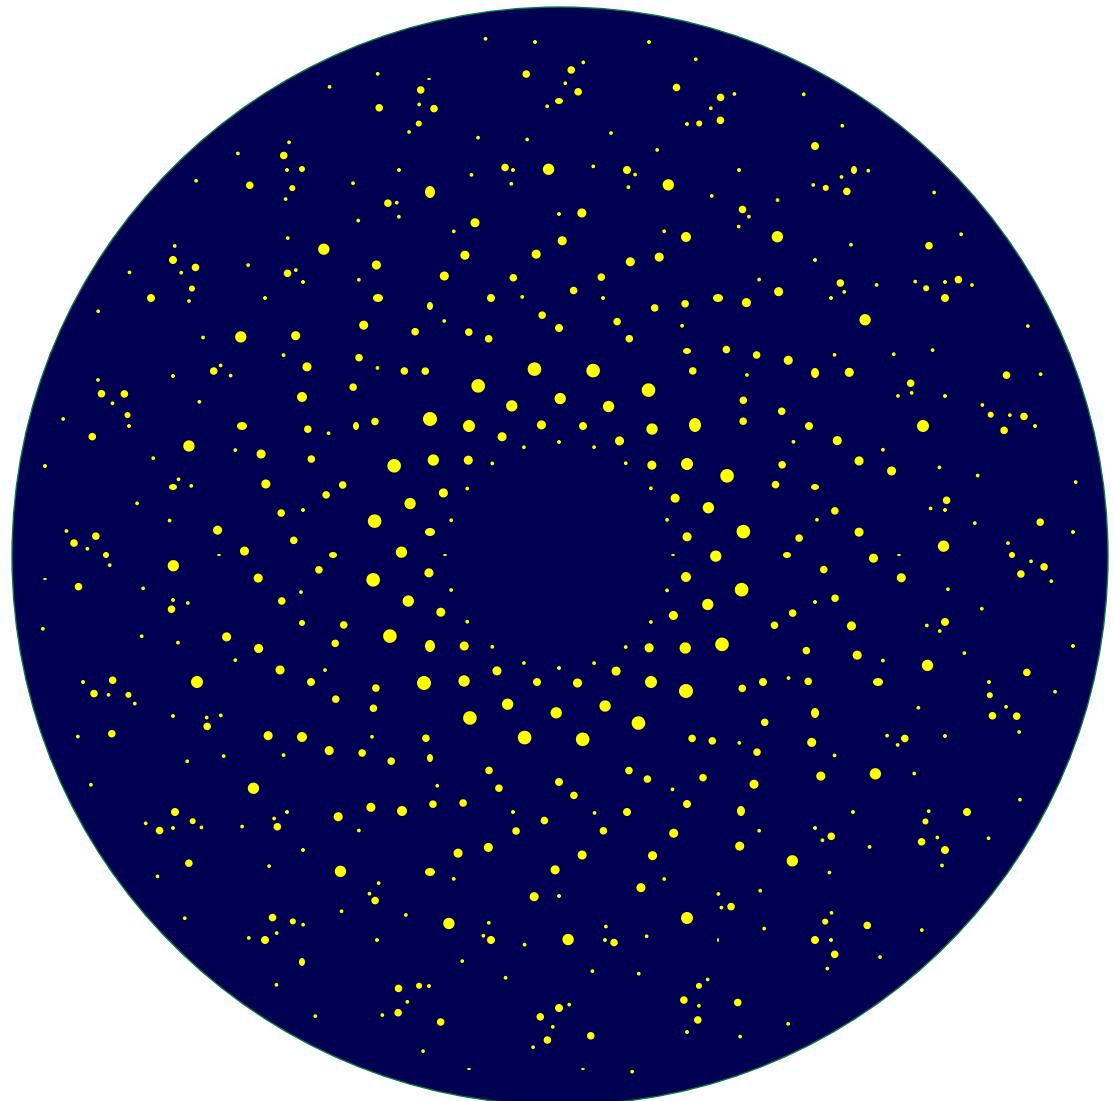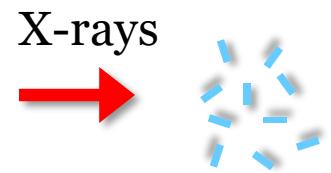


Powder Diffraction

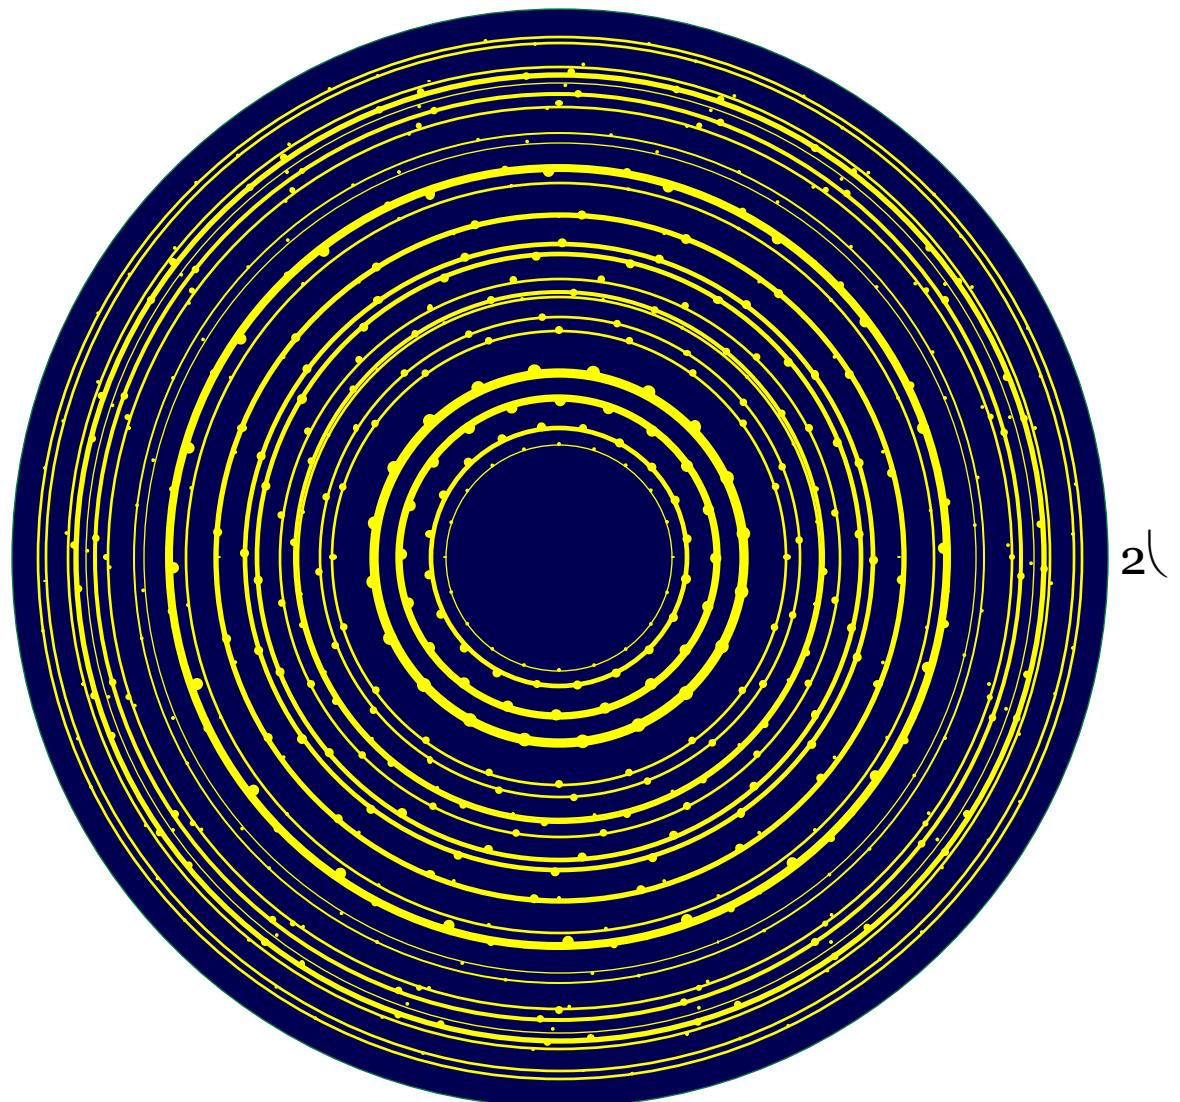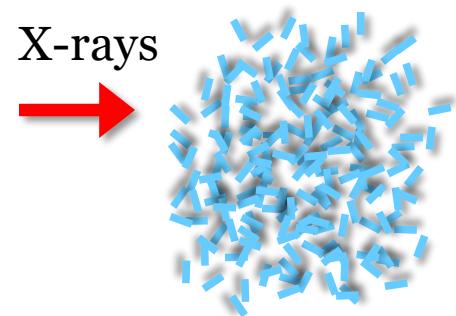

Polycrystallinity


Example: XRD of recrystallized aluminium

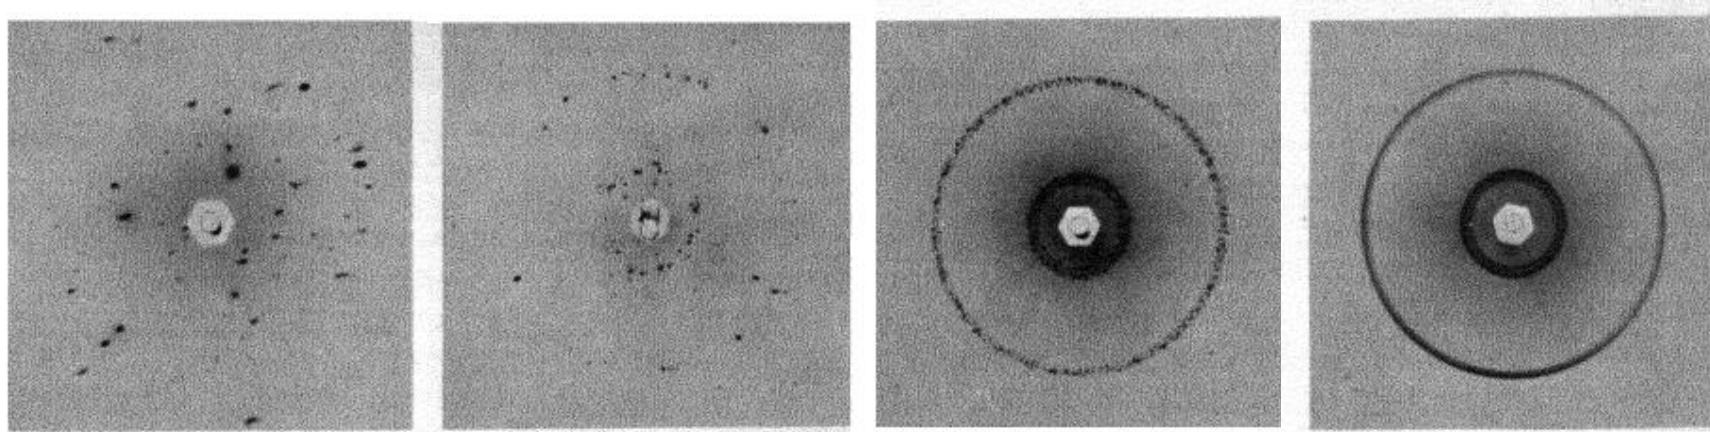

Decreasing grain size

Grain size be determined by comparing XRD-patterns recorded under **identical conditions** (in particular beam size!)

Schematic: number of grains in beam:
(smaller beams „see“ fewer crystallites)

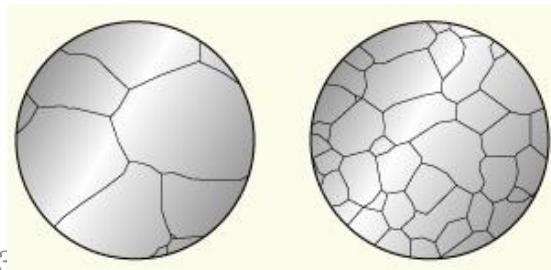


Sample types


single
crystal




twinned
crystal




crystal with
mosaic spread






textured
sample

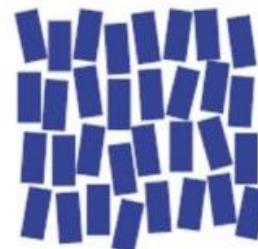

powder
sample

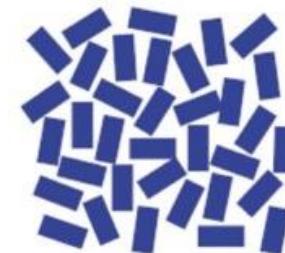


nanocrystalline
powder

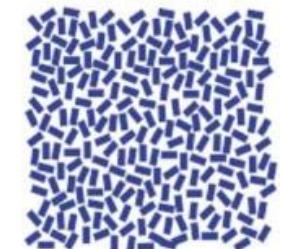

Nanocrystalline powder

- Example: nanocrystalline Ni

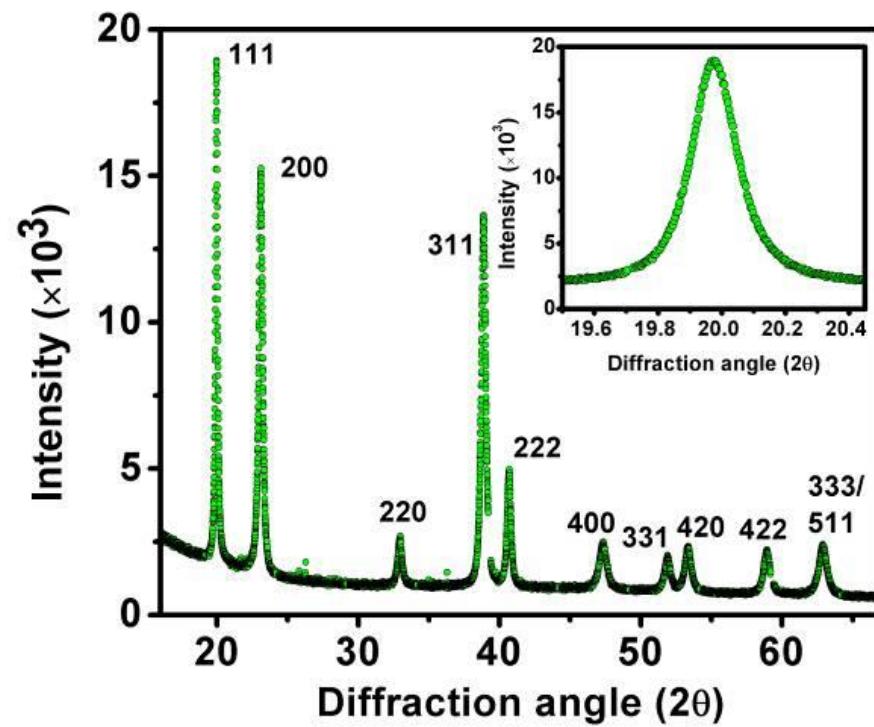

XRD

Imperfect microstructure

- large crystal with perfect atomic arrangement give rise to perfectly sharp peak (except of instrumental broadening)
- imperfections such as grain boundaries, defects at dislocations, stacking faults, stresses → peak broadening, as well as possibly peak position shifts
- small crystal size: “defect” as the long-range atomic arrangement is disrupted at the interface → peak broadening

XRD: Crystal size

Scherrer width


$$B = \frac{K \cdot \lambda}{D \cdot \cos \theta}$$

B: broadening of diffraction line at half maximum, in 2θ measured in radians


D: diameter of crystallite

K: constant, ≈ 1 , depends on crystal structure


small crystal \rightarrow broad peak

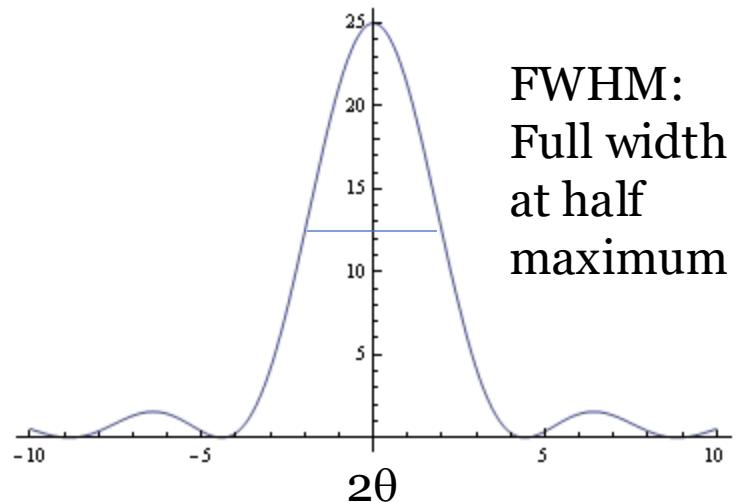

Plot versus Q

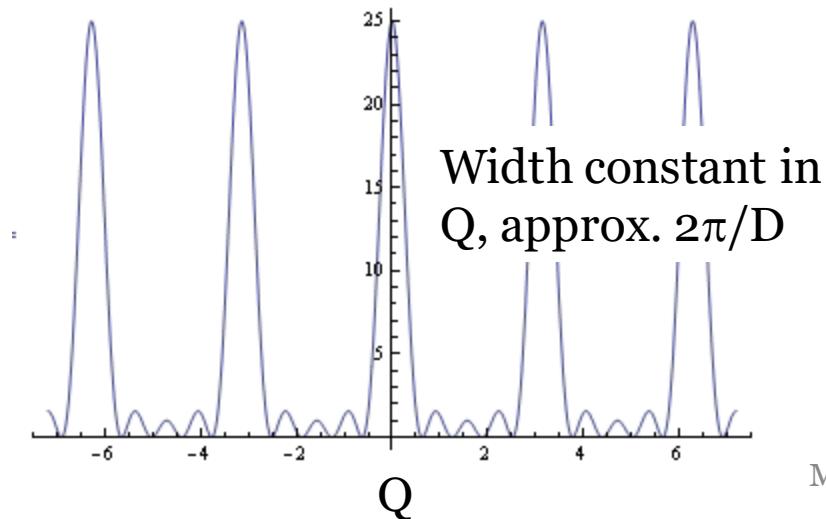



Plot versus 2θ

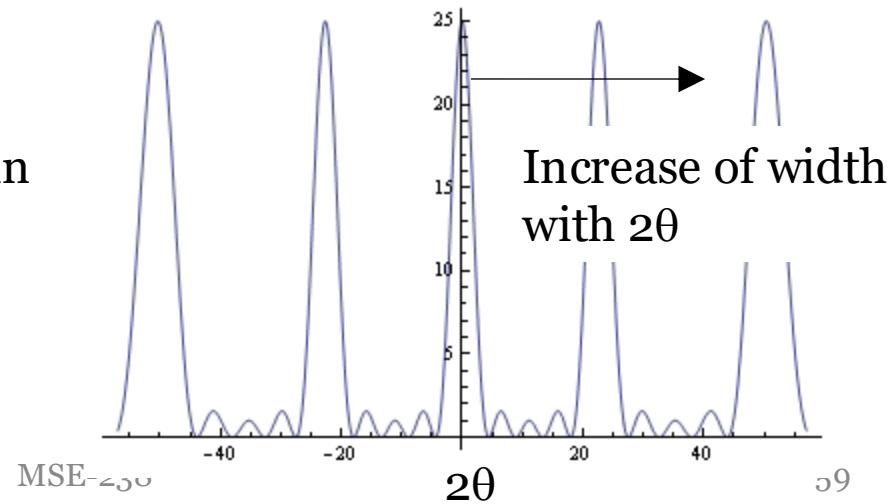

XRD: Crystal size

BaTiO₃ nanoparticles

Large-scale synthesis of BaTiO₃ nanopowders using a bioinspired process at nearly room temperature (25 °C). Size changes during sintering:

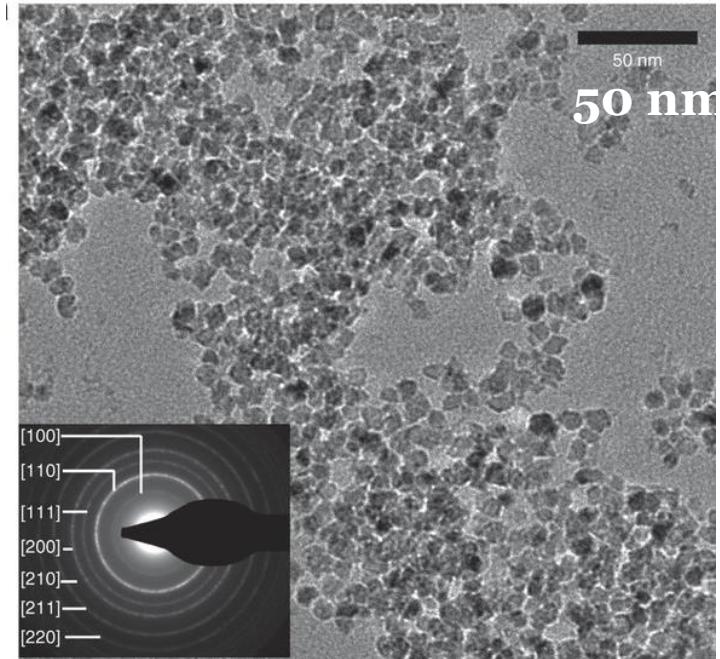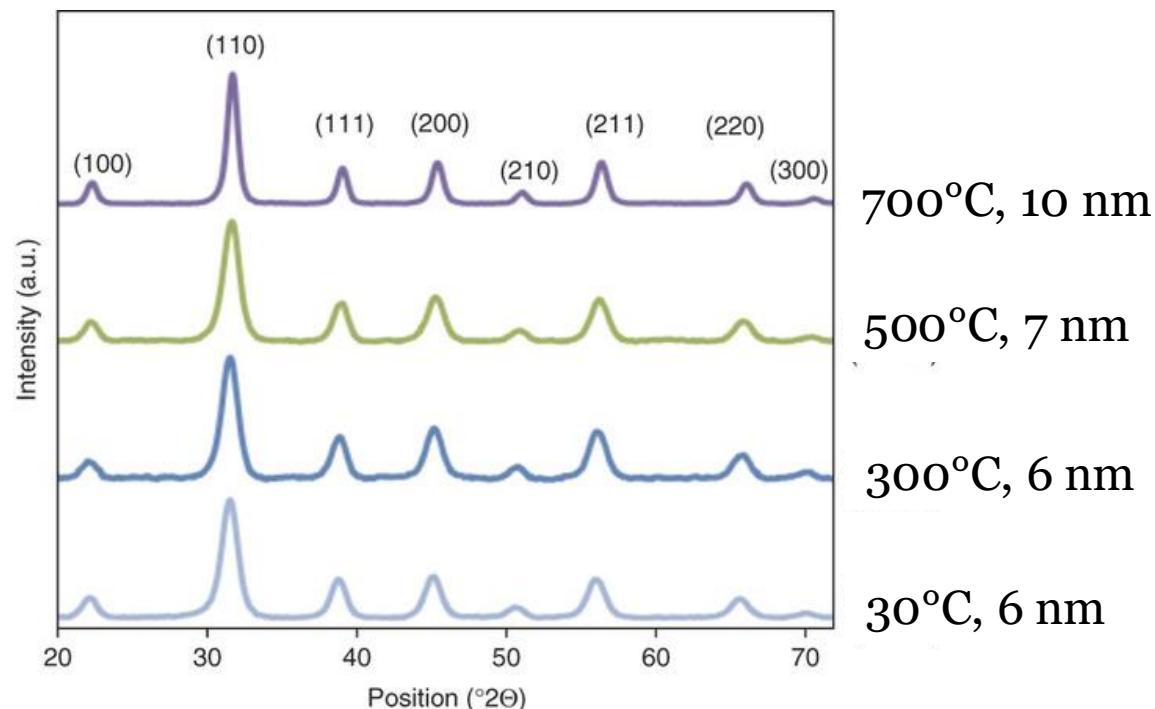

XRD: Strain broadening


Line broadening due to non-uniform lattice distortions.

Broadening related to strain:

$$b = \Delta 2\theta = -2 \frac{\Delta d}{d} \tan \theta = -2\epsilon \tan \theta$$


Often occurs with size broadening, difficult to separate.

Stronger dependence on θ (width increases for higher order reflections). Also different line shape.

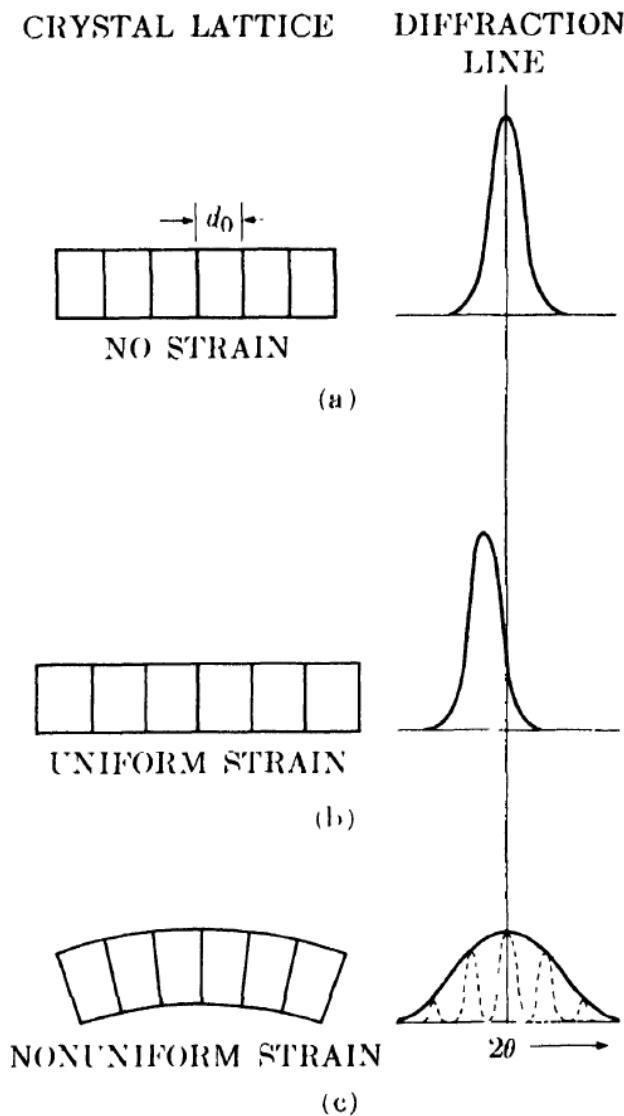


XRD: Strain broadening

Strain broadening
after cold rolling

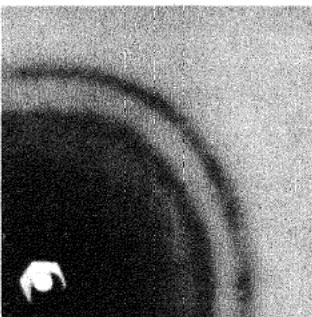


As rolled

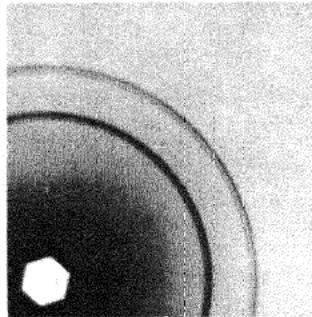


1 h at 300°C

Recovery

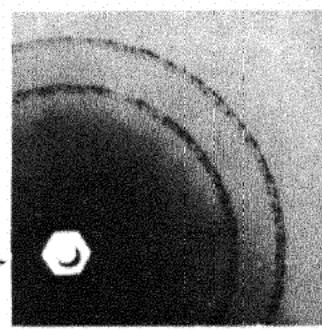

Recrystallization

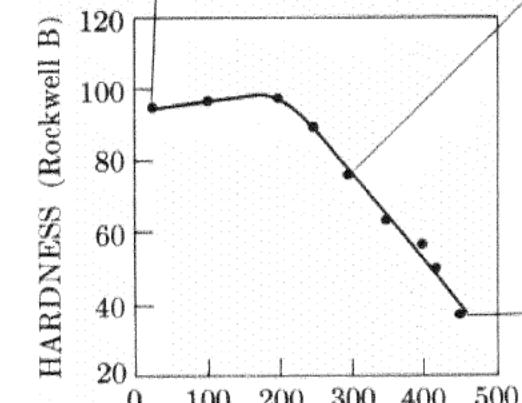

ANNEALING TEMPERATURE (°C)

(a) Hardness curve

XRD

Imperfect microstructure



- large crystal with perfect atomic arrangement give rise to perfectly sharp peak (except of instrumental broadening)
- imperfections such as grain boundaries, defects at dislocations, stacking faults, stresses → peak broadening, as well as possibly peak position shifts
- small crystal size: “defect” as the long-range atomic arrangement is disrupted at the interface → peak broadening
- when looking at more than one order of a reflection, the effect of ”size” and ”strain” can be separated
- Rietfeld refinement to get all information out of powder diffraction data

Peak profiles


- Peak profiles are determined by many factors. The most important ones include:
 - Resolution function
 - Coherent scattering length
 - Microstrain
 - Inhomogeneous elastic strain
 - Anti-phase boundaries
 - Faulting
 - Dislocations
 - Grain surface relaxation
 - Solid solution inhomogeneity
 - Temperature factors
- Peak profile is a convolution of the profiles from all of these contributions


Lab-source diffractometers for powder and single-crystal diffraction

<https://www.epfl.ch/schools/sb/research/isic/platforms/x-ray-diffraction-and-surface-analytics/x-ray-instrumentation/x-ray-scattering-instrumentation/>

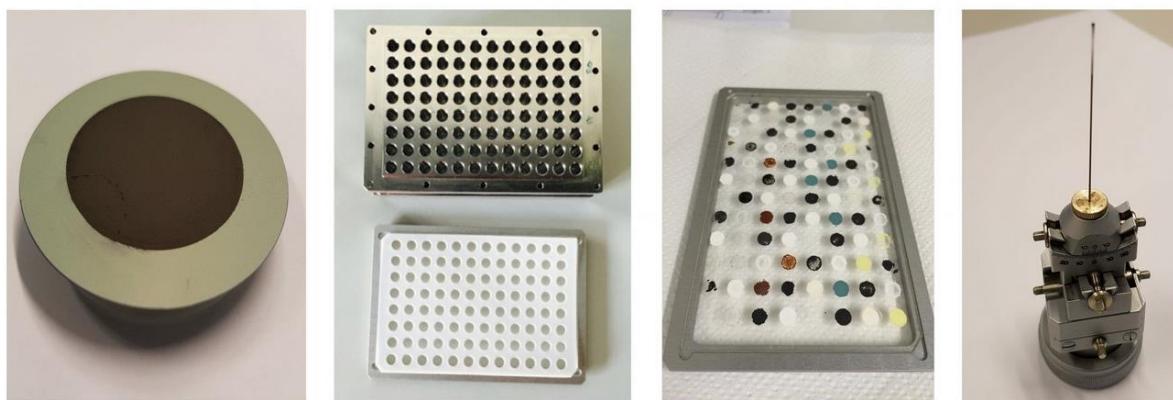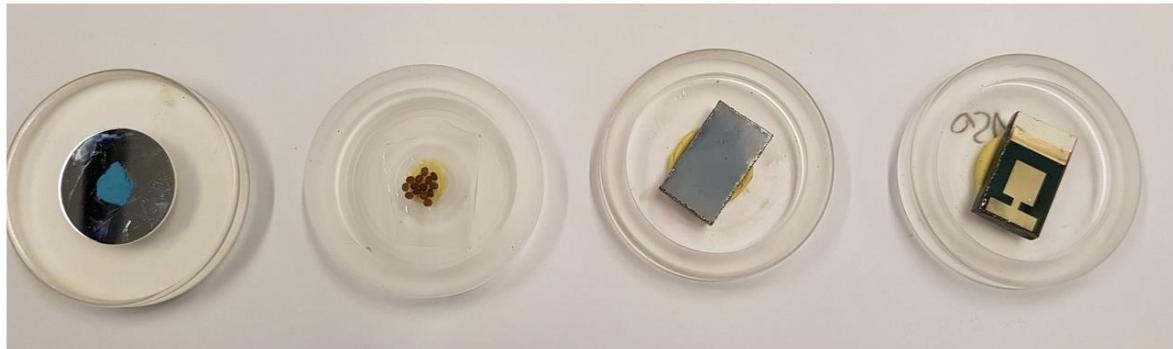


Samples: some examples of commonly measured samples are shown on **top**, from left to right: Metalorganic framework (MOF) powder sample, polymer beads, perovskite thin film, perovskite film with electrode. **bottom**, left to right: Solid Oxide Fuel Cell (SOFC), high throughput sample changer for synthesis robot (before and after loading), powder under Argon atmosphere in glass capillary.

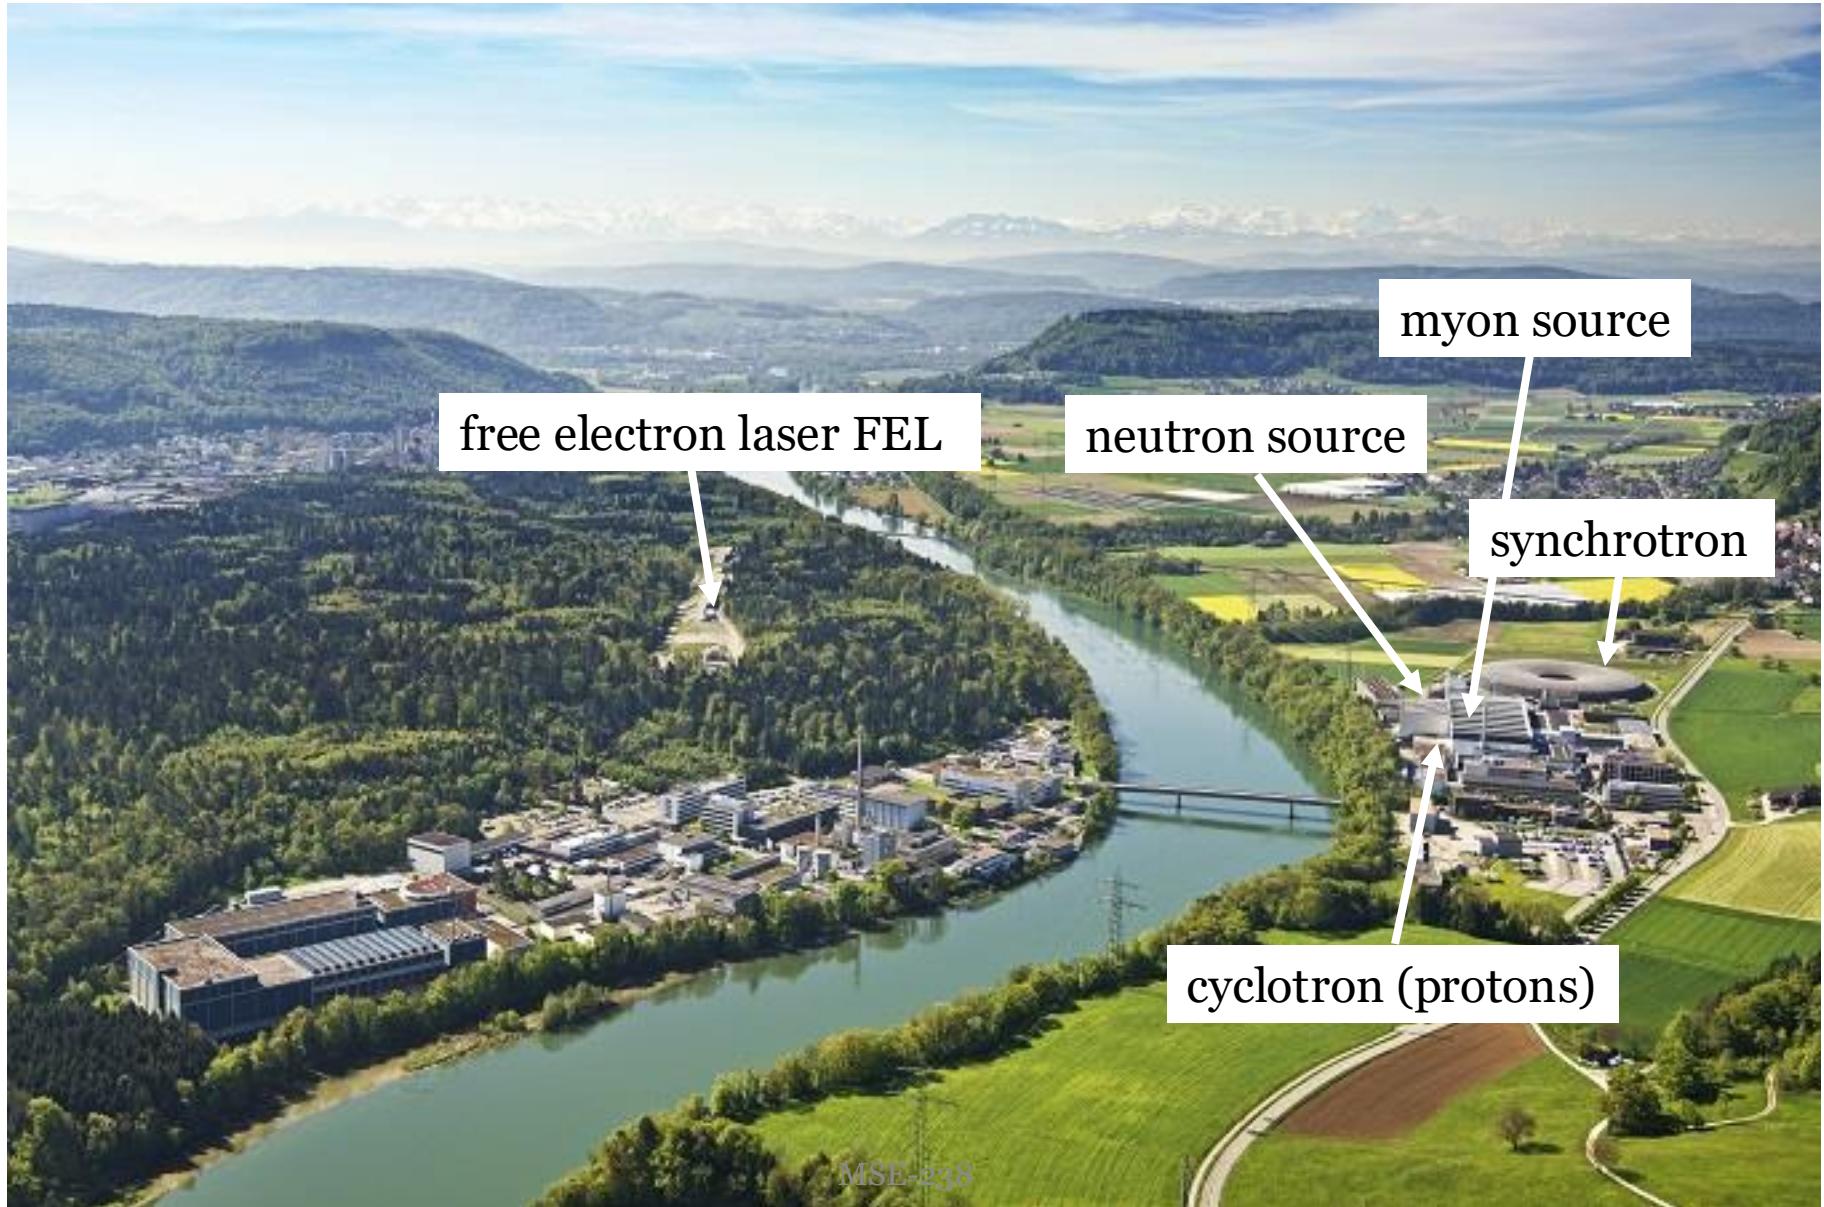

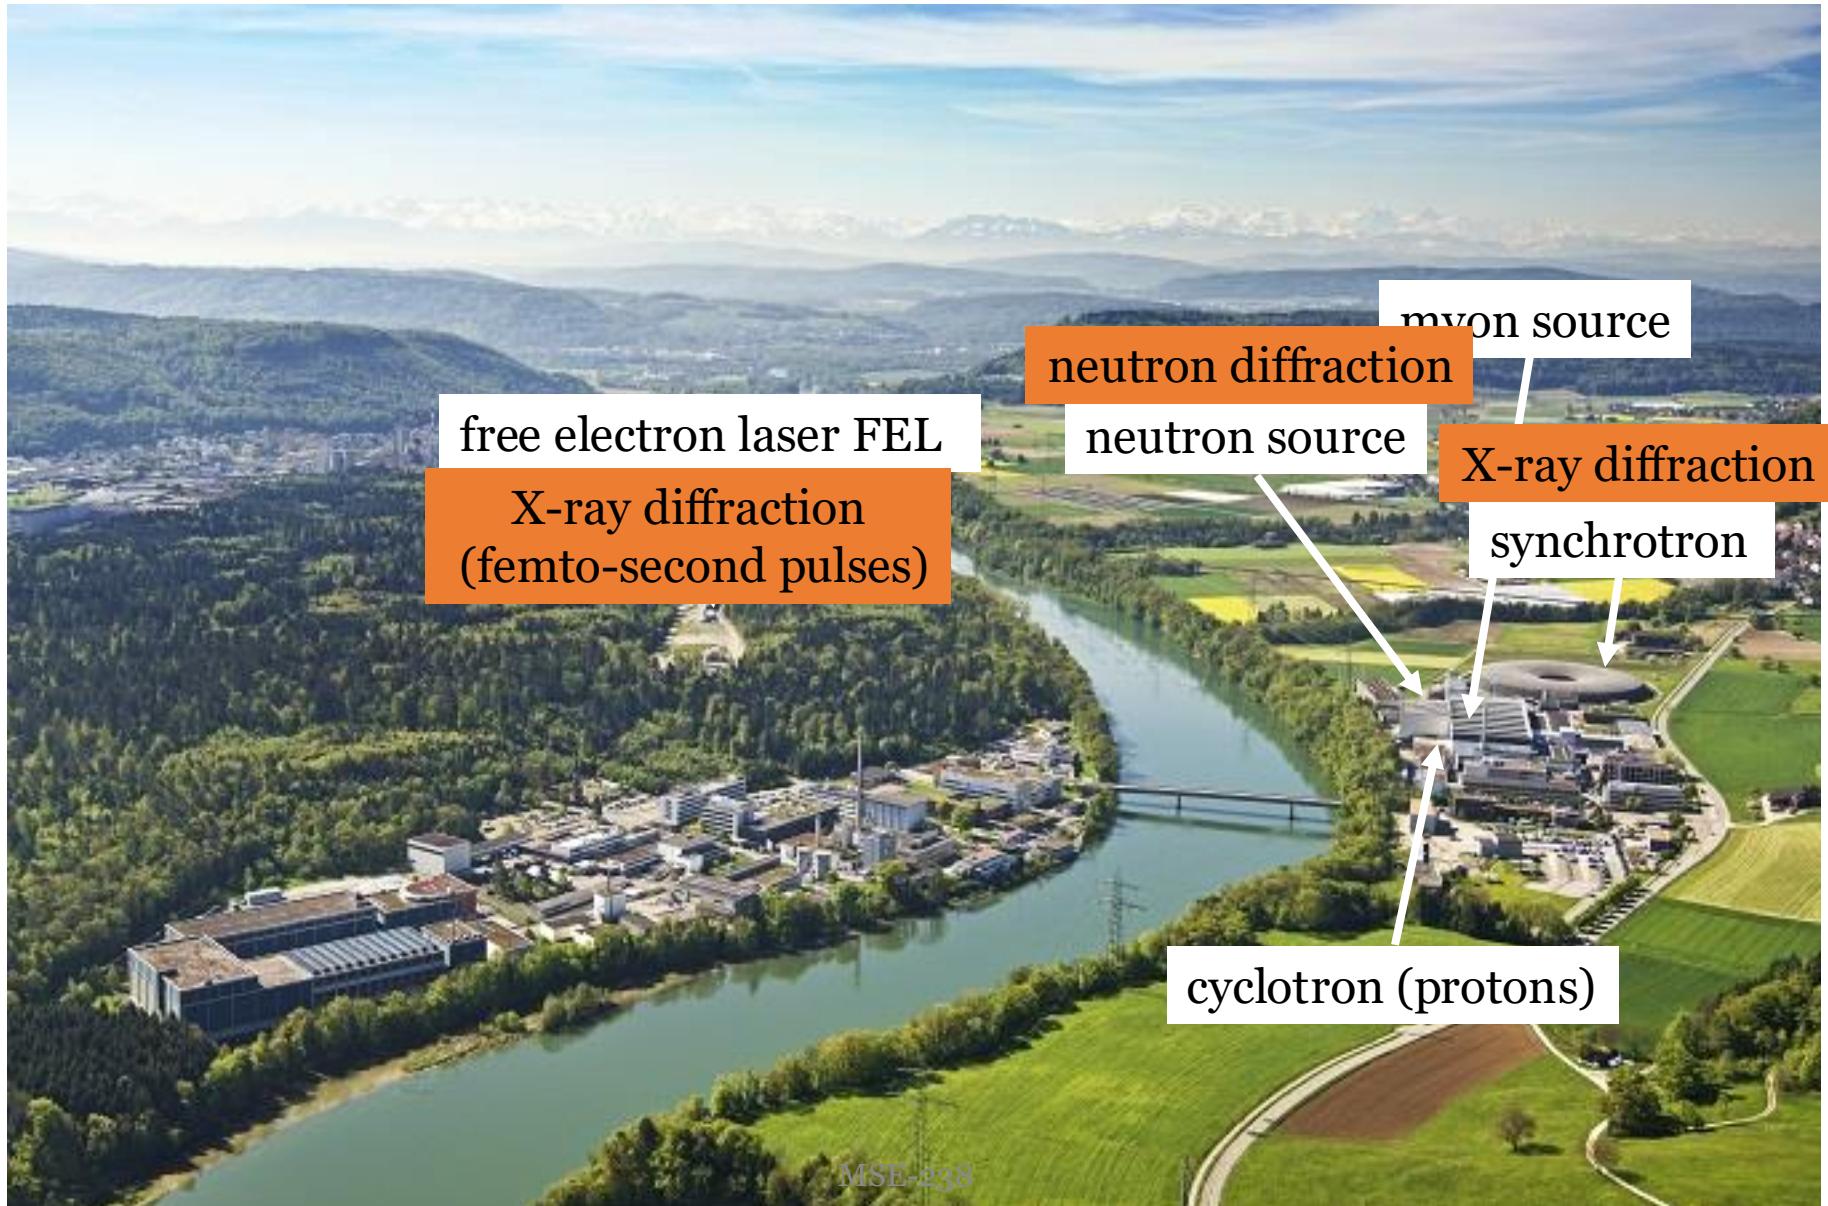

Lab source vs. Synchrotron

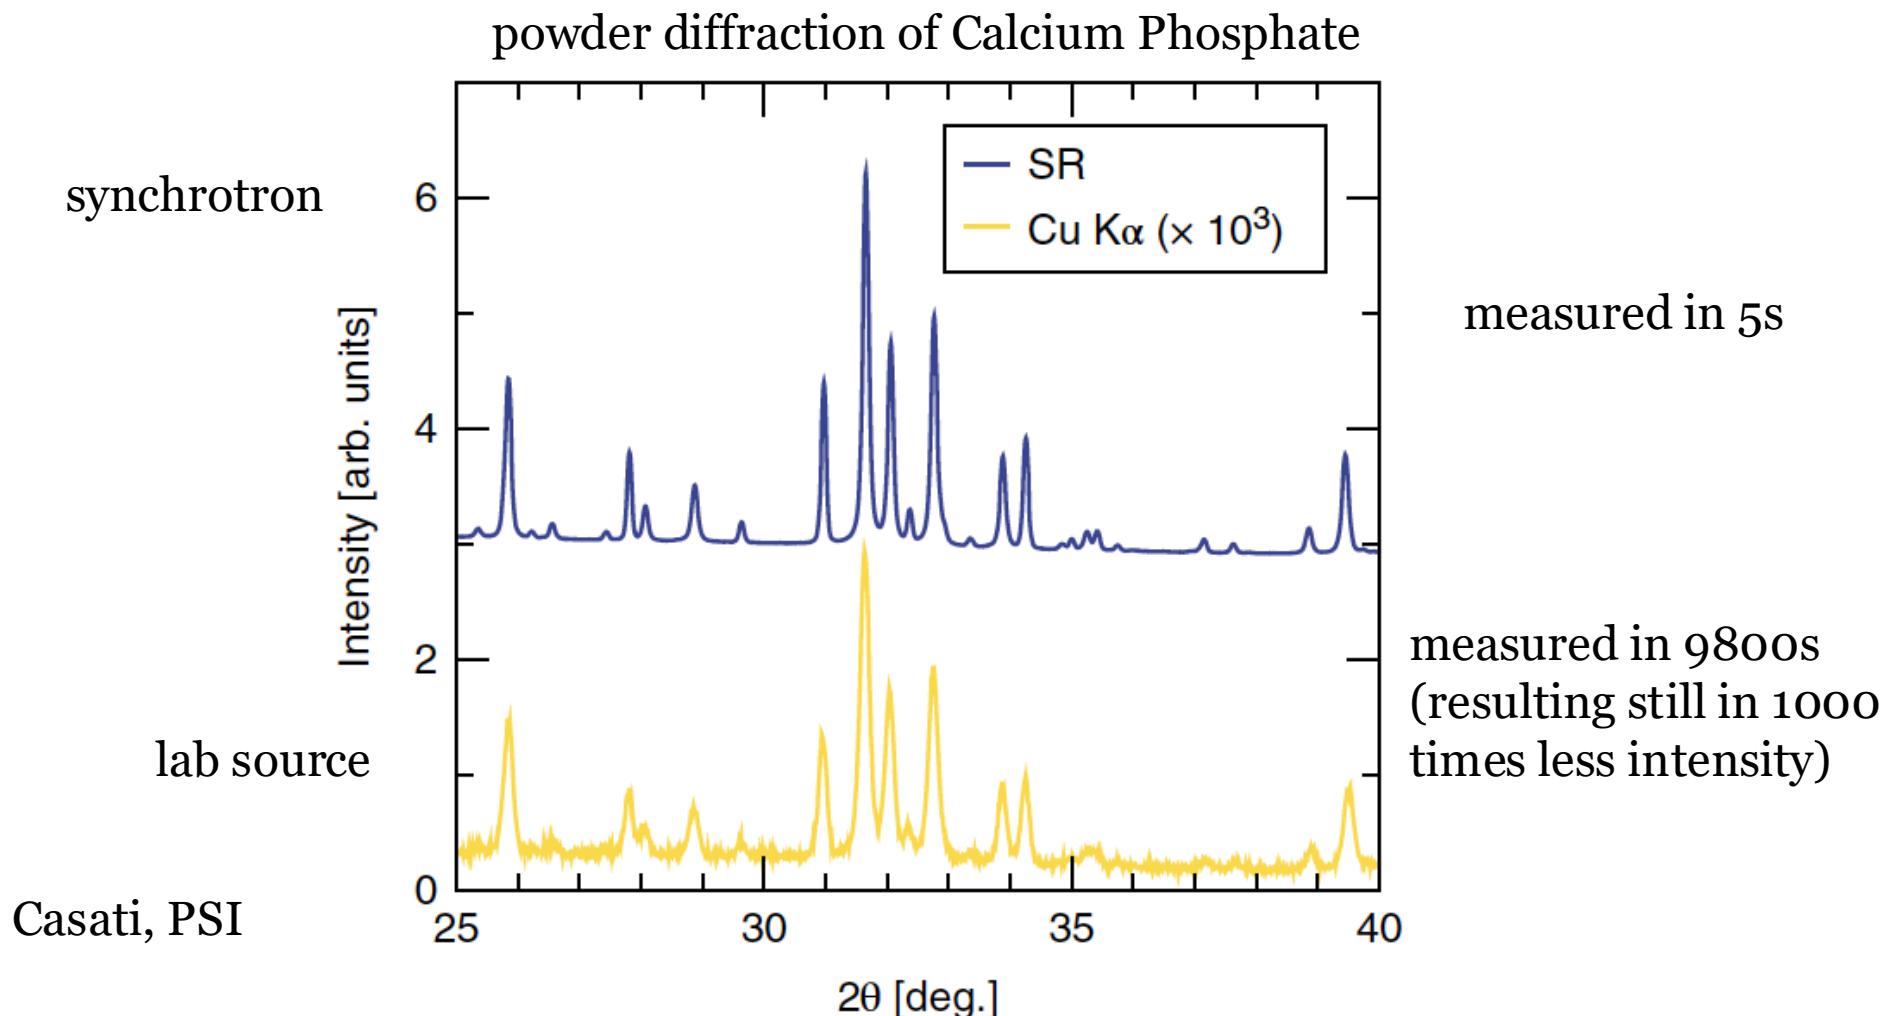

N. Casati, PSI

Summary

Diffraction:

- The scattering vector q
- Ewald sphere to determine which reciprocal lattice points are in Bragg condition in a certain geometry
- single crystal diffraction: rotation method or Laue diffraction
- imperfect crystals: defects, grainboundaries, strain: change peak width and/or position
- preferred direction of certain crystallographic directions: textured sample influence of symmetry
- polycrystalline material without preferred direction: “powder sample”
- X-ray diffraction Lab sources vs. synchrotrons